Math Paulding

MANUAL

OF

# ANALYTICAL MINERALOGY.

BY

FREDRICK ACCUM.

THE SECOND EDITION, WITH PLATES.

# A SYSTEM
### OF
## Theoretical and Practical
## CHEMISTRY,

*In Two Volumes with Plates, Second Edition with Additions.*

### By FRED. ACCUM.

——————" We think this work, as an elementary treatise, highly valuable. It is clear, explicit, and comprehenfive. The different properties of bodies are detailed with perfpicuity, and fupported by eafy appofite experiments. The particular defcriptions are preceded by a clear account of the nature of chemical action; and the facts that demonftrate the attraction and repulfion of bodies. The general laws of corpufcular attraction with the nature of chemical affinity are explained with peculiar fimplicity and precifion; and the latter is illuftrated by eafy experiments, &c."—*Critical Review.*

——————" This Work will prove highly acceptable to thofe who wifh to attain a practical acquaintance with the Science on which it treats. The Author exhibits throughout the work a great degree of chemical knowledge; and his method of communicating knowledge to others is engaging. With the practical part of the various proceffes in chemiftry he feems to be well acquainted; and the accuracy and precifion with which he defcribes them will render this work valuable, not only to tyros but to proficients in the Science."—*Philofoph. Mag.*

---

*Reviews of the First Edition of the*
## Practical Essay
### ON THE
## ANALYSIS OF MINERALS.
### *By FRED. ACCUM.*

" This Compendium is excellently contrived to affift the lefs experienced analyft; and even the more experienced chemift will find in it hints of no little importance, which he can fcarcely difcover in fyftematic authors."—*Critical Review.*

" The Author of this Work has been long known as an able practical Chemift; and his Effay contains clear and copious directions for the analyfis of mineral fubftances in general, &c.—Mr. Accum's Effay may be pronounced an ufeful compendium not only for the Mineralogift, but for all who deem fubjects of this nature worthy of their attention."—*European Mag.*
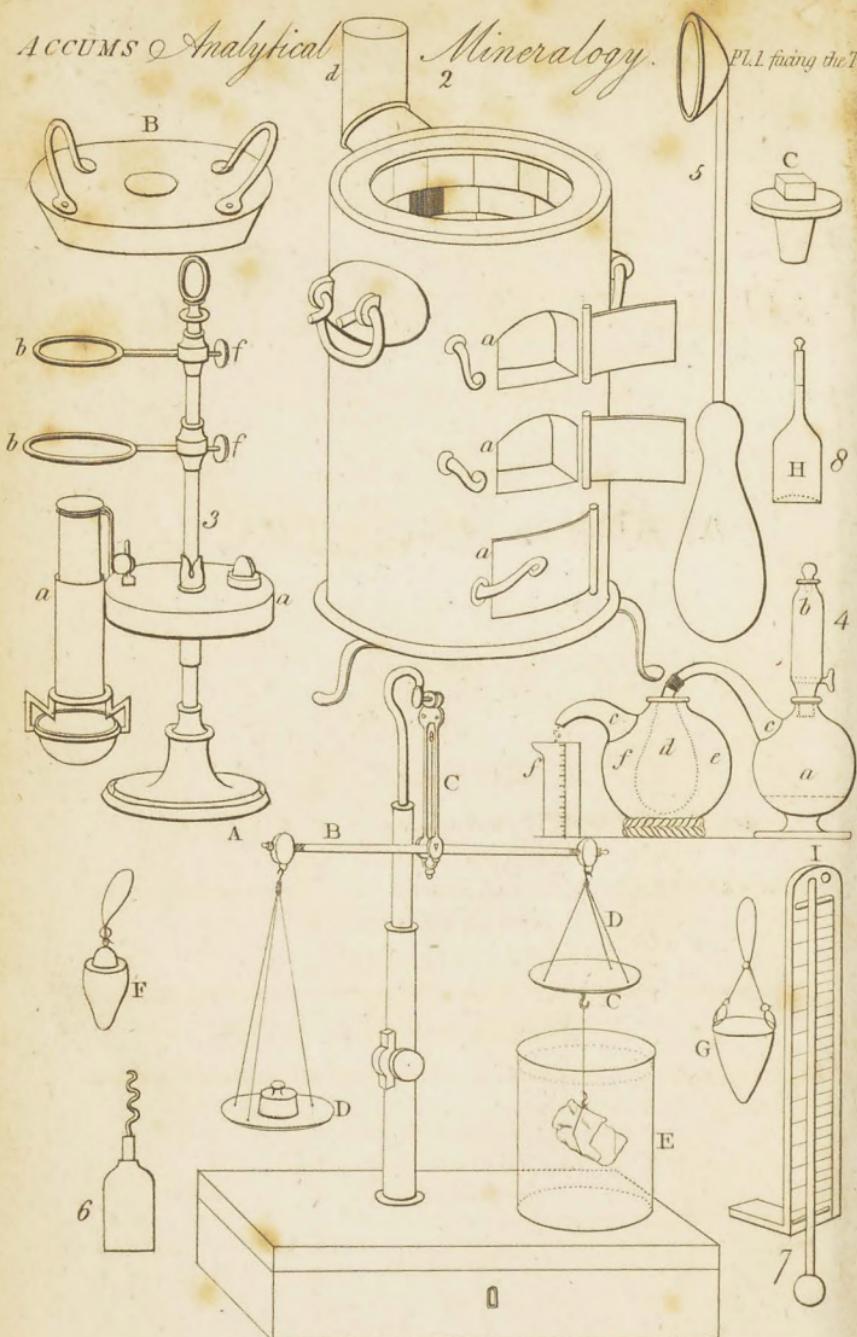
*Fig.1.*

A

# MANUAL

OF

# ANALYTICAL MINERALOGY,

INTENDED TO FACILITATE THE

## PRACTICAL

## ANALYSIS OF MINERALS.

IN TWO VOLUMES.

BY

## FREDRICK ACCUM,

HONORARY MEMBER OF THE ROYAL IRISH ACADEMY;

OPERATIVE CHEMIST;

LECTURER ON EXPERIMENTAL CHEMISTRY, AND ON MINERALOGY,

AND PHARMACY.

SECOND EDITION.

Vol. I.

TO

# RICHARD KIRWAN, Esq.

PRESIDENT OF THE ROYAL IRISH ACADEMY,

FELLOW OF THE

ROYAL SOCIETIES OF LONDON AND EDINBURGH, &c.

AS AN ACKNOWLEDGMENT

OF

THE GREAT ADVANTAGES AND IMPROVEMENTS

WHICH

THE SCIENCE OF MINERALOGY HAS RECEIVED

FROM

HIS NUMEROUS AND ADMIRABLE LABOURS,

THIS MANUAL

OF

## ANALYTICAL MINERALOGY

IS

RESPECTFULLY INSCRIBED.

# PREFACE.

11, *Compton Street, Soho.*

I~N~ the lines prefixed to the first edition of this book the reader is informed that the work was not originally drawn up for public inspection, but that it was intended to serve as a text book for my pupils, to render more useful the Series of Lectures I deliver on the subject of which it treats. By the repeated desire of others, whose judgment and advice I respect, it was afterwards re-published in the manner it was originally composed.

The unexpected public and private approbations which the work met with, amongst a scientific public, are flattering proofs that my labours were considered as not altogether useless.

And the rapid sale of an uncommonly large edition, which was disposed of in less than eighteen months after its publication, gives me reason to think that the votaries of the science are numerous. Indeed there is no extravagance in saying that there never was a time in which the science of Mineralogy was cultivated in Great Britain with more ardour and success than at present, and in which it has contributed more strikingly to the improvement of our Arts, and the extension of our Commerce. The foreign mining establishments and manufactures are overwhelmed and greatly ruined by the dreadful political storms in which they have been, and still are, engaged; whereas the British miner can carry on his subterraneous workings without molestation, and with success. The smelter is not driven from his furnace, nor the potter from his lathe, by political commotions; and the theatre of the war which we wage with foreign enemies is, and, whatever they may desperately attempt, will continue to be remote.

In the lines I now present to the judgment of the public, the original plan of the former work has been kept in view : a more enlarged scale however has been pursued, and an endeavour has been made to render the book more useful or perfect, and better adapted for those cultivators of the science, who have neither leisure nor inclination to obtain practical knowledge among the furnaces of the operative chemist, or to turn over the numerous treatises through which the necessary information lies scattered.

The whole has therefore been written anew, and the additions that have been made alone exceed twice the contents of the original publication.

I have endeavoured to condense into as narrow a compass as possible the general rules and practical proceedings necessary for the chemical examination of minerals, by pointing out to the student concise directions for conducting the analyses of metallic ores, of earths, stones, and other minerals, so as to enable him to ascertain, with the book in his hand, the nature and composition of all such mineral substances as he may

meet with; and to determine the uses to which
they may be applied.

And, as it is impossible to advance general
rules that might be applicable in all cases, I
thought it necessary to illustrate, in a series of
experiments, not only the practical operations
of analysis of such minerals as are commonly
met with, but I have exemplified likewise the
processes necessary for the examination of those
substances as occur but rarely in nature. To
give effect to this undertaking, I have syste-
matically exhibited all the substances which
form the empire of the mineral kingdom, and
have endeavoured to point out, under each class
and genus, the best practical proceedings of the
day, so as to present to the student a register of
the present state of analytical mineralogy, in-
terspersed with illustrative examples, taken from
the Memoirs of Klaproth, Vauquelin, and other
celebrated analysts.

I have also endeavoured to detail the respective
analyses and individual operations with as much
accuracy and fidelity as my slender abilities

could suggest. I have seldom entered into ex-
planatory discussions, taking for granted that
he who applies his hand to the practical exa-
mination of minerals, has previously acquired
some slight share of chemical knowledge.

And, although the greater part of the work
consists of the labours of others, those who
are familiar with the subject, on which it treats,
will nevertheless notice various facts and prac-
tical proceedings, of which all the praise and all
the blame belongs to the author of the work.
On these I do not conceive it necessary to make
any remarks. If what has been advanced, as far
as it goes, be deemed better than what is in general
use, the question whence it originated is, in this
case, of little consequence to the reader. 1 am
far from entertaining an opinion that the struc-
ture of the work is perfect, or that it stands in
no need of indulgence : for in the exposition of
a science where so many operations of art are to
be detailed, and such a multiplicity of compli-
cated facts to be developed, error is almost un-
avoidable. — These considerations alone will

plead my excuse.—Confident that the gene-
ralities of the advanced statements may prove
useful to the student, I may perhaps expect
some approbation from those I wish to in-
struct, and hope for some indulgence from
such as are skilled in the science. I have in-
deed written for beginners; but if great scholars
confess that they have read their grammar, over
and over again with profit, the good analyst
may perhaps reap some advantage from being
reminded—where he cannot be instructed.

LONDON, 1808.          FRED. ACCUM.

# CONTENTS

OF

## *THE FIRST VOLUME.*

---

### PART I.

b

## PART II.

### METALLIC MINERALS OR ORES.

## COPPER ORES.

## ORES OF LEAD.

## ORES OF TIN.

## ORES OF IRON.

## ORES OF TUNGSTEN.

## ORES OF TELLURIUM.

## ORES OF URANIUM.

## ORES OF MOLYBDENA.

## ORES OF CHROME.

## ORES OF TITANIUM.

The Work referred to, p. 377, and quoted in several other places of this Manual, will be published on the 1st of December, under the title of

A
## SYSTEM
OF
## MINERALOGY
AND
## MINERALOGICAL CHEMISTRY.

*With application to the Arts.*

In 3 Vol. 8vo. with 15 Copper Plates.

## ERRATA.

Page 20, line 10, *dele* as H viz.
  42,  1, *for* Potash, *read* nitrate of potash.
  *ibid*  2, *for* Barytes *read* nitrate of barytes.
  98,  17, *for* colubium, *read* columbium.
  408,  *for* Wavellite, *read* Wavillite.
  449,  10, *for* murite *read* silici-murite.
  505,  23, *for* fig. 1, plate I. *read* fig. 4, plate I.

N. B. The Title Vignette spoken of page 34 is intentionally omitted, being unnecessary.

A

# PRACTICAL ESSAY

ON THE

# ANALYSIS OF MINERALS.

## PART I.

### DEFINITION OF MINERALS.

THE name of MINERAL, in the strict sense of
the word, denotes only such substances as are
found in mines, but the term is generally ap-
plied in a more extended view to characterise
that class of inorganic and inanimate bodies,
which form the solid mass, or rather the exter-
nal covering of the globe we inhabit; so far at
least as the labour of man has hitherto pene-
trated.

B

The totality of these substances has received the appellation of the mineral kingdom, in opposition to the two remaining grand divisions of nature, called the vegetable and animal kingdom.

### GENERAL CHARACTERS OF MINERAL-SUBSTANCES.

MINERALS absolutely possess no life, nor do they exhibit any phenomena dependant on external organisation. Minerals may increase in size, but their growth is exceedingly different from the growth of organic beings. It does not take place by virtue of nutrition and subsequent expansion of organic matter. It is not affected by external functions, and produces no advantage to the individual. The magnitude of a stone can only be increased by virtue of a mechanical, or chemical application of new matter; it is the result of simple combination of external materials aided by mechanical action, or regulated by chemical affinity. The subjects of the mineral kingdom are absolutely passive, they are acted on by external agencies only, and possess no power of changing that action.

## NATURE OF MINERALOGICAL SCIENCE.

MINERALOGY is that department of the science of nature which makes us acquainted with the habitudes and characters of minerals. It teaches the art of distinguishing them, by means of accurate and well-defined characters; the mode of describing them with so much precision, as is sufficient to recognise them with facility whenever they occur, and the art of arranging or classing them in a certain order, called a system.

To accomplish these views it traces the simple distinctions, and even the most minute variegations of properties discoverable amongst the different bodies hitherto known. It observes and marks every possible variety of form, appearance, and structure, under which a mineral is found; and endeavours to define with the strictest attention the mineralogical method and nature of the characters employed, as well as the technical language and nomenclature by which these minute distinctions can be accurately expressed, so as to convey complete instruction.

## NATURE OF ANALYTICAL MINERALOGY.

ANALYTICAL Mineralogy, or the analysis of minerals, is a branch of philosophical chemistry. It teaches the art of examining minerals, not by the help of external characters, but chiefly by chemical agencies. Its views are directed to the development of the constituent parts of minerals, the order in which they are present, their relative quantities, and the best modes of separating them.

The views of analytical mineralogy are therefore more extended, more intricate and laborious than those which belong to the natural history of these bodies. The latter department of knowledge, unassisted by the labours of mineralogical chemistry is little more than a language composed of words arranged by an arbitrary title; it is from the progress of analytical mineralogy, that the natural history of minerals must receive its principal aid in advancing to a perfect and dignified science: and hence the rapid improvements which have been made in this department of knowledge, has thrown a strong and steady light on some of the most obscure branches of mineralogical science.

The views of analytical mineralogy may ap-
pear at first sight immense and intricate, The
number of different species of minerals, now
known, is between seven and eight thousand.

To separate five or six substances intimately
combined together, to exhibit them separate, to
ascertain the precise quantity of each ingredient,
and even to detect the presence and the weight
of substances which do not amount to the $\frac{1}{500}$th
part of the whole, would at no very remote
period have been considered as a hopeless,
if not an impossible task. The great pro-
gress which chemistry has made during our
own time, has greatly facilitated this branch of
enquiry,

The summary field of chemical investigation
is nevertheless so vast and spacious that the most
diligent enquiry cannot completely traverse it,
in all its extents, nor can any continuance of
labour exhaust its application.

The practical analysis of minerals consists in
a series of chemical operations, calculated either
to separate the constituent parts, masked and
concealed from our view, so as to exhibit them
in a detached state, or to cause them to form
new compounds from which their nature and
properties may be inferred ; a series of chemical

processes thus conducted lead to the object desired; namely, the knowledge of the constituent parts of the substance under examination, their respective quantities, and the best modes of separating them.

## RE-AGENTS AND TESTS.

To facilitate the analyses of minerals, the substance of which is the object of enquiry, is exposed under different circumstances to the action of various bodies which chemically act on it, or alter its properties so as to produce changes which are striking to the senses, and from which the presence or absence of certain bodies may be inferred. These agents, thus employed, are called chemical tests or re-agents, they enable us to pursue our enquiry according to certain rules founded on experience. The proper application of these bodies, together with the necessary practical proceedings, or artificial arrangements best adapted for the reciprocal action, constitute the operation of analytical mineralogy.

To illustrate the agencies of chemical tests, let us suppose that a drop of muriatic acid, when suffered to fall on an unknown substance, occasions an effervescence, we conclude from the phenome-

non produced, that the unknown body contains
carbonic acid; if a drop of the same fluid occa-
sions a white precipitate when mingled with a
solution of the mineral substance under consi-
deration, we then conclude that the unknown
body contains either silver or lead; let us suppose
that both these metals were present. To separate
them from each other we merely pour over the
precipitate, liquid ammonia. The silver will be-
come dissolved, and the lead left behind. To
pursue our enquiries further, let us suppose that
sulphate of iron produced a dark brown precipi-
tate, we conclude from the appearance produced,
that gold is present; if liquid ammonia effected
a blue precipitate, copper is suspected; if muriate
of gold throws down a brown precipitate, it con-
tains tin; if tincture of galls produces a black
precipitate, iron, &c. Thus it becomes evident
that certain bodies have the property of indi-
cating and separating other bodies, the exist-
ance of which is unknown, form compounds of
which they form a part. Now the great object
in analytical enquiries, is, to find a body $x$ ca-
pable of separating a body $a$, from another
body $b$.

It is by this means that chemical analyses are
effected by the help of certain re-agents or tests.

He accordingly, who is able to resolve the prob-
lem in the greatest variety of circumstances, is
the best analyst.    Hence the application of che-
mical tests facilitates and guides our enquiries,
and although the compleat analysis of a mineral
demands often an extended series of operations,
it is nevertheless certain, that by the simple appli-
cations of a few re-agents, many useful analytical
enquiries may be accomplished.  A mineralogical
knowledge of the composition of bodies being
generally sufficient in directing the most impor-
tant application of minerals for useful purposes.

## OPERATIONS OF ANALYSIS.

Before we proceed to exhibit the methods,
made use of by chemists in analysing minerals,
we shall give a short account of those general
processes and instruments to which it is neces-
sary to have continually recourse in almost every
analysis.

It was once thought, that for the purpose of
experimental inquiry, particularly of this nature,
a place or laboratory, regularly fitted up with
furnaces and other apparatus was absolutely ne-
cessary.  This is by no means the case.  The
great improvements which have been made in

analytical chemistry have superseded this ne-
cessity ; and it is now universally admitted, that
all the operations of analysis may (in the small
way) be conveniently performed, by the help
of a few instruments, in the closet of the ama-
teur of the science ; and that even all the appa-
ratus, re-agents, and other articles of experiment,
necessary for the analysis of minerals, may be
comprised in a convenient travelling chest. (See
Index Mineralogical Laboratory.)

When the object is to analyse a mineral ; for
instance an ore, particularly with a view to as-
certain the comparative richness with respect to
the metal it contains, it is absolutely necessary
that specimens of the ore, be taken, from the
richest, the poorest, and from that which seems
to be of middling quality. This precaution is
indispensible, because were the analysis made
with a rich specimen, it might raise too flatter-
ing expectations ; or if with a poor one, it
might produce discouragement.

The next step in the analysis of any kind of
mineral, consists in separating the substance
intended to be examined, from all kind of ex-
traneous matter, with which it is always more
or less united. They may be separated by pick-
ing, washing, or other mechanical operations,

in order that the mineral may be examined pure
or unmixt. This being done, its specific gravity
must be ascertained. The method of accom-
plishing this, shall be noticed presently. The
substance employed should next be reduced to
an impalpable powder by means of the pestle
and mortar. This operation is called *pounding,*
or *pulverisation.* The bottom of mortars should
be concave, and their sides neither so inclined
as to allow the substance operated on, to fall to
the bottom, between each stroke of the pestle,
nor so perpendicular as to collect it too much
together and retard the operation. A steel or
iron mortar is convenient for dividing large spe-
cimens of minerals into smaller pieces, to render
them more fit for being reduced to a finer pow-
der in a smaller mortar of Wedgwood's water or
agate.

*Trituration* differs from the process of pulve-
risation, only in degree; it is performed by
giving a rotatory motion to the pestle.

*Levigation* differs from trituration in the ad-
dition of water to the powder operated upon;
so as to form the whole mass into a tenacious
or rather liquid paste, which is rubbed in the
mortar till it is as fine as required. Very hard
substances, particularly all stones of the silicious

kind must be repeatedly heated to redness, and
then suddenly quenched in cold water, to render
them sufficiently friable.

*Weighing.* The quantity of substance thus
previously comminuted, should next be accu-
rately determined by the process called *weigh-
ing ;* for that purpose the operator should be
provided with a good balance, and an accurate
set of weights. The beam of a good balance
should remain in equilibrio without the scales,
and when the scales are changed, and should
turn sensibly with a small portion of additional
weight when loaded. Scales must be defended
as much as possible from acid vapours, as their
delicacy is impaired by them : for the same rea-
son they never should be overloaded. It is of
the utmost consequence in every analysis, to
ascertain at all times the precise quantity of
any matter which is subjected to examination,
and again to distinguish with equal accuracy the
quantities of the products. Hence the instru-
ments for weighing are to be regarded as parti-
cularly deserving of the young analyst's atten-
tion.

It is necessary to have scales and weights for or-
dinary use, and others for occasions where greater
accuracy is necessary. Fine scales should always

be kept apart from the laboratory, for otherwise
the beam will rust, and the accuracy of the
balance be destroyed. They are most conve-
niently used when suspended from a support,
so constructed as to raise the beam when em-
ployed for weighing. (See hydrostatic balance.)

Common balances are subject to many imper-
fections, the principal of which are as follows :

1st. A balance is frequently in equilibrio,
when the opposite weights in its scales are not
equal. This arises from the points of suspen-
sion being not equidistant from the centre of
motion; in which case the empty scales may
be made to balance each other; yet, when equal
weights are put in them, those weights will not
balance each other; for as they are suspended at
an unequal distance from the centre of motion,
their momentums are actually unequal.

The beam is often made too slight : in which
case it is apt to be bent more or less by the
weights that are put into the scales; and of
course the apparent equilibrium cannot be de-
pended upon.

They seldom are sufficiently sensible. This
defect arises from various causes, as from the
great weight of the beam, from roughness and
friction at the point of suspension, from the

centre of gravity of the beam being considera-
bly below the centre of motion, &c.

Balances for analysis may be had of a won-
derful degree of sensibility ; viz. capable of
having their equilibrium disturbed by so small a
quantity as $\frac{1}{1000}$ part of the weight in each
scale.

*Weights.* As the utility of analytical research
depends greatly upon the determination of the
quantities of the ingredients and products, not
only accurate scales but accurate weights are
also necessary. The weights of the analyst
should be divided into their several fractions,
both vulgar and decimal. All weights should
be adjusted by means of repeated and accurate
trials in the most delicate scales, and by skilful
workmen. It requires a tolerable share of ex-
perience and dexterity to use weights properly.
The best way of precisely ascertaining the weight
of a particular substance, is to weigh it twice,
once with the decimal division of the pound,
ounce, or grain, and another time with the
vulgar fraction or common subdivision, and by
comparing these we obtain the utmost accuracy.
If a balance be found to turn with a certain ad-
dition, is not moved by any smaller weight, a

C

greater sensibility may be given to that balance
by producing a tremulous motion in its parts.
Thus if the edge of a blunt saw, a file, or similar
instrument be drawn along any part of the sup-
port of the balance, it will produce a jarring
motion, which diminishes the friction of the
moving parts so much that the turn will be
evident, with one third, or $\frac{1}{4}$ of the addition
that would else have been required. In this
manner a beam, which will barely turn by the
$\frac{1}{10}$ part of a grain, may be made to turn with
the $\frac{1}{30}$ or $\frac{1}{40}$ part of a grain.

*Decimal Weights.*    Experimental chemists
divide their pound or ounce into decimal parts,
and a set of decimal weights are considered as
essential to the analyst. The set of decimal
weights most convenient for chemical and other
operations, is the following : viz. 1000 grains,
900 g. 800 g. 700 g. 600 g. 500 g. 400 g. 300 g.
200 g. 100 g. 90 g. 80 g. 70 g. 60 g. 50 g. 40 g.
30 g. 20 g. 10 g. 9 g, 8 g. 7 g. 6 g. 5 g. 4 g.
3 g. 2 g. 1 g. $\frac{9}{10}$ g. $\frac{8}{10}$ g. $\frac{7}{10}$ g. $\frac{6}{10}$ g. $\frac{5}{10}$ g. $\frac{4}{10}$ g.
$\frac{3}{10}$ g. $\frac{2}{10}$ g. $\frac{1}{10}$ g. $\frac{9}{100}$ g. $\frac{8}{100}$ g. $\frac{7}{100}$ g. $\frac{6}{100}$ g.
$\frac{5}{100}$ g. $\frac{4}{100}$ g. $\frac{3}{100}$ g. $\frac{2}{100}$ g. $\frac{1}{100}$ g. With these
weights the philosopher will always have the
same number of weights in his scales as there

are figures in the number expressing the weights in grains.

Thus 742,5 grains will be weighed by the weights 700, 40, 2, and $\frac{5}{10}$.

The error of adjustment is the least possible when one weight is in the scale; that is to say, a single weight of 5 grains, is twice as likely to be true as two weights, one of 2, and the other 3 grains, because each of these last has its own probability of error in adjustment.

*Pile of Weights.* Other weights may be made by a subdivision of a standard weight. If the weight be continually halved, it will produce the common pile, which is the smallest possible number for weighing between its extremes, without placing any weight in the scale with the body under examination. Granulated tin is a very convenient substance to be used in halving, which however is very tedious. The readiest way to subdivide small weights, consists in weighing a certain quantity of small silver wire, and afterwards cutting it into such parts, by measure, as are desired. Or the wire may be wrapped close round two pins, and then cut asunder with a knife. By this means it will be divided into a great number of equal lengths, or

small rings. The wire ought to be so thin, as
that one of these rings may barely produce a
sensible effect on the beam. If any quantity
(as, for example, a grain) of these rings be
weighed, and the number then reckoned, the
grain may be subdivided in any proportion, by
dividing that number, and making the weights
equal to as many of the rings as the quotient of
the division denotes. Then, if 750 of the rings
amounted to a grain, and it were required to
divide the grain decimally, downwards, $\frac{9}{10}$ would
be equal to 675 rings, $\frac{8}{10}$ would be equal to 600
rings, $\frac{7}{10}$ to 525 rings, &c. Small weights may
be made of thin leaf silver. Jewellers foil is a
good material for weights below the $\frac{1}{10}$ of a
grain, as low as to the $\frac{1}{100}$ of a grain ; and all
lower quantities may be estimated by actually
counting the rings of wire, whose value has been
determined.

*Specific Gravity.* By the term specific weight
or specific gravity of a body, is understood the
weight which any given bulk of matter bears
to the weight of another body of the same
magnitude, it is called the specific weight be-
cause it is the comparative weight of different
sorts of matter. Thus the specific weight of
mercury is to the specific weight of water as 13

to 1, the meaning of which is, that if a quan-
tity of mercury which exactly fills a certain
vessel, and a quantity of water which likewise
precisely fills the same vessel, be weighed se-
parately, the quicksilver will weigh 13 times
as much as the water, so that if the latter will
weigh 1oz. the mercury will weigh 13 oz.
The object of finding the specific gravity of
bodies is therefore to distinguish them from
each other in one of their most obvious quali-
ties, viz. weight of matter contained in a given
space. The specific gravity of bodies is as their
density; the density of a body is the quantity of
matter which it contains under a given bulk; the
density of a body is therefore measured by the
proportion which its quantity of matter bears to
its bulk, for the more numerous the particles of
matter are in the same portion of space the
greater is the density of the body, and on the
contrary, the fewer the particles of matter the
less the density. The nature of specific gravity
therefore implies comparison; some kind of sub-
stance must be fixed upon whose gravity must be
made a standard for the gravity of other bodies of
equal bulk to be compared with. This standard
body should have two properties, first it must be

had or come at upon all occasions; and se-
condly, it should be of as fixed and unalterable a
nature as possible that there may be no variation
in its gravity, in equal bulks, in different times
and places.

Water amongst fluids is that body which pos-
sesses in the highest degree the requisite pro-
perties for a standard. Distilled water is the
least objectionable, next to this rain water, but
common water for most purposes will answer
very well; hence water is always used as the
standard of comparison or as the unit with
which all other bodies are compared. The spe-
cific gravity is liable to be altered by two causes,
viz. by the admixture of other substances, and
by an alteration of temperature, for instance,
water at 100° is lighter than water at 60°, and
still lighter than water at 40°, hence it is abso-
lutely necessary that the water for ascertaining
specific gravities should always be used at the
same temperature, and should be free from he-
terogeneous matters.

The most natural way of determining the spe-
cific gravity of bodies is to weigh, in a pair of
scales, bodies of different sorts, of precisely the
same dimensions, and this indeed is a very
good practical method for fluids, which may be

put successively into the same phial, &c. but
the difficulty of forming solids exactly of the
same dimensions is so very great that their spe-
cific gravities are generally determined by weigh-
ing each body both out of water, or in air, and
in water, in the manner which will be particularly
described, excepting some powdery substances,
which in this respect may be treated like fluids.
It appears therefore that a fine pair of scales or
balance is the principal instrument which is re-
quired for determining the specific gravities of
bodies, it only requires to have a hook affixed
under one of the scale pans. This balance
when in use might be held in the operator's
hand; but as those experiments require a certain
time, and much accuracy, it is adviseable to have
them set upon a stand, such as is represented
in fig. 1, plate I. the whole apparatus then for de-
termining gravities, goes under the name of the
Hydrostatic balance. It consists of the fol-
lowing parts : A balance, such as A. B. C. D.
fig. 1, plate I. which should be so sensible as to
turn at least with the twentieth part of a grain,
when each scale is loaded with a weight of one
ounce. An accurate set of weights, especially
of grains, such as weights of 10 grains, and of
100 grains, besides the single grains, it being

much more commodious to make the computa-
tion entirely in grains, or at most in ounces and
grains, than to be encumbered with weights of
different denominations.  A glass jar E. about
seven or eight inches high, which is to contain
the distilled or rain water, a glass ball of about
an inch or an inch and a half in diameter with
a bit of fine platina wire about three inches
long affixed to it.*  A small glass bucket G.
A small phial or two, as H. (viz.) of such
a shape as to admit of their being easily
filled, emptied, and cleaned, and a thermo-
meter I.  This hydrostatical balance and ap-
paratus may be had of a very compact form,
so as to admit of its being packed up in a pretty
small box, but when in use it must be set upon
a table, where it must be remarked that the ba-
lance may be moved a little up or down, either
by means of the string, which goes along the

* This ball may be either of solid glass, or of hollow glass,
partly filled with quicksilver, or with some other heavy sub-
stance ; in the latter case it generally has a short perforated stem,
into the perforation of which the platina wire is fastened. But
if it be a solid glass ball, a hole of about one fifth of an inch in
length must be drilled in it where the wire is to be fastened. For the
sake of expedition in making the computation, it would be proper
to make this glass ball of a certain weight expressible by a round
number, for instance, of 100, or 500, or 1000 grains.

stand, in the common way, or by some rack work motion, or other mechanical contrivance, which need not be particularly described. We shall now proceed to state the practical methods of determining the specific gravities of bodies of various species.

I.—*Method of ascertaining the Specific Gravity of a Mineral or Solid which is heavier than water.*

RULE.—Suspend the solid by means of a slender wire or thread as may be just sufficient to hold it to the hook under the scale C. so as to hang at the distance of six or seven inches below that scale, and by putting weights in the opposite scale D. find out its exact weight in air, that is out of the water; then place the jar E. about three quarters full of rain, or distilled water, under the scale C. which is the case actually represented in the figure; let the solid body be immersed in the water, and either by removing some of the weights from the scale D. or by putting weights in the scale C. find out its exact weight in water; subtract the latter weight from the former, and note the remainder; lastly, divide the weight of the solid out of the water,

by that remainder, and the quotient will express
its specific gravity.  See the precautions which
follow the example.  A piece of mineral was
found to weigh in air (that is out of the water)
360 grains, and in water 300 grains; the latter
weight being subtracted from the former gives
60.  Now 360 divided by 60 gives 6, which is
the specific gravity sought.

The water in which the solid is to be weighed
besides its being distilled or rain water, must be
quite clean, its temperature as well as that of
the solid must be as near as possible to 62° of
Fahrenheit's thermometer, for which purpose
the ball of the thermometer must be placed in
the water, and the temperature is adjusted by
the addition of hot or cold water.  If the mi-
neral be soluble in water, as salts, &c. or if it
be porous enough to absorb any water, then it
must be varnished over with some thin varnish,
but in that case some allowance must be made
on account of the varnish.  When the solid is
weighed in water, its upper part ought to be a
little way below the surface of the water, and
care should be taken that no air bubles are at-
tached to it, for they would partly buoy it
up, these may be easily removed by means
of a feather.  The solid must be of a com-

pact form and free from accidental or artifi-
cial vacuities, so as not to harbour any air,
for otherwise its specific gravity cannot be as-
certained by weighing in water, &c. thus a
piece of silver, which is much heavier than
water, may be formed into a hollow sphere
which will appear to be much lighter than water,
for if this sphere were immersed in water, it
would displace a quantity of that fluid which
is equal not only to the silver, but also to the
space which is contained in the sphere,* these
precautions must be attended to in the practical
performance in the preceding as well as of the
following problems of this chapter as far as they
may be concerned in them.

2. *Method of ascertaining the Specific Weight of
   Minerals that are sufficiently heavy to sink in
   water, which are not soluble in that fluid, but
   are too small to be tied by means of a thread.*

RULE.—Suspend the glass bucket G. by the

* It is for this reason that a ship might be made of iron, of
copper, or in short of any substance, whose specific gravity far
exceeds that of water, and yet it would float as well as a ship
which is made of wood in the usual way.

interposition of a thread or wire to the hook of the
scale C. and find its weight in air, then place the
substance which is to be tried in it, and weigh
it again, the former weight subtracted from the
latter, leaves the weight of the substance in air,
this being done, the same operation must be
repeated in water, that is, let the loaded bucket
be weighed in water, then remove its contents
and weigh the bucket alone in water, subtract
the latter weight from the former and the quo-
tient is the weight in water of the substance
under examination; having thus obtained the
weight of that substance, in water and out of
water, you will then proceed according to the
preceding problem. (viz.) Subtract its weight
in water from its weight in air, and note the
remainder. Divide its weight in air by this
remainder the quotient will express its spe-
cific gravity. Observe the general precautions
stated before. By this means the specific gra-
vity of diamonds, and other small precious
stones as also of grains of platina, gold dust, of
filings of metal, of mercury, &c. may be ascer-
tained.

*Example.* The glass bucket being suspended
from the hook of the scale C. was counter-
poised by weights in the opposite scale D. some

gold dust was then placed in it, and by adding
more weights into the scale, D. its weight (viz.)
of the gold dust alone was found to be 460,6
grains, the loaded bucket was then weighed in
water, and was found to weigh 736,1 grains,
and after having removed the gold dust from
the bucket, the latter by itself was found to weigh
in water 300 grains, which being subtracted
from 736,1 left 436,1 grains for the weight of the
gold in water ; then this weight of the gold in
water (viz. 436,1) was subtracted from its weight
in air, (viz. 460,6) and the remainder was 24,5.
Lastly, the weight of the gold in air, viz. 460,6
was divided by the remainder 24,5, and the quo-
tient 18,8 expressed the specific gravity of the
gold dust.

3.   *Method of ascertaining the specific gravity*
     *of minerals or solid bodies lighter than water,*
     *or such as will not sink in it.*

RULE.—Take another body of a compact
form, but much heavier than an equal bulk of
water, so that when this body is connected with
the body in question they may both sink in wa-
ter.   This being prepared, ascertain the weight

D

of the lighter body in air, and the weight of the heavier body in water; then tie, by means of thread, both bodies together, but not so closely as to exclude the water from, or to harbour bubbles of air between them; and weigh them both in water. Now, since the heavy body is partly buoyed up by the lighter body, the weight of both in water will be less than the weight of the heavier body alone: subtract the former from the latter, and add the remainder to the weight of the lighter body in air; for this sum is the weight of a quantity of water equal in bulk to the lighter body, therefore, the weight of the lighter body in air must be divided by the last mentioned sum, and the quotient will express the specific gravity of the lighter body. Observe the general precautions as before stated.

*Example.* A piece of elm being varnished, in order to prevent its absorbing any water, was found to weigh in air 920 grains. A piece of lead, which was chosen for this purpose, was found to weigh in water 911,7 grains. The piece of elm and the piece of lead were tied together, and being suspended from the hook of the scale C, &c. in the usual manner, were found to weigh in water 331,7 grains (viz.) 580 grains less

than the lead alone, therefore 580 was added to
920 (viz.) to the weight of the elm in air, and
made up the sum of 1500. Lastly, 920 was
divided by 1500, and the quotient 0,6133 ex-
pressed the specific gravity of the piece of elm.
It is almost superfluous to observe, that the spe-
cific gravity of bodies that are lighter than water
are less than unity.

**4.** *Method of ascertaining the specific gravities
of small bodies (such as saline powders, &c.)
which are soluble in water.*

Rule.—The substance in question must be re-
duced into fine powder, unless it be already in that
shape. Take a clean glass phial, furnished with a
ground stopper, put it in one of the scales of the
balance, and counterpoise it by placing weights
in the opposite scale; then fill the phial with the
powder in question, ramming it as close as pos-
sible, and quite up to the top. This done, re-
place the phial in the same scale in which it
stood before, and by adding more weights in the
opposite scale, find out the exact weight of the
powder alone. Now remove the powder from
the phial; fill the latter with rain or distilled

water, and placing it in the scale as before, as-
certain the weight of the water alone.    By this
means you have the weights of equal quantities
of the powder and of water, which are exactly
as their specific gravities; but the specific gra-
vity of water is not expressed by unity, therefore
say, as the weight of the water is to the weight
of the powder, so is unity to a fourth propor-
tional, which is the specific gravity of the pow-
der, when that of water is reckoned unity;
that is, divide the weight of the powder by
the weight of the water, and the quotient will
express the specific gravity of the powder.    In
certain cases, the saline substances, or other small
bodies, if the reducing them to powder be ob-
jected to, may be weighed in the bucket; but,
instead of water, they must be weighed in some
other fluid, in which they are not soluble, and
whose specific gravity is already known; for the
specific gravities thus found may be easily refer-
red to that of water.

*Example.*    The phial full of a certain salt,
was found to weigh 630 grains (meaning the salt
alone, independent of the phial) and the same
phial full of rain water was found to weigh 450
grains (viz. the water alone) therefore 630 was

divided by 450, and the quotient 1,4 expressed
the specific gravity of the salt.

5. *Method of ascertaining the specific gravities
of mineral waters and other fluids.*

RULE.—This may be done either by the me-
thod last mentioned, which indeed is the most
proper, as being the most accurate for nice ex-
periments, or in the following manner: suspend
the glass ball F, or a piece of metal, to the hook
of the scale C, and find successively its weight in
air, its weight in water, and its weight in any
other fluid you wish to try. Subtract its weight
in water from its weight in air, and the remainder
is its loss in weight, when weighed in water.
Also, subtract its weight in the other fluid from
its weight in air, and the remainder is its loss of
weight in the other fluid. Now those two last
weights are exactly as the specific gravities of the
two fluids respectively, but the specific gravity
of water is not in this case expressed by unity ;
therefore say, as the loss of weight in water is to
the loss of weight in the other fluid, so is unity to
a fourth proportional; that is, divide the loss of
weight in the other fluid by the loss of weight in

water, and the quotient will express the specific
gravity of the other fluid. For this purpose, a
glass ball, with a bit of platina wire, are prefer-
able to other substances, because, amongst all the
variety of fluids, there are fewer that have any
action upon glass and platina, than upon any
other solid; yet they are corroded by one or two
fluids, and therefore, when these are to be tried,
the method before stated must be adopted, but
the phial must consist of such a substance as is
not liable to be corroded by the fluid in question;
or the glass phial may be lined in the inside with
a film of bees wax, which is easily done by
warming the phial, for this film will prevent its
being corroded.

*Example.* A glass ball, which weighed 100
grains in air, was found to weigh 60 grains in
water, and 70 grains in another fluid; so that
the loss of weight in water was 40 grains, and
the loss of weight in the other fluid was 30 grains;
therefore 30 was divided by 40 and the quo-
tient 0,75 expressed the specific gravity of the
other fluid.

*Solution* is a most general process of analysis.
It is the diminution of the aggregation of any
solid substance, in consequence of its entering
into a new chemical combination. This pro-

cess consists in affusing upon the substance to
be dissolved, a fluid employed as solvent; suffer-
ing it to stand in the cold, or assisting the ac-
tion of the bodies upon each other by heat
according to the nature of the substance. So-
lution may be performed in glass matrasses, or
Florence flasks. The vessel employed should
not be above ½ full. It should be tied over with
a piece of wet bladder, and pierced with one or
more small holes made with a pin, so that the
evaporation of the fluid may be retarded as much
as possible. The flask may be heated over the
lamp-furnace, (see title page). Solution is ac-
celerated by shaking and agitating the mixture.
Perfect transparency and permanent suspension
of the solid are marks of perfect solution, by
which it is distinguished from simple mixture,
or mechanical diffusion.

*Precipitation* is the reverse of solution. It
consists in separating a dissolved body from the
solvent or substance which held it in solution
by the intervention of another body. The sub-
stance separated is called the precipitate. Long
conical glasses answer very well for this pro-
cess.

*Filtration* is employed for separating solids
from fluids, particularly when the former do not

subside, or at least very slowly. To filter sub-
stances, white paper freed from size, alum, &c.
(filtering paper,) is folded in a conical form,
called a filter, and placed in a glass funnel.
The substance to be filtered is then poured
upon the filter gradually. That part of the
fluid which passes first, is seldom clear; it must
always be poured back again upon the filter,
until, by the swelling of the fibres of the paper,
the fluid acquires complete transparency. It is
of advantage in filtration to introduce glass rods,
bleached pack-thread, or straw, between the
filter and the funnel, to prevent the paper from
adhering too closely to the latter. Acids, alca-
lies, and other corrosive fluids, are best filtered
by means of a glass funnel filled with pounded
glass, a few large pieces being first put in the
neck of the funnel, smaller ones over these, and
the finer powder placed over all. The porosity
of this kind of filter retains much of the fluid,
but it may be recovered by gently pouring on it
as much water; the fluid will then be displaced
and pass through, and the water be retained in
its place.

  *Decantation* differs from filtration merely in
degree, it is the expedient by which such fluids
are separated from solids, as differ considerably

in specific gravity. The heavier body falling to
the bottom speedily, so as to allow the superna-
tant fluid to be decanted, either wholly or in
part, without disturbing the heavier part. De-
cantation is best performed from tall cylindrical
glass vessels, furnished with a spout or lip.

*Elutrition* is confined to such mineral sub-
stances on which water has no action. It is per-
formed for separating them from foreign articles
and impurities of a different specific gravity, in
which case they are said to be washed; or for
separating the impalpable powders obtained by
trituration and levigation from the coarser par-
ticles. This process depends upon the property
that very fine or light powders have, of remain-
ing for some time suspended in water. It is
performed by diffusing the powder or paste,
formed by levigation, through plenty of water,
in a tall cylindrical vessel, letting it stand a suf-
ficient time until the coarser particles settle at
the bottom, and then pouring off the liquid in
which the finer or lighter particles are suspend-
ed. (See analysis of gold dust.) Fresh water
may be poured on the residuum, and the opera-
tion repeated: or the coarser particles which fall
to the bottom may be previously levigated a
second time.

*Evaporation* is a chemical process intended for separating volatile, from fixed bodies, by converting the former into vapour by means of heat. It is performed in sections of glass spheres, or shallow basons of Wedgwood's-ware, supported by the rings of the lamp-furnace; (see title vignette.) Small quantities of fluids may be conveniently evaporated in watch glasses, whose absolute weigh is marked on the outside by means of a diamond. Evaporation is promoted by enlarging the surface of the fluid, and by agitation.

*Distillation* is a process of evaporation performed in close vessels, so as to collect the products. Distillation is performed by means of the *Retort* and *Receiver*. The retort is a globular vessel either of glass or earthen-ware, with a neck extending in a curved direction from one side of the globe, terminating in an open point or mouth. (See title vignette.) The materials to be distilled are introduced into the body of the retort, and heat is applied, to cause the substance to boil. To the neck of the retort is adapted a receiver, or globular vessel, with a short straight neck, wide enough to allow the neck of the retort to be introduced into it. (See title vignette.) It is intended to condense and

receive from the retort, the fluid that distils
over.

*Abstraction* is that species of distillation in
which a fluid once distilled is again distilled off,
from the same substance from which it was
obtained.

*Reduction* is the operation employed for re-
storing oxids of metals to the metallic state, by
the intervention of another body, which acts
chemically upon them. It is performed in cru-
cibles, or other vessels, by the action of heat, and
addition of different substances.

*Roasting* or *Ustulation* is a process to be per-
formed upon metallic ores, by exposing them in
a crucible, or other convenient vessel, to the ac-
tion of heat in contact with air. The volatile
parts are thus driven off, and the ore is prepared
for farther analysis.

*Vitrification* is the fusion of such substances as
are capable of assuming the brightness, trans-
parency, and hardness of glass. Crucibles are
employed for this process.

*Stratification* consists in arranging solid sub-
stances in layers, with intermediate *strata* of
other substances, in order to expose them in a
crucible to heat, so as to cause them to act upon
each other. See analysis of ores of zinc.

*Granulation* is employed for the mechanical
division of some metals.  It is performed either
by stirring the melted metal with an iron rod,
until it cools, or by pouring it into water, and
stirring it continually, or by pouring it into a
covered box, previously well rubbed with chalk,
and agitating it until the metal cools, when
the rolling motion will be converted into a
rattling one.  The adherent chalk is to be
washed away: Or the melted metal may be
poured through a perforated iron ladle.

*Fusion* is the conversion of a solid into a li-
quid, by the application of heat.  The sub-
stance thus rendered fluid, is said to be fused or
melted.  A minute quantity of a substance may
be fused by the flame of a candle or lamp, urged
by the *blow-pipe*.  The best blow-pipe is a
conical tube, furnished with a small pipe near
the base, to which jets or caps of different perfo-
rations may be adapted at pleasure.  The air is
either forced into the blow-pipe by the lungs of
the operator, or by means of double bellows at-
tached to the instrument.  The substance to be
fused must be placed upon a piece of excavated
charcoal, or held in a spoon, made of gold, or
platina.  The quantity of the substance exa-
mined by the blow-pipe should not exceed the

size of a pepper-corn. If larger quantities of substances are intended to be fused, the vessels in which the operation is to be performed are called *crucibles* or *melting-pots*.

*Crucibles* are made of different materials. It is absolutely necessary to have a crucible of perfectly pure silver. Those of earthen-ware should be of various sizes and shapes. The larger are generally conical, with a small spout, for the convenience of pouring out the melted matters. The smaller crucibles are truncated triangular pyramids. Those known in commerce by the name of *Hessian crucibles* are in every respect superior to those manufactured in this country. The black-lead crucibles made of clay and black-lead are very durable, but they cannot be used for alkaline fluxes, or saline matters. Crucibles which ring clearly when struck, and which are of an uniform thickness, and have a reddish brown colour, without black spots, are the best: they should never be placed upon the grate of the furnace, but always on a piece of brick, or other support of stone or earthen-ware. When the fusion of a metallic substance is completed, the substance may either be permitted to cool in the crucible, or it may

E

be poured into a heated mould, anointed with
tallow (never with oil), or what is still better,
covered with a thin coating of chalk; which
being previously diffused in water, may be con-
veniently applied with a brush, and then evapo-
rating the water completely, by heating the
mould. Conical moulds, for receiving fused
substances, are called *casting cones*; bar-shaped
ones, are called *ingots*.

For performing the operations of analysis
which require the aid of heat, and particularly
the process of fusion, a *portable universal fur-
nace*, and an *improved lamp-furnace*, are the
chief instruments necessary. The operator who
is provided with them may perform all the ope-
rations of mineralogical chemistry, which require
a very low or very intense heat. Descriptions of
the best furnaces of that kind as well as of the in-
struments of experiment, enumerated in the op-
posite page, will be given hereafter.

In the conducting of experiments, I cannot
recommend better general rules than those ad-
vanced by Mr. Henry, in his valuable Epitome
of Chemistry, p. 2; namely, let every jar or
phial have a label affixed to it, denoting the
substance it may contain (except in cases where
the nature of the contents is evident from mere

inspection) and the date and object of the expe-
riment. I would caution the student not to en-
gage in many different experiments at once; the
consequences of which are, that the attention is
distracted, and that many interesting changes
pass unnoticed. It will contribute to form a ha-
bit of accurate observation, if the appearances
that occur in experiments be regularly and dis-
tinctly noted down; and such an exercise will
tend also to facilitate the acquirement of the art
of describing chemical phenomena; to do which,
with selection and precision, is very far from
being an universal talent.

The summary apparatus and instruments, ne-
cessary for the analysis of minerals, are the fol-
lowing:

### INSTRUMENTS OF EXPERIMENT.

A portable universal furnace.

A lamp furnace.

A blow-pipe, and platina spoon.

Crucibles of silver, platina, black lead, cast-
iron, and earthen-ware, of different sizes and
shapes.

E 2

Crucible-stands and covers.

Crucible and other tongs of various shapes.

A spirit lamp.

A portable forge.

Mortars of Wedgwood's ware, of glass, cast-
iron, and porphiry.

Florence flasks, digesters, and assay jars.

A goniometer for measuring the angles of crys-
tals.

A mineralogical electrometer.

A hydrostatic balance.

Accurate beams, scales, and weights in deci-
mals.

A cubic inch measure, and graduated glass mea-
sures for fluids.

Glass funnels of biscuit ware, of different areas,
fluted and plain.

An apparatus for separating deliquescent salts.

Filtering paper, and filtering stands for support-
ing funnels

Test tubes, and stand.

Glass rods, for stirring corrosive fluids.

Evaporating basons of glass, of biscuit ware, of
silver, and platina.

Iron ladles, with lips, in sizes.

Precipitating glasses.

An apparatus for drying precipitates.

A small anvil stand, and mineralogical hammers.

Cylinders of zinc, tin, copper, and iron.

A magnetic needle and stand.

A deep magnifier.

Watch glasses for evaporating minute quantities of fluids.

Muffles and cupels.

A steel graver, for trying the hardness of minerals.

Steel and ivory palette knives.

Glass retorts and receivers, in sizes, plain and tubulated.

Retort and hydrostatic funnels.

Ingots and casting cones.

Glass syphons.

A chemical thermometer, with naked bulb.

An apparatus for ascertaining the quantity of carbonic acid contained in mineral substances.

### LIST OF RE-AGENTS, OR TESTS

| | |
|---|---|
| Sulphuric acid | Muriate of gold |
| Nitric acid | ———— Barytes |
| Muriatic acid | Muriate of Ammonia |
| Alcohol | Liquid Ammonia |
| Boracic acid | Nitrate of Silver |

Crystallized  Potash        ~~Nitrate~~ Potash

Hydrate of Barytes        ———— Barytes

Carbonate of soda freed    Succinate of Soda
    from  its water of    Tincture of Galls
    crystallization        ———— Cabbage

Muriate of Tin        Prussiate of Potash

———— Platina        ———— Mercury

White Flux        ———— Ammonia

Oxalate of ammonia    Phosphate of Soda and

Acetate of Silver        ammonia

Black Flux        Test Papers.

————————

*A select Collection of* CHEMICAL RE-AGENTS
*prepared under the direction, and in the Labo-
ratory of the Author, together with the most
essential* APPARATUS *and* INSTRUMENTS *for ana-
lyzing minerals may be had as a companion to
this Essay, forming a* PORTABLE MINE-
RALOGICAL LABORATORY.

*Lutes* also form a necessary part of chemical apparatus. They are compositions of various substances intended,

a. To close the joinings of apparatus.
b. To coat glass and other vessels.
c. To line furnaces.

Lutes of the first description are commonly employed to confine elastic vapours. They should therefore possess the following properties :

a. Compactness.
b. The capability of resisting acid vapours.
c. The power of resisting a certain intensity of heat.
d. Facility of removal after the operation.

Viscid substances, as flour, starch, and gum, possess the first and last properties in a sufficient degree; they are therefore employed when the heat is moderate, and the vapour not corrosive. They are mixed with water, and spread upon slips of paper or linen, which are wrapped round the joinings of the vessels, and if necessary, secured with packthread.

Slips of bladder macerated in water, and applied with the inside next the vessels, are employed in the same circumstances; but from their great contraction on drying, they are apt to break weak vessels.

A paste formed of almond or linseed meal and water, or mucilage, forms a very close and plastic lute, which is easily removed.

Quicklime reduced to powder and well incorporated with a sixth part of muriate of soda, or with white of egg diluted with water, applied on slips of linen, dries easily, and becomes very hard. It is used for the distillation of the concentrated acids; but for this purpose burnt gypsum and water answers very well. Both these lutes must be used as soon as they are prepared, as they harden very quickly.

Chalk and oil, or glaziers putty, is a very compact lute. As it becomes so hard as not to be easily removed, it is principally used for luting tubes into vessels for pneumatic purposes.

A paste of powdered tobacco pipe-clay and drying oil, or, what is still better, amber varnish, is very close, adhesive, and plastic, and is easily removed; but as it softens with heat, it must be secured by slips of linen or thread, and will not

adhere to the vessels unless they are perfectly
dry.

The same clay beat up with as much sand as
it will bear, without loosing its tenacity, with
the addition of cut tow and a sufficient quantity
of water, furnishes a very good lute, which has
the advantage of resisting a considerable heat,
and it is applicable where the fat lute would be
melted or destroyed.

Clay and sand, in the proportion of one to
four, form an excellent lute, capable of resisting
very high temperatures, and the greatest number
of corrosive substances.

Eight parts of yellow wax melted with one of
oil of turpentine, with or without the addition
of some resinous substances, according to the
degree of pliability and consistence required,
form a very close and compact lute, through
which the subtile corrosive vapours will not
escape. But it is softened and liquefied by heat,
therefore cannot be used for purposes where high
temperatures are required.

The lute employed for the coating of glass
vessels, with the intention of making them
stronger and capable of resisting violent heats,
without softening, consists of four parts of sand
and one of clay, made into a very thin mass,

and applied in successive layers, taking care that each coat be perfectly dry before another be laid on.

In every instance where a lute is applied it is absolutely necessary to allow it to dry before the process is began; and even the fat lute, by the exposure to the air during a few days after its application, is much improved in its quality. Lutes composed of clay and sand are perfectly useless, except they be permitted to dry. In applying a lute, the part immediately over the junction of the vessel should swell outwards, and its diameter should be gradually diminished at each side.

The junctures of vessels which are to be luted to each other must previously be accurately and firmly fitted, by introducing between them, when necessary, short bits of wood or cork, or if the disproportion be very great, by means of a cork fitted to the one vessel, having a circular hole bored through it, through which the neck of the other vessel or tube passes.

After being thus fitted, the lute is rolled and worked between the fingers till it be softened, and is then formed into small cylinders, which are successively applied to the junctures, taking care that each piece be made to adhere firmly

and perfectly close in every part before another
is put on. Lastly, the whole is secured by the
slips of linen or bladder.

In many cases to permit the escape of elastic
vapours, a small hole is made through the lute
with a pin, or the lute is perforated by a small
quill, fitted with a stopper. This, however, is
seldom necessary.

### FUEL AND APPLICATION OF HEAT.

As caloric is an agent of the most extensive
utility in the chemical operations of mineralogy,
it is necessary that we should be acquainted
with the means of employing it in the most
economical and efficient manner.

The rays of the sun are used to accelerate
spontaneous evaporation; the only attentions
necessary are to expose as large a surface of the
fluid as possible.

The combustion of different substances is a
much more powerful and certain source of heat.
Alcohol, oil, tallow, wood, turf, coal, charcoal,
and coke, are all occasionally employed.

Alcohol, oil, and melted tallow, are burnt in
lamps of various constructions. These afford a
very uniform, though not very high temperature.

Alcohol has the great advantage of burning
without smoke. But oil burnt upon a cylin-
drical wick, so contrived that the air has free
access both to the outside and to the inside of
the cylinder, as in Argand's lamp, may be made
to produce a considerable temperature of great
uniformity, and without the inconvenience of
smoke.

Wood, turf, coal, charcoal, and coke, are
burnt in grates and furnaces. Wood has the
advantage of kindling readily, but affords a very
unsteady temperature, is inconvenient from its
flame, smoke, and soot, and requires much at-
tention. The heavy and dense woods give the
greatest heat, burn longest, and leave a dense
charcoal.

Dry turf gives a permanent heat, and does not
require so much attention as wood; but its
smoke is copious and penetrating, and the em-
pyreumatic smell which it imparts to every thing
it comes in contact with adheres to them with
great obstinacy. The heavy turf of marshes is
preferable to the light superficial turf.

Coal is the fuel most commonly used in the
laboratory. Its heat is considerable and suffi-
ciently permanent, but it produces much flame
and smoke.

Charcoal, especially of the dense woods, is a very convenient and excellent fuel. It burns without flame or smoke, and gives a strong, uniform, and permanent heat, which may be easily regulated, especially when it is not in too large pieces, and is a little damp.

Coke, or charred coal, possesses similar properties to charcoal. It is less easily kindled, but is capable of producing a higher temperature. *The best fuel for general purposes of the laboratory, however, is coke and charcoal mixt together; two or three parts of the former to one of the latter,* broken into pieces of the size of a walnut.

For experiments in the small way, spirits of wine is upon the whole the neatest and most convenient fuel, and hence the spirit lamp may be employed for most operations of analysis as a very convenient furnace.

GENERAL VIEW

OF

# THE SOLID PART

OF

# THE EARTH.

———

Iꜰ we contemplate the solid parts of the globe, we behold an immense assemblage of heterogeneous bodies. We perceive it to be arranged with an irregularity of distribution, which may well excite our surprize, and arrest our attention. Stones, metallic substances, inflammable fossils, saline bodies, either in lapideous or in metallic aggregation, or else in a state of comminution, are the only proper component parts of the whole.

The traces of some great revolutions visible in
every part of the globe, have at all times arrested
the attention of mankind. Whether we excavate
the plains, penetrate into the caverns of moun-
tains, or scale their rugged flanks, every where
the spoils of organised bodies are buried in those
beds which form the external coat of our earth.
Immense masses of shells are found at great dis-
tances from every sea, and at immense heights.
Banks of slate contain fish, and beds of coal
display impressions of vegetables, at elevations
or at depths equally astonishing. Here beds of
shells, extending for many miles under ground,
cover others which contain only vegetables:
there the bodies of fish are placed above land
animals, and they in their turn are covered by
strata, containing the remains of plants and
shells. Torrents of lava, and heaps of pumice-
stone, the products of subterraneous fire, mingle
in other places with the inhabitants of the
ocean. It is under the equator that we find
living animals analogous to the shells and fossil
fish of the North, and in the icy regions of the
arctic circle are the remains of those indigenous
to the torid zone.

A force of incredible extent has every where

distated those very regions and rocky pavements
of the earth, which our imagination paints as
the abodes of everlasting silence and rest.

### INTERNAL STRUCTURE AND MEAN DENSITY OF THE EARTH.

The internal constitution of the earth is little
known. The deepest excavation that have been
made by human art do not exceed 2400 feet, or
less than half a mile; which is a very short dis-
tance indeed when compared with the diameter
of the earth, which is about 7947 English
miles: so that whatever lies below that depth is
utterly unknown. The substances which have
been extracted from those excavations are not
in general of a nature different from those which
in some particular places have been found im-
mediately upon the surface. These substances
are in general arranged in strata, variously in-
clined to the horizon, and of a thickness not
very equal. Some indeed have supposed that
they follow each other, in a certain order almost
throughout the globe; but this opinion appears
to rest on slight foundations.

The mean density of the earth, deduced from
the observations made by Dr. Maskelyne on

the sides of Schehallien, an insulated moun-
tain in Perthshire, is $4\frac{1}{2}$, reckoning water, as
usual, the standard of comparison. Mr. Caven-
dish has lately assigned a greater quantity, or
about $5\frac{1}{2}$, from a very elegant experiment on the
principle of torsion, which Coulomb employed
so successfully in a variety of delicate researches.
Perhaps the true proportion will be found to lie
between these limits. The observations of Dr.
Maskelyne, however skilfully conducted by that
eminent astronomer, were performed under the
most unfavourable circumstances, in a foggy
climate and rainy season. And Mr. Caven-
dish's experiment was not perhaps made on
a scale sufficient to afford very great preci-
sion. Nor is it at all improbable, that the ap-
parent force of attraction was in some degree
augmented by a slight infusion of magnetic
virtue; for the masses of lead which discovered
their mutual appetency might yet contain a
certain admixture of iron, in a state of such
intimate combination as to resist the action of
chemical solvents.

We are disposed to think that, instead of se-
lecting a conical hill with a view to ascertain the
deviation of the plummet, it would be more eli-

F 3

gible to place the observer successively on the
opposite sides of a narrow vale, bounded by two
ranges of lofty mountains which run from east
to west. Those stations would be very commo-
dious for determining the altitude of a star, and
their true distance could be found trigonometri-
cally with the utmost exactness. The moun-
tains themselves might be surveyed by consider-
ing them as composed of a number of parallel
and vertical slices, formed by planes, in the di-
rection of the meridian. The best scene that I
am acquainted with for attempting these opera-
tions is in the Upper Valais, where the Rhone
holds a westerly course; and the enormous Alps,
in a double chain, having more than a mile of
perpendicular height, approach at their lower
flanks perhaps within two or three miles.

### GEOLOGICAL THEORIES.

Different opinions have been formed con-
cerning the question, in what manner our earth
was brought into the present distribution of its
parts.

An origination of this globe out of a chaos
was the general belief of the ancients. Moses,
in the beginning of the Pentateuch gives an

account of a series of successive changes, which he represents as the first which took place, from the moment at which matter was made subject to the laws it obeys to that æra at which it was finally fit for the residence and support of animals, and had living inhabitants, brute and human, placed upon it.

In modern times, different classes of speculatists have attempted to investigate the circumstances which must have attended the origin of it.

Divines have endeavoured to justify the account of Moses, by an appeal to the present laws of nature: but Burnet and others have been easily convicted of supposing primæval states of things utterly incompatible with these laws.

Chemists have conceived that the origin of the earth, in its present form, is from a general liquidity of its whole matter: others again have attributed it to the action of fire.

Astronomers have been persuaded that it was owing to the action of some comet, or to an altered arrangement of the planets.

Others have conceived the idea of a world perhaps without beginning, but by the action of internal fires, with volcanic orifices, continually

lacerated, undermined, and subverted, with the constant rise of a new earth, the residue and product from those fires, by which the former was demolished.

Others, again, have fancied a continual flitting of the ocean around the globe; by which that which was lately land becomes now the bottom of the sea, and that which is now covered by the sea is again to become land.

These fanciful opinions, to say nothing of the impious nature of some of them, have generally rather resembled philosophical dreams than the conceptions of waking and sober reason. Their authors, in forming them, have been too often guided by imagination more than judgment; and have laboured rather to support a favourite hypothesis than to consult the voice of authentic history, or patiently to examine the materials and structure of the fabric which they undertook to describe.

And, although there has been in modern times a wonderful variety of fanciful productions, under the name of geological theories, we are by no means to imagine that nothing has been usefully done in this department of natural history. Amidst all the splendid rubbish with which it has been incumbered, some precious

treasures have been brought to light. Amidst
the speculations which have *darkened counsel,*
large additions have been made to our knowledge
of this important subject. These may be briefly
summed up in the following particulars.

The *materials* for the formation of a correct
and rational theory of the earth have been greatly
augmented during the last age. Enlightened mi-
neralogists, practical miners, and patient chemi-
cal experimenters, have been engaged, through-
out the century, in making accurate observa-
tions; in visiting foreign countries; in exploring
the bowels of the earth; in comparing the strata
of every portion of the globe; in examining their
form, direction, extension, and connexion; in
analysing their component parts; and in col-
lecting a multitude of facts, which have all
tended to throw light on the origin and history
of our planet. By means of the useful disco-
veries which these inquirers have made, we are
furnished with weapons for beating down false
theories, and with information enabling us to
pursue our investigations further, and with more
advantage.

Difficulties have been lately removed which
were once supposed, by some, to militate
strongly against the *possibility* of a *general*

*Deluge.* Early geologists, for want of accurate information, supposed that all the waters of the globe were not sufficient to cover the whole earth to such a depth as the sacred historian describes. It was asserted that the mean depth of the ocean did not exceed a quarter of a mile, and that only half of the surface of the globe was covered by it. On these data Dr. Keil computed, that *twenty-eight* oceans would be requisite to cover the whole earth to the height of *four miles,* which he judged to be that of the highest mountains; a quantity, which, at that time, was utterly denied to exist. But further progress in mathematical and physical knowledge has since shown, that the different seas and oceans contain at least *forty-eight* times as much water as they were supposed to do, and much more than enough for the extent ascribed to the deluge in the sacred history.*

While difficulties which were supposed to render the deluge *impossible* have been removed by the investigations of modern philosophers, many facts have been, at the same time, brought to light, showing the *possibility,* and even *certainty,* of that mighty inundation. In every

* Kirwan's *Geological Essays,* p. 66, 67.

valley and mountain support for revelation has
been found. *Marine shells* have been disco-
vered in situations so elevated, and under cir-
cumstances so remarkable, as to prove that they
were left there by a flood extending over the
whole globe; and what confirms this conclu-
sion is, that shells peculiar to different shores
and climates very distant from each other have
been found in promiscuous heaps, plainly show-
ing that they could have been brought together
only by an extensive inundation. The bones of
*elephants* and of *rhinoceros* have been found, in
a multitude of instances, far distant from the re-
gions in which they are found to live, and where,
from the nature of the climate, they could never
exist in the living state: and between the cli-
mates which they might have inhabited, and the
places in which they are now found, too many
mountains intervene to suppose them carried
thither by any other means than a *general de-
luge.** The most patient and accurate exami-
nations of detached mineral substances, and of
the strata of the globe, which late inquirers have
made, afford every reason to believe that the earth
was for a considerable time wholly overflowed

* Kirwan's *Geological Essays,* p. 54, *et seq.*

with water. And, to crown all, as voyagers and travellers have explored new regions of the earth, they have found, every where, the indications of geological phenomena confirmed and supported by the notices of tradition. Accordingly, it is very remarkable that a great majority of modern theorists have embraced the *Neptunian* doctrines; and even such of them as rejected the Mosaïc account of the deluge have been compelled to seek for other means of immerging the present continents in the ocean.

Finally, the researches of modern geologists have given abundant confirmation to the sacred history, not only with respect to the general *deluge,* but also with regard to the *age* of the earth.

### CLASSIFICATION OF MINERALS.

To arrange our examination of minerals with greater precision, as well as to facilitate the primary knowledge of them in general, mineralogists have divided minerals into certain classes, distinguishable from each other, by very obvious and permanent characters.

Mineralogy is chiefly employed in arranging similar bodies under the same, and dissimilar

bodies under different denominations. It judges
of similarity two ways, either from similarity of
external appearances, or from the similarity of
the internal composition.

The knowledge of the similarity of the inter-
nal constitution is acquired chiefly by regarding
the changes produced in them by the chemical
actions of other bodies; that of the internal cha-
racters, by regarding the figure, colour, texture,
fracture, or other properties, which these bodies
present to our senses, and which may be ob-
served without causing them to undergo any
material alteration whatever.

From the knowledge of the constituent parts
of minerals is derived their economical applica-
tion, their uses in agriculture, metallargy, and
in the arts.

Most mineralogists have contented themselves
with classing minerals according to their most
obvious qualities, and have therefore classed to-
gether very heterogeneous substances. Sensible
at last of this imperfection, others have availed
themselves of the assistance of chemical know-
ledge, and have endeavoured to arrange minerals
according to their internal component parts.
This method is perfect in its kind, and usesul for

common application. For instance, all earths
and stones, which by certain additions form glass,
and in which flint abounds, are called silicious
stones, those which do not melt into glass, but be-
come converted into brick, or become hard, and
to which clay gives the character, are called argil-
laceous stones, those which burn into lime, cal-
careous stones, &c. To discriminate minerals
therefore with accuracy and precision, the great
outlines of the classification of mineral sub-
stances may most usefully be made from the
chemical investigation of their constituent parts.
Each individual mineral, however, has not, and
cannot be analysed, this would be impracticable,
and were it not it would be without utility; but
when the analysis of a mineral has been effected,
we presume that a similarity of composition will
exist in other specimens which agree with it
closely in their internal and external characters.

# SYSTEMATIC
# DISTRIBUTIONS OF MINERALS

## TABULAR VIEW

OF

THE WERNERIAN SYSTEM OF MINERALOGY,

ADOPTED IN

*THE GERMAN SCHOOL OF MINES.*

## CLASS I.

*Earthy minerals, or minerals chiefly composed of earths.*

> 1. DIAMOND GENUS.
>
> Diamond.

> 2. ZIRCON GENUS.
>
> *Zircon family.*
>
> Zircon.
> Hyacinth.
> Cinnamon stone.

### 3. FLINT GENUS.

*Chrysolite family.*

| | | |
|---|---|---|
| Chrysoberyl | Olivine | Augite |
| Chrysolite | Coccolite | Vesuvian |

*Garnet family.*

| | | |
|---|---|---|
| Leucite | Garnet | Staurolite or grenatite |
| Melanite | précious | Pyrope |
| | | Meïonite |

*Ruby family.*

| | | |
|---|---|---|
| Ceylanite | Sapphire | Corundum |
| Spinelle | Emery | Diamond spar |
| | | Automalite |

*Topaz family.*

Topaz
Fibrolite
Sommite

*Shorl family.*

| | | |
|---|---|---|
| Euclase | Shorl | Zoisite |
| Emerald | tourmaline | Axinite, or |
| Beryl | Pistacite | Tummerstone. |
| precious | | |
| shorlaceous | | |

*Quartz family.*

| | |
|---|---|
| Quartz | Rock crystal |
| Amethyst | Milky quartz |
| thick fibrous | Phrase |

Iron flint
Horn stone
  splintery
  conchoidal
  woodstone
Flinty slate
  lydian stone
Flint
Calcedony
Cornelian
  fibrous
Hyalite
Opal
  precious
  translucent
  semi-opal

Opal
  wood-opal
Menilite
Jasper
  Egyptian
  red
  brown
  striped
  conchoidal
  earthy
  opal
  agate
Heliotrope
Chrysophrase
Plasma
Cat's eye

*Pitchstone family.*

Obsidian
Pitchstone

Pearlstone
Pumice
  glassy
  porphyritic

*Zeolite family.*

Wavelite
Phrenite
  fibrous
  foliated
  needle stone
Zeolite
  mealy
  fibrous
  radiated
  foliated

Cubizite
Crosstone
Lomonite
Dipyre
Natrolite
Azulite
Azur stone

e 3

*Feldspar family.*

Andaluzite                    Scapolite
Feldspar                      Wernerite or arctizite
    Adularia                  Spodumene
    Labrador spar            Ichthyophthalmite
        glassy
        variolite
        hollow spar
        compact feldspar

### 4. Clay Genus.

*Clay family.*

Pure clay                     Clay stone
Porcellain earth              Adhesive slate
Common clay                   Polishing slate
        Loam                  Tripoli
        Potters clay          Float stone
            earthy            Alum stone
        Variegated clay
        Slaty clay

*Clay slate family.*

Alum slate                    Drawing slate
    glossy                    Whet slate
Bituminous shale              Clay slate

*Mica family.*

Lepidolite              Clorite
Mica                        chlorite earth
Pinite                      chlorite slate
Polstone                    foliated chlorite

### Trap family.

Diaspore
Hornblende
    labradore
    basaltic
    hornblende slate

Smaragdite
Basalt
Wacke
Clinkstone
Iron clay
Lava

### Lithomarge family.

Green earth
Lithomarge
    friable
    indurated

Rock soap
Umber
Yellow earth

### 5. MAGNESIA OR TALC GENUS.

Native magnesia
Bole
Meerschaum

Fullers earth
Steatite
Agalmatolite

### Talc family.

Nephrite
    axe stone
Serpentine
    precious
    conchoidel
    splintery
Schillerstone

Talc
    earthy
    indurated
Asbest
    rock cork
    amianth
    rock wood

### Actynolite family.

Actynolite
    asbestous
    glassy

Tremolite
    asbestous
    glassy
Cyanite
Sahlite

### 6. GADOLINITE GENUS.

Gadolinite.

### 7. CALCAREOUS. GENUS.

*Lime family.*

A. *Carbonate of lime.*
  Rock milk
  Chalk
  Lime stone
        compact
        roe stone
  Foliated lime stone
        granular
        calc spar
        pea stone
  Calc tuff
  Foam earth
  Slate spar
  Brown spar
        foliated
        fibrous
  Schaal stone
  Dolomite
  Rhomboidal spar
  Swine or stink stone
  Marl
      marl earth
      indurated marl
  Bituminous marl slate
  Arragon

B. *Phosphate of lime.*
  Appatite
  Asparagus stone
  Phosphorite

C. *Fluate of lime.*
  Fluate of lime
        compact
        fibrous

D. *Sulphate of lime.*
  Sulphate of lime, or
      gypsum
        gyps earth
        compact gypsum
        foliated gypsum
        fibrous gypsum
  Selenite
  Cube spar

E. *Borate of lime.*
  Boracite
  Cryolite

### 8. BARYTIC GENUS.

Carbonate of barytes
Sulphate of barytes, or heavy spar
        Compact

Sulphate of barytes
> Granular
> Straight lamellar
>> fresh
>> disintegrated
> Columnar heavy spar
> Prismatic heavy spar
> Bolognean heavy spar


### 9. STRONTIAN GENUS.

Carbonate of strontian
> fibrous
> compact

Sulphate of strontia, or celestine
> foliated
> prismatic

# CLASS II.

## NATIVE SALTS.

A. *Carbonates.*
Carbonate of soda

B. *Nitrates.*
Nitrate of soda

C. *Muriates.*
Muriate of soda
Stone or rock salt
    foliated
    fibrous
    lake salt
Muriate of ammonia

D. *Sulphates.*
Sulphate of iron
Sulphate of magnesia and sulphate of iron, or
 hair salt
Native alum
Sulphate of magnesia, or Epsom salt
Sulphate of soda, or glauber salt

# CLASS III.

## INFLAMMABLE FOSSILS.

### 1. SULPHUR GENUS.

Native sulphur
    coherent

Native sulphur
    earthy
      volcanic

### 2. BITUMEN GENUS.

Mineral or fossil oil
Mineral pitch
    elastic
    earthy
    slaggy
Brown coal
    bituminous wood
    earthy coal
    alum earth
    common brown coal
    moor coal

Black or pit coal
    pitch coal
    columnar coal
    slate coal
    cannel coal
    foliated coal
    coarse coal

### 3. GRAPHITE GENUS.

Glance coal
    conchoidal
    slaty

Graphite
    scaly
    compact
Mineral charcoal

### 4. AMBER, OR RESIN GENUS.

Amber
    white
    yellow

Mellite, or honey stone

# CLASS IV.

## METALLIC MINERALS.

### 1. Platina Genus.
Native platina

### 2. Iridium Genus.
Ore of Iridium.

### 3. Gold Genus.

Native gold        Native gold
  Gold yellow          Greyish yellow
  Brass yellow

### 4. Mercury Genus.

Native mercury       Mercurial liver ore
Native amalgam          compact
  semifluid           slaty
  solid         Cinnabar
Mercurial horn ore        dark red
                light red

### 5. Silver Genus.

Native silver        Silver glance
  common        Brittle silver glance
  auriferous      Indurated silver glance
Antimoniated silver     Red silver ore
Arseniated silver           dark
Muriatic, or horn silver        light
Silver black         White silver ore
  friable        Black silver ore
  coherent

### 6. COPPER ORES.

Native copper
Copper glance
    compact
    foliated
Variegated copper ore
Copper pyrites
Grey copper ore
Copper black
Red copper ore
    compact
    foliated
    capillary
Tile ore
    earthy
    indurated

Azure copper
    earthy
    radiated
Malachite
    fibrous
    compact
Copper green
Ironshot copper green
    earthy
Copper emerald
Copper mica
Lenticular ore
Oliven ore
Muriate of copper

### 7. IRON GENUS.

Native iron
Iron pyrites
    radiated
    hepatic
    capillary
Magnetic iron
Magnetic iron stone
    iron sand
Iron glance
    compact
    foliated
    iron mica
Red iron stone
    frothy
    ochrey
    compact
    red hematite
Brown iron ore
    brown iron froth
    ochrey brown
    iron stone

Iron ore
    compact
    brown hematite
Sparry iron ore
Black iron ore
    compact
    black hematite
Clay iron ore
    Reddle
    Columnar clay
    iron ore
    Lenticular clay
    iron ore
    Jaspery clay iron
    ore
    Common clay
    iron ore
    Reniform clay
    iron ore
    Pea ore, or pisi-
    form iron ore

H

Bog iron ore
    Morass ore
    Swampy iron ore
    Meadow iron ore

Pitchy iron ore
Green iron earth
Cube ore

## 8. LEAD GENUS.

Sulphuret of lead, or
    lead glance
        compact
Blue lead ore, or galena
Brown lead ore
Black lead ore
White lead ore

Green lead ore
Red lead ore
Yellow lead ore
Sulphate or vitriol of lead
Earthy lead, or
    Lead earth
        coherent
        friable

## 9. TIN GENUS.

Tin pyrites, or sulphuret of tin
Tin stone, or oxid of tin
Wood tin

## 10. BISMUTH GENUS.

Native bismuth
Sulphuret of bismuth, or bismuth glance
Bismuth ochre, or oxid of bismuth

## 11. ZINC GENUS.

Sulphuret of zinc, or blende
    yellow
    brown

Sulphuret of zinc
    black
Calamine

## 12. ANTIMONY GENUS.

Native antimony
Grey antimonial ore
    compact
    foliated
    radiated

Antimony ore
    plumose
Black antimony ore
Red antimony ore
White antimony ore
Antimonial ochre

### 13. TELLURIUM GENUS.

Native tellurium
Graphic ore

Yellow tellurium
Black tellurium

### 14. COBALT GENUS.

White cobalt ore
Grey cobalt ore
Brown cobalt ore
Red cobalt ore
 cobalt crust

Cobalt ore
 cobalt bloom
Cobalt glance
Black cobalt ore
 earthy
 indurated

### 15. MANGANESE GENUS.

Grey manganese ore
 radiated
 foliated
 compact

Grey manganese ore
 earthy
Black manganese ore
Red manganese ore

### 16. NICKEL GENUS.

Sulphuret, or copper nickel  Nickel ochre

### 17. ARSENIC GENUS.

Native arsenic
Arsenical pyrites
 argentiferous

Orpiment
 yellow
 red
Arsenic bloom

### 18. MOLYBDENA GENUS.

Sulphuret of molybdena  Molybdate of lead

### 19. TUNGSTEN GENUS.

Wolfram, or tungstate of iron and manganese
Tungsten

### 20. Titanite Genus.

Menachanite           Nigrin
Octahedrite           Iserine
Rutilite                Brown menachanite ochre
                      Yellow

### 21. Uranite Genus.

Pitch blende          Uran ochre
Uran mica

### 22. Chrome Genus.

Chromate of lead, or red lead ore      Chromate of iron

### 23. Columbium Genus.
Columbate of iron

### 24. Tantalite Genus.
Tantalium

### 25. Cereum Genus.
Cerete.

# TABULAR VIEW

OF

## HAÜY's METHODICAL DISTRIBUTION OF MINERALS,

*Adopted in the French School of Mines.* *

---

I<sub>N</sub> this System of Mineralogy the arrangment of simple minerals is almost strictly chemical; but the classification and description of the rocks and lavas is founded on certain hypothesis respecting their formation. The species of the simple minerals is determined from one character, namely, the integrant molecule.

* Copied from a Synopsis of the mineral kingdom.

# DIVISION I.

## MINERAL SUBSTANCES WHICH ADMIT OF SPE-
## CIFIC DISTINCTION.

# CLASS I.

Acidiferous substances, composed of an acid
united to an earth, or to an alcali, or to both.

### ORDER I.

*Combinations of earths with acids.*

#### GENUS I.—LIME.

SPECIES.

| | |
|---|---|
| Carbonate of lime | Sulphate of lime |
| Phosphate of lime | Nitrate of lime |
| Fluate of lime | Arseniate of lime |

VARIETIES.

*Carbonate of Lime united to different substances, so as
to preserve its structure, or some of its principal
characters.*

Aluminiferous carbonate of lime
Ferriferous carbonate of lime
Siliceous carbonate of lime
Magnesian carbonate of lime
Hydro sulphurised, or fœtid carbonate of lime
Bituminous carbonate of lime

### GENUS II.—BARYTES.

Species.

Sulphate of barytes　　　Carbonate of barytes

### GENUS III.—STRONTIA.

Species.

Sulphate of strontia　　　Carbonate of strontia

### GENUS IV.—MAGNESIA.

Species.

Sulphate of magnesia　　　Borate of magnesia
Carbonate of magnesia

## ORDER II.

*Combinations of alcalies with acids.*

### GENUS I.—POTASH.

Species.
Nitrate of Potash.

### GENUS II.—SODA.

Species.
Muriate of soda　　Borate of soda　　Carbonate of soda

### GENUS III.—AMMONIA.

Species.
Muriate of ammonia.

### ORDER III.

*Combinations of earths and alcalies with acids.*

### GENUS I.—ALUMINE.

SPECIES.

Sulphate of alumine and potash
Fluate of alumine and potash

## CLASS II.

### NON ACIDIFEROUS SUBSTANCES,

*Or Minerals exclusively composed of Earths, except when united sometimes to an alcali.*

SPECIES.

Quartz
- Hyaline
- Agate
- Resinite
- Jasper
- Pseudomorphic

| | |
|---|---|
| Zircon | Meïonite |
| Telesia | Feldspar |
| Cymophane | Corundum |
| Spinel ruby | Pleonaste |
| Topaz | Axinite |
| Emerald | Turmaline |
| Euclase | Amphibole |
| Amphigene | Actinite |
| Idocrase | Pyroxene |

* *This Class has no orders nor genera, but is only a series of individual species.*

Staurotide
Epidote
Garnet
Sphène
Wernerite
Diallage
Anatase
Dioptase
Gadolinite
Lazulite
Mesotype
Stilbite
Phrenite

Chabasie
Analcime
Nèpheline
Harmotome
Pèridot
Mica
Disthène
Grammatite
Pycnite
Dypyre
Asbestus
Talc
Macle

# CLASS III.

## COMBUSTIBLE SUBSTANCES.

### ORDER I.

*Simple combustible substances.*

#### SPECIES.

Sulphur — Diamond — Anthracite

### ORDER II.

*Compound combustible substances.*

#### SPECIES.

Bitumen
Pit-coal
Jet
Amber
Mellite

# CLASS IV.

## METALLIC SUBSTANCES.

### ORDER I.

*Substances not immediately oxidable and reducible by heat.*

#### GENUS I.—PLATINA.
Alloy of Platina

#### GENUS II.—GOLD.
Native Gold

#### GENUS III.—SILVER.

| | |
|---|---|
| Native silver | Sulphuret of silver |
| Antimonio-sulphuret of silver | Antimonial silver |

Muriate of silver

### ORDER II.

*Substances immediately oxidable and reducible by heat.*

#### GENUS.—MERCURY.

##### SPECIES.

| | |
|---|---|
| Native mercury | Sulphuret of mercury |
| Argentiferous mercury | Muriate of mercury |

Hydrosulphuret of mercury

## ORDER III.

*Substances which are oxidable, but not immediately reducible by heat.*

I. SUBSTANCES CONTAINING DUCTILE AND MALLEABLE METALS.

### GENUS I.—LEAD.

SPECIES.

Native lead (volcanic)   Carbonate of lead
Sulphuret of lead        Phosphate of lead
Arseniate of lead        Sulphate of lead
Chromate of lead         Muriate of lead
            Muria-sulphate of lead

### GENUS II.—NICKEL.

SPECIES.

Arseniate of nickel        Oxid of nickel

### GENUS III.—COPPER.

SPECIES.

Native copper          Muriate of copper
Sulphuret of copper    Blue carbonate of copper
Grey oxid of copper    Green carbonate of copper
Red oxid of copper     Arseniate of copper
            Sulphate of copper

### GENUS IV.—IRON,

SPECIES.

Oxid of iron           Sulphate of iron
Oligistous iron        Carbonate of iron
Arseniate of iron      Chromate of iron

## GENUS V.—TIN.

SPECIES.

Oxid of tin        Sulphuret of tin

## GENUS VI.—ZINC.

SPECIES.

Sulphuret of zinc        Sulphate of zinc
Carbonate of zinc

II. SUBSTANCES CONTAINING METALS NOT POSSESSING DUCTILITY AND MALLEABILITY.

## GENUS VII.—BISMUTH.

SPECIES.

Native bismuth        Sulphuret of bismuth
Oxid of bismuth

## GENUS VIII.—COBALT.

SPECIES.

Arseniate of cobalt        Grey oxid of cobalt
Black oxid of cobalt

## GENUS IX.—ARSENIC.

SPECIES.

Native arsenic        Oxid of arsenic
Sulphuret of arsenic

## GENUS X.—MANGANESE.

SPECIES.

Oxid of manganese

### GENUS XI.—ANTIMONY.

SPECIES.

Native antimony      Oxid of antimony
Sulphuret of antimony    Hydrosulphuret of antimony

### GENUS XII.—URANIUM.

SPECIES.

Oxid of uranium      Oxidulated uranium

### GENUS XIII.—MOLYBDENA.

SPECIES.

Sulphuret of molybdena.

### GENUS XIV.—TITANIUM.

SPECIES.

Oxid of titanium     Siliceo-calcareous titanium

### GENUS XV.—TUNGSTEN.

SPECIES.

Feruginated tungsten    Calcareous tungsten

### GENUS XVI.—TELLURIUM.

SPECIES.

Native tellurium, united to different metals.

### GENUS XVII.—CHROMIUM.

SPECIES.
Chrome.

ı

# DIVISION II.

## SUBSTANCES WHICH DO NOT ADMIT OF SPECIFIC DISTINCTION.

### I. DOUBTFUL MINERALS, OR SUBSTANCES NOT YET SUF-FICIENTLY KNOWN TO HAVE A PLACE IN THE SYSTEM.

Amianthoide
Aplome
Arragonite
Coccolithe
Diaspore
Ecume de Terre
Emerald of France
Feldspar, apyrous
Jade
Koupholite
Lèpidolithe
Lime, sulphated anhydrous
Lime, sulphated quartzi-
   ferous

Madrèporite
Malacolithe
Micarella
Petrosilex
Scapolithe
Radiant spar
Shistous spar
Spinthère
Tourmaline
Triphane
Zeolite, efflorescent
Zeolite, yellowish radiated
Zeolite, red

### II. AGGREGATES OF DIFFERENT MINERAL SUBSTANCES USUALLY DENOMINATED COMPOUND ROCKS.

## ORDER I.

*Aggregates considered as of primitive formation, and which bear more particularly the name of rocks.*

Feldsphathic rock
Quartzose rose

Amphibolic rock
Micaceous rock

Talcous rock  
Calcareous rock  
Jadean rock  
Petrosiliceous rock

Cornean rock  
Serpentinous rock  
Argillaceous rock

## ORDER II.

*Aggregates generally considered secondary or tertiary
in their formation, and which seem to owe their origin
to sediments, and their hardness to desiccation.*

Clay  
Calcariferous clay or marle  
Argillo-ferriferous polishable limestone, or secondary
marble  
Calcariferous sulphate of lime, commonly called plaister
stone

### VARIETIES.

Potter's clay  
Fuller's clay  
Lithomargic clay

Ochreous clay  
Schistous clay

## ORDER III.

*Aggregates composed of fragments agglutinated posterior
to the formation of the substances to which they have
belonged.*

Quartz-agate breccia  
Calcareous breccia  
Agglutinated arenaceous quartz, or grit  
Tripolian aluminiferous quartz. *Tripoli*  
Recomposed granite, commonly called grit of the coal
mines

III. SUBSTANCES MODIFIED BY SUBTERRANEAN FIRE.

# CLASS I.

## I. VOLCANIC PRODUCTS.

### LAVAS:

*Substances which have undergone igneous fluidity.*

### ORDER I.

*Lithoidal lavas, viz. having the appearance of stones.*

#### GENUS.

Basaltic lithoidal lavas    Feldspathic lithoidal lavas
Petrosiliceous lithoidal lavas  Amphigenic lithoidal lavas

### ORDER II.

*Vitreous lavas, having more or less a vitrified appearance.*

### ORDER III.

*Scoriated lavas, resembling more or less the scoria of forges.*

#### VARIETIES.

Obsidian vitreous lava    Pumiced vitreous lava
Enamelled vitreous lava   Capillary vitreous lava
Pearled vitreous lava

# CLASS II.

### THERMANTIDES:

*Substances which indicate only traces of the agency of subterranean heat.*

### VARIETIES.

Cementing thermantide     Tripolian thermantide
Pulverulent thermantide

# CLASS III.

### PRODUCT OF SUBLIMATION.

Sulphur             Sulphuret of arsenic
Muriate of ammonia    Oligistous iron, &c.

*N. B. These admit of specific distinction, and have a place in the method: but considered with reference to volcanic products, are only various sublimates.*

# CLASS IV.

### DECOMPOSED LAVAS,

*Having suffered more or less decomposition by the attacks of acido-sulphureous vapours or by the action of the atmosphere.*

### VARIETIES.

Aluminiferous decomposed lava.   The alum stone
of Tolfa.

I 3

## CLASS V.

### VOLCANIC TUFAS.

*Products of muddy eruptions, cementations, and agglutinations, by the humid process.*

## CLASS VI.

### SUBSTANCES FORMED IN THE INTERIOR OF LAVAS POSTERIOR TO THEIR FLOWING.

#### VARIETIES.

| | |
|---|---|
| Mèsotype | Chabasia |
| Analcime | Carbonate of lime |
| Stilbite | Sulphuret of iron |

## CLASS VII.

### II. NOT VOLCANIC PRODUCTS,

*Substances modified by subterranean fires.*

#### VARIETIES.

Porcelain thermantide          Tripolian thermantide

Whatever arrangement of minerals we may adopt or frame, it is enough that the classification should be so made that minerals which possess some general, obvious, or physical properties should be placed together, in order to form a certain system or methodical arrangement, namely :

*Class* I.   ORES.
       II.   EARTHS AND STONES
      III.   MINERAL OR NATIVE SALTS.
       IV.   INFLAMMABLE FOSSILS.

This is the general division of minerals a-dopted by men of science. But as some of these classes present to us a vast variety of individuals, mineralogists have been under the necessity of sub-dividing them into certain genera and species, in order to remove, or at least to facilitate the numberless difficulties which would otherwise oppose the acquisition of general scientific knowledge. This will become more conspicuous in the sequel of this essay.

# PART II.

## CLASS 1.

# METALLIC MINERALS,

OR

# ORES.

THE name of ORES, or metallic ores, as they are frequently called, is given to all those minerals, which are either entirely composed of metals, or of which metallic substances constitute the most considerable part. It is from this class of bodies that metals are obtained. The number of metals hitherto known amount to 29. It is obvious therefore, that the same number of different orders of ores must exist. Each of which is distinguished by the name of the par-

ticular metal, which forms its most essential part; but as four metals have hitherto been found only in other ores, or combined with different metallic substances, the number of the orders of ores are reduced to 25, viz.

ORES OF

| | |
|---|---|
| Platina, | Cobalt, |
| Gold, | Arsenic, |
| Silver, | Tungsten, |
| Copper, | Tellurium, |
| Lead, | Uranium, |
| Tin, | Molybdena, |
| Iron, | Chrome, |
| Zinc, | Titanium, |
| Mercury, | Manganese, |
| Antimony, | Colubium, |
| Bismuth, | Tantalium, |
| Nickel, | Iridium, |

Osmium.

### PHYSICAL PROPERTIES OF METALS.

All metals are combustible bodies. They possess a certain brilliancy, in consequence of the complete reflection of the light that falls upon them, which is termed *metallic lustre.*

They are the most dense and heavy substances in
nature; the heaviest fossil, not metallic, having
a specific gravity much below that of the lightest
metal.    They are the most opaque of all bodies.
A stone of the greatest opacity, when divided
into thin plates, has more or less transparency;
whereas gold is the only metal which admits of
being reduced to such a degree of thinness as to
admit the smallest perceptible transmission of
light.   Gold leaf, which is about $\frac{1}{280000}$ part
of an inch in thickness, transmits light of a
lively green colour; but silver, copper, and all
the rest of the metals, are perfectly opaque.
Another property which belongs exclusively to
metals (though they do not all possess it), is
*malleability*; by which is meant a capacity of
having their surface increased, either in length
or breadth, without being liable to fracture.
This capacity is not precisely the same in those
metals which do possess it; for some, which
admit of extension when struck with a hammer,
cannot be drawn into wire, which is properly
termed *ductility*. this property depends in some
measure on another peculiar quality of metals,
namely, *tenacity;* by which is meant the power
which a metallic wire of a given diameter has of
resisting the action of a weight suspended from

its extremity.  All metals are fusible, though
the degree of temperature, at which this can be
effected, differs very much.  Mercury is always
fluid at the ordinary temperature of our atmos-
phere, while platina can scarcely be melted by
the most intense heat of our furnaces.  Metals
are perfectly opaque when in a state of fusion;
and are crystalisable when suffered to cool slowly
and undisturbed.  The tetrahedron and the cube
are their primitive figures, though they very often
take the octahedral form.  They can likewise be
volatilised at very high temperatures.  They are
the best conductors of caloric and electricity.
Their susceptibility of combination is very great:
they unite with carbon, sulphur, and phospho-
rus.  They do not combine with earths by fu-
sion;  but their oxids readily unite to acids,
alcalies, and earths.  They decompose water and
several acids.  Some effect this at common tem-
peratures: some require a red heat, and others
the interposition of another body.  Water does
not dissolve any of the metals, though it is a
solvent of some of their oxids.  They are inso-
luble in ardent spirit, ether, or oils.  They are
all capable of combining with oxigen, though
many of them require very high temperatures to
effect this union, and others cannot be united to

it but in an indirect manner. Most of the metals can be combined with each other; they then form alloys, many of which are of the greatest utility in the arts.

### NATURAL HISTORY OF ORES.

Ores may be either native, that is to say, metals in a state more or less pure, or uncombined with any other substance, or in the state of an oxid, or sulphuret, or carburet, or metallic salt. They are found in the bowels of the earth, sometimes indeed at the surface, and more generally in mountains than in plain or level districts.

Ores are usually met with in crevices, or clefts of rocks, and are then called *veins.* These veins are frequently deposited *upon,* mixt, or surrounded by some stony substance, which is of a different nature from that of which the rock itself is composed. This substance whatever it may be, is called the matrix of the ore, which however must not be confounded with the mineralizing substance, with which the metal is combined, such as sulphur, arsenic, oxigen, &c. for this latter is chemically combined with the metal, so as not to be separable but by chemical

means, whereas the matrix may be separated by mechanical efforts.

The veins of ores are always more or less inclined to the horizon, and hence they are distinguished by the names of direct, oblique, or inclined veins, according to the angle they make with the horizon. Thus placed by the hand of nature, they are more easily discovered, than if situated on a level, or in plains. For a more circumstantial account of the general nature and characters of mineral veins, beds of ores, their formation, relative age, modes of working, and modes of discovering them, the reader is referred to a System of Mineralogy and Mineralogical Chemistry now in the press, which will be published shortly.

### CHARACTERISTIC PROPERTIES OF ORES.

Ores of metals may be distinguished from other minerals, by their greater specific gravity. They are at least five or six times heavier than water when perfectly free from foreign matters. All that is necessary to be done to distinguish metallic ores from other mineral substances is, to find their specific gravity, or in other words,

K

to weigh them hydrostatically. This may be done as stated already, page 21.

### ANALYSIS OF ORES.

The variety of metallic ores being very great, no general method of analysing them can be given, which might possibly prove useful to those who are not skilled in chemical pursuits. The best method of acquiring that knowledge consists in examining the different orders and genera of ores, one by one, so as to acquire a knowledge of those generalities which have been deduced from the analytical labours of former philosophers, and to become familiar with certain general principles, and manipulations, which characterize, and are requisite for the analysis of each individual.

## ORDER I.

### ORE OF PLATINA.

#### *Genus* I.—*Native Platina.*

This ore has hitherto been met with only in the state of an *alloy*, containing, either mechanically mixed or chemically combined with it, nine or ten other metallic substances, of which

not less than four are distinct metals, besides the
metal to which the name of platina properly
belongs.

#### ANALYSIS OF NATIVE PLATINA.

The grains of platina met with in commerce,
which were, until lately, considered as a homo-
geneous substance, are now known to contain
not less than eight metals, and sometimes even
nine or ten : these are, mercury, gold, platina,
iron, palladium, rhodium, osmium, iridium,
copper, and lead.

*Process* I.—To separate the mercury, intro-
duce the ore into a barometer tube ten or
twelve inches long, closed at one end : place the
closed end in a crucible filled with sand, sur-
round the crucible with fire in the furnace, till it
is of a dull red heat. The mercury will thus
become sublimed in the colder part of the tube,
it may be collected by cutting the tube with a
file, and removing the sublimed quicksilver by a
feather or wire.

II.—The separation of the iron requires less
trouble. This metal is present chiefly in the
state of iron sand ; the greatest portion of which

may be separated by the magnet, the remainder will be best obtained by a process to be detailed immediately.

III.—To separate the gold which was alloyed with the mercury, let the ore be digested in dilute nitro muriatic acid, without the assistance of heat. Repeat this operation till all the gold is dissolved, which may be known by a solution of sulphate of iron, not occasioning a precipitate when added to the muriatic solution.

IV.—To obtain the gold from this fluid, add to it a solution of green sulphate of iron, or sulphureous acid, till no more cloudiness ensues; the precipitate which falls down is metallic gold, it may be collected on a filter, and fused into a button.

V.—The solution from which the gold has been separated, should next be examined for platina, portions of which may probably have been dissolved by the nitro-muriatic acid. (Experiment III.) To detect this metal, add to it a solution of muriate of ammonia; if a buff, or orange-coloured precipitate ensues, platina is present; the precipitate which falls down is muriate of ammonia and platina : let it be put aside for farther use.

VI.—The ore left and thus freed from the gold

it may contain, should be digested in sixteen
times its quantity of nitro-muriatic acid, com-
posed of two parts of muriatic, and one of nitric
acid, diluted with one-fourth part of water, as-
sisting the action by a gentle heat. This ope-
ration is to be repeated until all the platina that
was present in the ore is dissolved, which may
be known by muriate of ammonia, not occa-
sioning a precipitate when added to the acid
that has been made to act on the ore. The
insoluble substance left, may be washed, dried,
and preserved for further use. It contains the
two new metals iridium and osmium.

VII.—The muriatic solution contains platina,
palladium, rhodium, copper, iron, and lead, if
the latter 3 metals are present, to separate the
platina add to it a solution of muriate of am-
monia, dry the precipitate, and reduce it to the
metallic state by heat, together with that ob-
tained before. (Experiment V.)

VIII.—Into the fluid from which the platina
is separated, a polished plate of zinc may then
be suspended, and suffered to be immersed in it
till it cease to produce any farther precipitate;
this obtained product consists of all the metals
(iron excepted) that were contained in the solu-

tion, namely, rhodium, palladium, copper, lead, and perhaps a small portion of platina.

IX.—Digest the precipitate obtained in dilute nitric acid repeatedly, until a chrystal of sulphate of potash, when added to the solution, occasions no further cloudiness; the precipitate is muriate of lead, which may be reduced by fusing it with carbonate of soda.

X.—To this fluid from which the lead has been separated, after having been concentrated by evaporation, add liquid ammonia in excess, a brown precipitate perhaps falls down which is iron; this precipitate after being ignited with a little wax, gives the quantity of metallic iron that was contained in the ore.

XI.—To obtain the copper, neutralize the ammoniacal solution, from which the iron has been separated, by sulphuric acid, and suspend in it a cylinder of polished zinc or iron, the copper will become precipitated in a metallic state upon the cylinder of zinc.

XII.—To separate the rhodium, palladium, aud platina, from the insoluble residue left, (in process IX.) digest it in dilute nitro-muriatic acid, and effect a solution; to which muriate of soda, equal in weight to about $\frac{1}{50}$th part of the ore of platina employed, should be added, then

evaporate the whole to a dry mass by a gentle
heat : the dry mass consists of the triple salts of
muriate of platina and soda, palladium, and
rhodium. To separate these salts, wash the dry
mass repeatedly in small quantities of alcohol;
the muriate of platina and soda, as well as the
palladium become separated, and the salt of
rhodium remains behind in a state of purity,
being insoluble in alcohol.

XIII.—To separate the palladium, add to the
alcoholic solution prussiate of potash, the preci-
pitate which falls down is prussiate of palladium.
On heating it to redness the palladium will be
obtained in a metallic state.

XIV.—To ascertain the presence of platina,
if any is contained in the solution, add muriate
of ammonia, collect the precipitate, and proceed
as directed before, process VI.

XV.—To obtain the rhodium, take the salt
which was not acted on by alcohol, (process
XII.) which consists of the oxid of rho-
dium, united to common salt ; re-dissolve it
in boiling water, and suspend in it a cylinder
of polished zinc ; the black powder which falls
down is rhodium : on heating it strongly with
borax, it assumes a metallic lustre; it may be
rendered fusible by arsenic, and also by sulphur,
both of which may again be separated by a con-

tinued heat. For the analysis of the black
powder, left behind in process VI. containing
the two new metals called iridium and osmium,
the reader is referred to the article iridium.

## ORDER II.

### ORES OF GOLD.
*Division of Ores of Gold.*

Gold, the most precious of all metals, is hither-
to found only in the state of an alloy, combined
with silver, copper, tellurium, &c. Ores of gold
are generally divided into four sub-species, viz.

Sub-species 1.— *Pure gold.*
            2.— *Brass yellow native gold.*
            3.— *Greyish yellow native gold.*
            4.— *Gold dust.*

Gold is also met with in some species of py-
rites, called auriferous pyrites ; and in some lead
ores, viz. auriferous sulphuret of lead. Of the
different sub-species of gold ores, several varieties
are distinguished from each other, according to
the different shapes in which the gold is found
to exist in them, hence the denominations of
*gold in filaments*, or *filamentous gold ore, den-
dritical gold, lamellated, arborescent, wire-
shaped gold, &c.*

ANALYSIS OF ORES OF GOLD.

1. *Analysis of Native Gold.*

The analysis of gold ores is very simple, the chief difficulty arising from the minute portion of this metal contained in the greater part of the ore, even of these which are called very rich.

*Process* I.—Take one part of the ore, freed as much as possible from its matrix, reduce it to a fine powder, mix it with four times its weight of sub-carbonate of potash and one of glass of borax, melt the mixture in an earthen crucible, and after having fused it for half an hour, pour it out on a stone slab, suffer it to cool, and reduce it to powder.

II. Transfer the mass into a Florence flask, cover it with nitro-muriatic acid and digest it in a gentle heat for a few hours. Decant the fluid and repeat the digestions until the residue is of a pure white colour. Let it be washed, and add the washings to the muriatic solution.

III.—Transfer the fluid obtained in the foregoing processes into a Wedgwood's bason, and evaporate it slowly, over a lamp, to dryness.

IV.—Pour upon the residue, obtained in the last process, so much boiling distilled water as

is sufficient to dissolve it, and filter the solution through paper placed in a funnel.

V.—Having done this, prepare a solution of green sulphate of iron, by dissolving one part of that salt in eight or ten of boiling water, and add so much of the solution to that obtained in process IV. till no farther change of color ensues, then suffer the whole to stand undisturbed for some days; the gold which was contained in the fluid will now be precipitated, and found at the bottom of the vessel, in the state of a brown powder.

VI.—Decant the fluid from this powder carefully, collect the latter, which is metallic gold, by putting it upon a filter, and when perfectly dry, introduce it into a crucible, and fuse it into a button or mass, with a small portion of nitre.

*Remark*—If the gold exists in the ore alloyed with a small portion of silver, as in the ores, called yellow native gold, a white powder will be seen floating in the nitro-muriatic solution : 100 parts of this powder when separated by the filter, and perfectly dried, contain 75 parts of silver, which may be obtained from it, as shall be noticed more fully under the article of silver ores.

The presence of silver may also be detected by

exposing the insoluble residue (process II.) to the rays of the sun, the mass will acquire a purplish tint if it contains silver. If this be the case, let it be mixed with three times its weight of sub-carbonate of potash, and fuse it for a quarter of an hour. The silver will be thus reduced to the metallic state.

If the ore contained copper, a polished cylinder of iron or zinc, after having been immersed in the nitro-muriatic solution, will be covered with a crust of copper, the increase of weight of the cylinder gives the quantity of copper. In this case the solution should have no excess of acid.

When gold is found interspersed amongst sand, or earthy substances, in the state of so minute particles, that it cannot be distinguished by the mere eye, we may examine such substances, in the following manner:

## 2. *Analysis of gold dust.*

*Process* I.—Diffuse the sand or earth through a large quantity of water in a convenient vessel, and frequently decant the fluid immediately after stirring it each time, by that means, the lighter particles of sand, or earth, as well as other

substances, remaining longer suspended, may thus be washed away by the water employed, whilst the more ponderable particles of gold, fall to the bottom with greater rapidity.

II.—But as it would be difficult to separate the gold thus completely, by mere mechanical ablution with water, let the last portion of sand which has been repeatedly washed, be reduced to a very subtile powder, put it into a flask, cover it with nitro-muriatic acid, and digest it by heat for at least one hour, dilute the fluid with water, and separate the gold, by adding to it a solution of sulphate of iron, as directed, page 106, process V.

The presence of gold may be detected in any ore by effecting a solution of it in nitro-muriatic acid, and then mingling it with a solution of green sulphate of iron. If the minutest quantity of gold be present, a purple brown precipitate will gradually appear.

When a mineral is examined merely for gold and silver, which it contains, it is a usual practice to pulverise it very finely, and digest it first in moderately strong nitric acid, and then in nitro-muriatic acid. The first solution contains the silver, the second the gold. This, however, is a very inaccurate way of proceeding, especially

for the silver, because whenever this does not greatly exceed the gold, it will be more or less covered by it, from the action of the nitric acid, and, on the subsequent digestion with nitro-muriatic acid, will be converted into muriate of silver, and thus rendered insoluble.

There are several ways mentioned by authors of analysing in the dry way, or rather of assay-ing ores of gold; none of them, however, are equal in accuracy to the modes of analysis in the humid way, which we have mentioned.

L

# ORDER III.

SILVER ORES.

*Division of Silver Ores.*

The ores of silver are more numerous than those of gold, mineralogists have divided them into different genera, according to their mineralising substance, which with the metal forms the ore; namely,

GENUS I.—*Alloys of Silver.*

Species 1.—Native Silver.
      2.—Plumbiferous Silver.
      3.—Auriferous Silver.
      4.—Antimonial Silver.
      5.—Arsenical Silver.

GENUS II.—*Sulphurets of Silver.*

Species 1.—Common Sulphuret of Silver; or, Vitreous Silver Ore.
      2.—Antimonial Sulphuret of Silver; or, Brittle, Vitreous Silver Ore.
      3.—White Silver Ore.
      4.—Grey Silver Ore.

5.—Black Silver Ore.
6.—Bismuthic Silver Ore.

GENUS III.—*Oxides of Silver.*

Species 1.—Dark red, or ruby, Silver Ore.
2.—Light red Silver Ore.

GENUS IV.—*Salts of Silver.*

Species 1.—Muriate of Silver.
2.—Carbonate of Silver.
3.—Argillaceous muriate of Silver.

As each of these different genera of ores require different treatment, we shall consider them one by one, in order to give an example of all of them.

### ANALYSIS OF ALLOYS OF SILVER.

Species I. *Analysis of Native Silver.*

*Process* I.—Take one part of the ore previously comminuted, affuse upon it in a Florence flask three or four parts of nitric acid, and apply a gentle heat; repeat this operation till a new addition of nitric acid does not produce any

further action upon the residue, from which the acid has been decanted; having done this, mix the different nitric solutions, pour over the insoluble residue a small quantity of water at a time, till this fluid runs off tasteless, then mix the water used for washing, with the first obtained solutions.

II.—Add to the fluid obtained in the first process, common salt, dissolved in water, in small quanties at a time, till no farther precipitate ensues; collect this precipitate, pour water over it so as to wash it thoroughly, then suffer it to dry. When perfectly dry, 100 parts contain 75 of silver, which may be obtained from it in the following manner:

III.—Mix one part of the dry precipitate (muriate of silver) with three of carbonate of soda, freed from its water of crystallisation, introduce this mixture into a crucible in the bottom of which a portion of the same salt has been put and pressed down; expose the mixture to a red heat for half an hour, or till it fuses quietly. Then suffer the crucible to cool, and upon breaking it, a button of pure silver will be found at the bottom.

Species II.—*Analysis of Plumbiferous Native Silver.*

In this ore the silver exists alloyed with lead, and sometimes also with iron. The analysis of it may be accomplished in the following manner :

*Process* I.—Proceed as in the former process I, page 111, and immerse into the solution of the ore in nitric acid, a polished cylinder of copper : let it continue in the solution for at least 24 hours. The silver will now be precipitated in a metallic state. It may be fused into a button, without any addition, and its weight ascertained. It is essential however in this case that the solution of the ore should have not much excess of acid.

II.—To the fluid from which the silver has been obtained, add a solution of sulphate of soda in water. If a white precipitate ensues it is a proof that lead was present in the ore. Its quantity may be determined by the weight of this precipitate; 100 parts of it when perfectly dry, indicate 30 of metallic lead.

III.—The presence of iron may be investigated by dropping into the solution, prussiate of potash, which in that case occasions a blue precipitate ; or by ammonia, occasioning a brown powder to fall down.

Species III. — *Analysis of Auriferous Native Silver.*

In this ore silver exists alloyed with gold. The analysis may be conducted thus :

*Process* I.—Let one part of the ore reduced to a fine powder be repeatedly digested in three of nitric acid, until the portion of the acid last decanted from the ore, does not yield any white precipitate, by dropping into it muriatic acid.

II.—Digest the insoluble residue in nitro-muriatic acid, till a new addition of that fluid extracts no more gold, which may be known by not becoming turbid by the addition of sulphate of iron, or by adding to it a few drops of muriate of tin.

III.—To recover the gold contained in the nitro-muriatic solution, proceed as mentioned before, page 105, process III, IV, V, &c.

IV.—The silver that was contained in the ore, and which is extracted in the first process by means of nitric acid, may be separated by precipitating it with muriatic acid, and subsequent reduction. See page 112.

*Remark.*—If the ore contains copper, as is the case in the *cupriferous native silver ore,* the presence of this metal may be detected by

dropping into the nitric solution liquid ammonia, the fluid will instantly acquire a blue colour.

## Species IV.—*Analysis of Antimonial Silver.*

In this ore silver is alloyed with antimony.—Its analysis may be effected in the following manner:

*Process* I.—Digest one part of the ore repeatedly in muriatic nitric acid, till all the silver is removed.

II.—Separate the silver from this solution by a cylinder of copper, as stated, page 113.

III.—Digest the residue of process I. repeatedly in muriatic acid, assisted by heat, and decompose this solution by immersing in it a cylinder of iron: the precipitate which falls down is metallic antimony.

## Species V.—*Analysis of Arsenical Silver.*

This ore consists of silver, arsenic, iron, and antimony.

*Process* I.—Digest the ore repeatedly in nitric acid, until all the silver is extracted.

II.—Separate the silver from the obtained solution by muriatic acid, or common salt, and reduce it to the metallic state, by fusing it with carbonate of soda. See process III. page 112.

III.—The silver being separated, let the so-
lution be rendered neutral by the admixture of
carbonate of potash: a precipitate falls down
which is arseniate of iron.

IV.—To decompose the arseniate of iron let
it be dissolved in nitric acid, and decompose the
solution by the addition of nitrate of lead : 100
parts of the dried precipitate indicate about 22 of
arsenic.   Or the decomposition of the arseniate
of iron may be effected by heating it repeatedly,
in contact with ignited charcoal, till no arseni-
cal smell is observable.   The arsenic will be vo-
latilized, and the oxid of iron left behind.

V.  To separate the antimony let the inso-
luble residue of process I. be repeatedly digested
in muriatic acid, and separate the antimony, by
immersing in it a cylinder of iron.

### ANALYSIS OF SULPHURET OF SILVER.

Species I.—*Analysis of common Sulphuret of
Silver.*

The analysis of this ore, which consists of
silver and sulphur only, may be accomplished
thus:

*Process* I.—Let one part of the ore be digested
in eight times its weight of nitric acid, of about

13.5, specific gravity, diluted with half its quantity of water, and repeat this operation till a new portion of acid (after being suffered to act upon the ore for some time) does not become cloudy by the addition of a few drops of muriatic acid; then wash the residue, and add the water thus employed to the nitric solution of the ore.

II.—In order to separate the silver from this solution, proceed as directed in the analysis of native silver ore, page 111.

III.—To ascertain the quantity of sulphur, which existed in the ore, take the insoluble residue of the first process dried thoroughly, put it into a crucible, and expose it to a red heat; the sulphur will take fire, and burn off. The loss of weight indicates the greater part of the sulphur. But in order to be more correct, pour water upon the residue left in the crucible, filter the fluid and drop it into a solution of nitrate of barytes, a white precipitate will fall down, collect it on a filter and dry it perfectly, 100 parts of this precipitate indicate 14. 5 of sulphur, which added to the loss of the weight which the residue of the first process suffered, gives the real quantity of sulphur contained in the ore.

*Remark.*—The fluid obtained in process II. by

decomposing the nitric solution of silver, by means of muriatic acid, should also be assayed for sulphuric acid, which perhaps may have been formed during the repeated action of the nitric acid upon the sulphur contained in the ore. If therefore a precipitate takes place on dropping into the above fluid nitrate of barytes, sulphuric acid has been produced ; the precipitate must be collected and weighed, and the quantity of sulphur calculated as stated above, and this should be added to that already noticed.

### Species II.—*Analysis of Antimonial Sulphuret of Silver.*

The analysis of this ore was effected by Klaproth, in the following manner:

*Process* I.—One hundred grains of the ore were repeatedly boiled in nitric acid, till the original black colour became changed to a greyish yellow.

II.—To this nitric solution muriate of soda was added, by which a precipitate of 84.75 grains of muriate of silver was obtained.

III. — The filtered solution was examined by sulphate of soda, but no precipitate took place ; thus shewing the absence of lead. An excess of liquid ammonia was then added,

which threw down a grey precipitate, weighing
five grains. This, when heated, exhaled a slight
arsenical odour; and being dissolved in nitric
acid, afforded a deep blue precipitate with prus-
siate of potash : thus showing it to be oxyd of
iron, with a little arsenic.

IV.—The ammoniacal solution, which had a
light blue colour, was slightly supersaturated
with sulphuric acid; a polished iron cylinder
being then immersed, became tinged with cop-
per, but in so small a quantity as not to be
appreciable.

V.—The ore left, and which was insoluble in
nitric acid, process I. was digested in nitro-muri-
atic acid, and the part not taken up by this fluid
amounted to 13 grains, of which 12 were burnt
off on a scorifying test, and were sulphur ; the
remainder was silex.

VI.—The nitro-muriatic solution, being pour-
ed into water, deposited 13 grains of oxyd of an-
timony.

Species 3.—*Analysis of White Silver Ore.*

The analysis of this ore was accomplished by
the same chymist, in the following manner :

*Process* I.—Four hundred grains of this ore,
being pulverized, were mixed with four ounces of

strong nitric acid, and two ounces of water.
After the acid had ceased to act it was poured
off, and replaced by two ounces of nitric acid, to
which, being made to act upon it for some time,
was mingled with eight ounces of water, and the
whole made to boil. The undissolved residue
weighed 326 grains.

II.—To the nitric solution was added com-
mon salt, by which muriate of silver was imme-
diately precipitated, and after a few hours were
also deposited crystals of muriate of lead. The
mixed precipitate was boiled with much water,
by which the muriate of lead was dissolved, and
the muriate of silver obtained pure. From this,
by fusion with soda, as stated before, page 112,
were obtained 81.5 grains of silver.

III.—Into the two solutions, mingled toge-
ther, ammonia was added to saturation, which
threw down a light brown precipitate, weighing
40 grains. This was re-dissolved in nitric acid,
and by the addition first of prussiate of potash,
and then of soda, was separated into 12 grains
oxyd of iron, and 28 alumine.

IV.—The undissolved residue was boiled in
repeated portions of muriatic acid, and at length
there remained only 51 grains, which, when ig-
nited, proved to be 49 grains of sulphur, and

two grains of a residue, half of which consisted of silex, and the rest being soluble in muriatic acid, was added to the other muriatic solution.

V.—The muriatic solution was evaporated till it ceased to deposit crystals. These being collected, and mixed with twice their weight of black flux, and reduced in a lined crucible, afforded 16¾ grains of lead, which, being cupelled, emitted a few antimonial vapours, and left behind ⅛ of a grain of silver.

VI.—The muriatic solution, from which the muriate of lead had been separated, being poured into water, deposited oxid of antimony, which, mixed with soap and black flux, was reduced by fusion to the metallic state. In this process, however, a slight portion of the antimony was volatilized ; what remained weighed 31.5 grains.

Species IV.—*Analysis of Grey Silver Ore.*

The analysis of this ore was conducted by Klaproth, thus :

*Process* I.—Three hundred grains of this ore were pulverized and digested with four times their weight of nitric acid. When this had ceased to act, it was poured off, and replaced by

M

another equal quantity of the same acid. The undissolved residue was of a greyish yellow colour, and weighed 188 grains.

II.—The nitric solution was decomposed by muriated soda. The precipitate obtained afforded, by fusion with soda, 31.5 grains of silver.

III.—The silver being thus separated, sulphate of soda was added to the solution, but without occasioning any precipitate, therefore the liquor contained no lead.

IV.—Ammonia was then added to the fluid in excess, which occasioned a brownish red precipitate, which, after being ignited, weighed 9.25 grains. By digestion in nitric acid it dissolved, with the exception of 0.5 grains of silex. Prussiate of potash threw down from the solution a deep blue precipitate, and 1.5 grains of alumine was obtained, by means of soda. —Hence the oxyd of iron amounted to 7.25 grains.

V.—The blue ammoniacal solution was now supersaturated with sulphuric acid, and a cylinder of polished iron precipitated 69 grains of copper.

VI.—The insoluble portion was boiled with six times its weight of muriatic acid, which,

being poured off when its action had ceased, left 105.5 grains still undissolved.

VII.—The muriatic solution having been concentrated by evaporation, deposited a little muriate of silver, from which 0.25 grains of metal was obtained. The fluid being then poured into water afforded 97.25 grains of oxid of antimony, equivalent to 75 of metal.

VIII.—The residue left in Experiment VI, which resisted the action of muriatic acid, weighing 105.5 grains, was ignited, and 25.25 grains of sulphur were burnt off. The remainder, being silex, was fused with black flux, and afterwards dissolved in water, leaving behind 0.75 grains of silver. Hence the amount of silex was 79.5 grains.

The analysis of the black silver ore may be effected in a similar manner.

Species V.—*Analysis of Bismuthic Silver Ore.*

*Process* I.—Digest the ore repeatedly in nitric acid, till this fluid exercises no further action on the ore.

II.—Pour the nitric solution into a large quantity of water, a precipitate falls down, which

is oxid of bismuth ; 123 parts of it, when dry, are equivalent to 100 of bismuth.

III.—Evaporate the fluid to at least one-third of the original bulk, and drop into it muriatic acid. Collect the precipitate which falls down ; wash and dry it.

IV.—The precipitate now left is muriate of silver : let it be digested in nitric acid, decant the fluid, and mingle it with a large quantity of water. If any precipitate should ensue, it is a portion of oxid of bismuth which escaped the action of the water in process II. Let it be dried and added to that obtained before.

V.—The remaining fluid may next be assayed for lead : let it therefore be concentrated to dryness ; dissolve the residue in a sufficient quantity of water, and drop into it sulphuric acid. A precipitate will appear if lead be present : let it be collected and dried, and the quantity of lead determined, as stated, page 113, process II.

VI.—The solution from which the lead is separated may then be examined for iron ; for that purpose add to it liquid ammonia, till the odour of the latter considerably predominates. A brown precipitate falls down, if iron was contained in the ore : this precipitate must be heated to redness, and weighed : 100 parts of it are equal to 53 of iron.

VII.—If the ore contained copper, the fluid has now a blue colour. It may be saturated with sulphuric acid, in excess: a cylinder of iron will precipitate the copper.

VIII.—The insoluble residue left in process I. may be examined for sulphur; for that purpose let it be ignited in a crucible, and proceed according to the rules mentioned, page 117.

IX.—The residue may again be digested repeatedly in muriatic acid, and assayed for lead by sulphuric acid. If a precipitate ensues, it is sulphate of lead, which is to be added to that obtained before. The residue now left, if any, is merely the matrix of the ore.

### ANALYSIS OF OXIDS OF SILVER.

### Species 1.—*Analysis of Dark-Red, or Ruby, Silver Ore.*

In this ore silver exists, in the state of an oxid, combined with sulphur and oxid of antimony, and sometimes sulphuric acid. Its analysis was effected by Klaproth in the following manner:

*Process* I.—Five hundred grains, being very finely pulverized, were digested for several hours

M 3

in a gentle heat, with six times their weight of
strong nitric acid and water: a further quantity
of water was then added, and the liquor made to
boil. The nitric solution was decanted off, and
the undissolved residue digested with a like por-
tion of acid as at first, repeatedly; and lastly it
was poured on a filter, and the residue washed
in water.

II.—The nitric solutions, together with the
washings, being mingled together, were evapo-
rated to one-eighth of their bulk, and the re-
maining fluid deposited, by cooling a consi-
derable quantity of greyish-white crystals of sul-
phate of silver. The nature of these crystals be-
ing ascertained, water was added to the super-
natant liquor, and by a gentle heat the whole
was re-dissolved. To the solution muriatic acid
was added, as long as any precipitate fell
down. The muriate of silver weighed 391.5
grains, when dried.

III.—The fluid from which the above preci-
pitate had been obtained was reduced to a small
bulk by evaporation, in consequence of which it
became turbid, and deposited one grain more of
muriate of silver. Nothing now remained in the
fluid, except sulphuric acid.

IV.—The insoluble residue which resisted the action of nitric acid weighed 202 grains, it was digested in nitro-muriatic acid, consisting of five parts muriatic, and one of nitric acid, which left 65 grains undissolved. This residue, being washed and dried, was exposed to a gentle heat, in which the sulphur was volatilized, leaving six grains and half of muriate of silver.

V.—The nitro-muriatic solution, after having been concentrated by evaporation, was poured into a large quantity of water, which occasioned a white pulverulent precipitate, weighing, when dried, 132 grains, which was oxyd of antimony, entirely unmixed with the smallest portion of arsenic. When fused, in a covered crucible, with tartrate of potash, a button of reguline antimony was produced ; and this, when heated on a scorifying test, became volatilized, leaving behind 0.5 grains of silver.

VI.—The residues of the nitro-muriatic solution (IV.) and of the nitric solution (III.) were mixed and distilled till dense white vapours appeared. The concentrated fluid was diluted with water, and muriate of barytes added, as long as a cloudiness appeared. The sulphate of barytes obtained weighed 194 grains.

In this analysis, the muriate of silver obtained
amounted to 399 grains, which, being reduced
to the metallic state furnished, together with the
half grain of silver contained in the antimony
(process V.) exactly 300 grains of pure silver;
a result which was confirmed by two assays of
this ore on the cupel, each of which yielded 30
*per cent.* of silver.

In order to ascertain the quantity of antimony
contained in the 132 grains of white oxid (pro-
cess V.) 100 grains of reguline antimony were
digested by heat in muriatic acid, to which nitric
acid was added, drop by drop, till the whole of
the metal was dissolved. This solution being
concentrated by evaporation, and then poured
into water, afforded 130 grains of white oxid.
Hence the above 132 grains of oxid indicate
101.5 of metallic antimony.

With respect to the sulphuric acid which
made its appearance in this analysis, it is affirmed
by Klaproth to have pre-existed, at least for the
most part, in the ore, and not to have been pro-
duced by the action of the nitric acid upon the
sulphur, for the following reasons:

In the first place, the quantity of nitrous gas
disengaged during the action of the nitric acid

•n the ore, appeared by no means sufficient to account for the production of so large a quantity of sulphuric acid.

Secondly, some finely pulverized red silver ore, being digested with strong muriatic acid, the solution was found to contain not only antimony and silver, but also sulphuric acid.

Now, as muriatic acid is incapable of acidifying sulphur, it follows, that the abovementioned acid must have pre-existed in the ore.

This is further confirmed by an observation of Henkel's, that the silver may be extracted from the red ore merely by successive digestions in muriatic acid, which could not have happened without the presence of sulphuric acid likewise. —We shall return to the consideration of this question presently.

The analysis of this ore by Vauquelin was thus conducted :

*Process* I.—One hundred parts of the ore, finely pulverized, were digested in 400 parts of nitric acid, and 200 of water : the colour of the ore became grey, and lastly white. During the whole of this change there was no perceptible disengagement of nitrous gas; whence it may be concluded, says the author, that the ingredients of the ore were already sufficiently oxyge-

nated to dissolve in nitric acid. After a gentle ebullition, the whole was poured on the filter, and the insoluble portion, after ablution with water, weighed 42.06.

II.—The insoluble portion of process I. was digested in strong muriatic acid, by which its colour became yellow, and its amount was reduced to 14.66. Being then laid on a hot coal, it burnt entirely away with a blue flame, and all the other characters of sulphur. The sulphur of the ore, therefore, may be reckoned at 14.66.

III— The muriatic solution, being mingled with a large quantity of water, deposited a white precipitate of oxyd of antimony, weighing 28.25, which, according to Vauquelin, are composed of 16.13 antimony, and 12.12 oxygen.

IV—The nitric solution was mixed with muriatic acid, and furnished 72.66 of muriate of silver, which he estimated, according to Bergman, at 56.67 of metal.

*Remarks.* — In this analysis by Vauquelin there is no mention made of sulphuric acid, which was found so abundantly by Klaproth; and in order to bring this matter more completely to an issue, 100 parts of the ore were digested with a solution of potash. As soon as the two substances came into contact, the

colour of the ore changed first to grey, and pre-
sently to a deep black, 66 parts remaining un-
dissolved. These were treated with dilute nitric
acid, at a gentle heat, upon which a disen-
gagement of nitrous gas took place, and the un-
dissolved matter amounted only to eight parts,
and was sulphur. The nitric solution, on the
addition of muriatic acid, afforded 70 of muriate
of silver. The alkaline solution, which was per-
fectly clear and colourless, gave, when treated
with muriatic acid, 32 of sulphuretted oxid of
antimony. After the separation of this, the re-
maining fluid was mixed with muriate of barytes,
without any precipitate being formed : hence it
contained no sulphuric acid. Indeed, Klaproth
himself, at the conclusion of his dissertation on this
subject, appears to be disposed to think that the
sulphuric acid does not exist in the ore, but that
the whole of the sulphur is in the state of an
oxid : on account of the action of the acid em-
ployed in the decomposition of the ore, the
whole of the oxigen unites with part of the sul-
phur, converting it into sulphuric acid, and leav-
ing the remainder of the sulphur completely de-
oxygenated. But we do not see how this can
be the case : besides, it is obvious that the sil-
ver at least must be in the state of oxid, since

it dissolves in nitric acid, without producing any nitrous gas. If it were not, therefore, for the circumstance, that the ore, when treated with simple muriatic acid, gives out sulphuric acid, we should be disposed to believe, that the ore contains no sulphuric acid, and that the oxigen is combined, not with the sulphur, but with the metal.

The light red silver ore may be analysed in a similar manner.

### ANALYSIS OF NATIVE SALTS OF SILVER.

Species 1.—*Analysis of Muriate of Silver.*

The analysis of this ore was conducted by Klaproth thus:

*Process* I.—Two hundred grains of a massive variety of muriate of silver were treated with thrice their weight of nitric acid, but no perceptible action took place, either in the cold or at a boiling heat, except that a little oxid of iron was separated. The solution being decanted, and mixed with ammonia, an additional portion of oxid of iron was thrown down. The supernatant liquor became opalescent on being mixt with muriatic acid, but no precipitate was deposited :

hence it was manifest, that the muriate of silver
in the ore was not mixed with any in the metal-
lic or sulphuretted state, otherwise it would have
been taken up by the nitric acid, and have af-
forded a precipitate with muriatic acid.

II.—The insoluble part of the ore was then
fused with twice its weight of subcarbonate of
potash, and yielded 133 grains of metallic silver.

On these preliminary experiments the following
analysis was founded.

III.—Two hundred grains of the ore were
mixed with 600 grains of potash, freed from
carbonic acid, and fused in a glass retort. After
cooling, the neck of the retort being broken off,
the fused mass was softened with hot water, to
effect a solution, and the fluid was rendered clear
by filtration.

IV.—The insoluble portion was next digested
in nitric acid, by which the greater part of it was
dissolved.

V.—The insoluble part now left was digested
in nitro-muriatic acid, which left undissolved a
few grains of residue, of a white colour, which
proved to be muriate of silver, with a little of the
matrix of the ore. This muriate of silver afforded
two grains of silver. The nitro-muriatic solu

N

tion, being decomposed by liquid ammonia, yielded seven grains of oxyd of iron.

VI.—To the nitric solution (IV.) was added common salt dissolved in water, and the muriate of silver thus obtained afforded, by fusion with soda, $134\frac{1}{2}$ grains of silver. The remaining fluid gave, by saturation with ammonia, five grains of oxyd of iron.

VII.—The alkaline solution (III.) being saturated with acetous acid, yielded three and half grains of alumine, which after being separated, the fluid was evaporated to dryness, and the product digested in alcohol; by which means the acetite of potash formed was removed, and the muriate of potash left behind: this latter, by solution in water, and subsequent evaporation, yielded $117\frac{1}{2}$ grains of muriate of potash.

VIII.—The muriate of potash being again dissolved in water, muriate of barytes was added, by which means about three grains of sulphate of barytes was obtained, which, according to Klaproth, indicate one and half grains of sulphate of potash, and this reduces the amount of muriate of potash to 116 grains, in which the muriatic acid amounts to 42 grains.

From these results the contents of the ore are stated as before.

*Remark.*—The analysis here adopted appears to be perfectly satisfactory, but there seems to be a few oversights in stating the results.

The silver is a little under-rated; its amount, according to processes V. and VI. being 136.5 or 68.25 *per cent.* There is no notice taken of the oxigen, which forms an essential part of muriate of silver; and in consequence of this omission, the muriatic acid is probably estimated much too high. The amount of the silver may be considered as ascertained with the most exactness, as it was actually reduced to the reguline state. Assuming this, therefore, as the basis of our calculations, and that 100 parts of muriate of silver consist of 75.24 silver, 8.16 oxigen, and 16.6 acid, it follows, that 136.5 of silver require, in order to be converted into muriate of silver, 14.72 of oxigen, and 30.04 of acid. But 30.04 of muriatic acid, when saturated with potash, would afford only about 84 of muriate of potash, instead of 116, as obtained by process VIII. It may be added, as a further proof of the amount of this salt being erroneously stated, that 42 grains of muriatic acid (contained in 116 grains of muriated potash) indicate 253 grains of muriate of silver, which is impossible, the

whole amount of the ore being only 200 grains.
It is probable, therefore, that the following cor-
rected statement of the contents of this ore
is nearer the truth than that quoted above,
viz.

> 68.25 Silver
> 7.36 Oxygen
> 15.02 Muriatic acid
> 6.00 Oxyd of Iron
> 1.75 Alumine
> 0.5 Sulphuric acid
> _____
> 98.88
> _____

Species 2.—*Analysis of Argillaceous Muriate
of Silver.*

The analysis of this ore may be conducted like
the preceding.—Klaproth states his analysis as
follows :

Upon 35 grains of pulverised ore nitric acid was
poured, and the mixture made to boil : neither
effervescence, nor red vapours appeared ; the
acid seemed to attack the ore but weakly ; the re-
siduum assumed the form of a precipitate, re-

sembling a cheesy coagulum. The acid, which was tinged of a faint blue, being separated through a filter, admitted of combination with common salt, without being rendered turbid. By the addition of carbonate of ammoniac to excess, alumine was thrown down, and the fluid appeared of a deep blue; but after it had been supersaturated with sulphuric acid, and an iron cylinder immersed into it, it deposited a thin coppery crust. The dried residue weighed 30 grains; it was extracted by repeatedly pouring upon it liquid ammonia, agitating it frequently. Nitric acid being added to a few drops of it, some muriate of silver immediately precipitated. The whole of this solution, when evaporated by a gentle heat, became converted into flexible membranes, of a pearl grey, which tarnished into blue by exposure to air; and when gently melted in a small silver cup, ran into a waxy substance. The weight of this fused muriate of silver amounted to $10\frac{1}{2}$ grains. When the alumine that was left behind, after the extraction of the muriate of silver by ammoniac, was melted with soda, it still afforded a bead of silver, of three-quarters of a grain. As this is equal to one grain of muriate of silver, the above 36 grains of this ore con-

tained $11\frac{1}{2}$ grains of muriated, or $8\frac{5}{8}$ths. of me-
tallic silver, and $2\frac{7}{8}$th grains of concentrated mu-
riatic acid.

Klaproth says, it is owing to the alumine con-
tained in this ore that it does not assume the
same appearance, when heated on charcoal, as
the common muriate, but that the metal trans-
udes in the metallic state, in small globules ; for
as that earth deprives the muriate of silver of its
acid, when heated, the silver is enabled to assume
the metallic form.

As silver, notwithstanding its great affinity
with muriatic acid, cannot enter into combina-
tion with it in the reguline state ; and since that
metal, as far as we know, is never found in the
bowels of the earth, in an oxidated state, it is dif-
ficult to ascertain the operation of Nature in
producing the corneous ore. Bergmann* was of
opinion, that Woulfe had solved that doubt by
asserting, that in the above-mentioned ore he
had traced the sulphuric acid, besides the muri-
atic, for silver unites readily with sulphur; and
since sulphurated silver not unfrequently under-

* Torb. Bergmann, on the Generation of Natural Corneous
or Muriated Metals.

Crett's Chemistre Annalen, 1784; No. IV page 377.

goes a decomposition, more especially when, as
in this case may be conjectured, from the pre-
sence of oxyd of iron, some sulphuret of iron,
disposed to disintegration, intervenes, the sul-
phur passes over into the state of sulphureous
acid, and forms sulphate of silver. If now mu-
riatic acid interferes, it will, by virtue of its
greater affinity to silver, decompose the sulphate,
and instead of it form muriate of silver—of that
species of muriate of silver which is found in
regular cubic chrystals, Bergman had already
conjectured, that it might be considered as pure,
and free from sulphuric acid. He also wished to
convert this conjecture of his into an established
truth, by duly examining that fossil; for, as he
very justly says, it is better to sacrifice such a
specimen, scarce as it yet is, to investigation,
than to deprive the science of a means of en-
larging our knowledge, by preserving it. The
wish of this chemist is in some degree accom-
plished, and his conjecture for the most part
confirmed, by the inquiry of Klaproth, with the
unimportant difference, however, that instead of
chrystallized muriate of silver, the chemist of
Berlin has employed a specimen of that which
occurs in lumps, or massive.

Mr. Klaproth thinks that, in order to comprehend how Nature can produce the muriate of silver, without the interposition of sulphur, or sulphuric acid, we may receive some light from the following intelligence, taken from a letter of Proust, in Rozier's Journal de Physique.—It is there stated, that the coined silver of the Spanish ship San Pedro d'Alcantaro, that was wrecked on the coast of Portugal, became coated with a blackish crust, of $\frac{1}{48}$th of an inch thickness, during the short time before it was recovered from the sea. This crust broke off in scales, and was a true muriate of silver. Moreover, Pallas* relates, that he has found, on the Jaik in Siberia, several old Tartarian silver coins, which in that tract of saline land were converted into true muriate of silver, some throughout their whole mass, and others on the surface only.

From this knowledge of the constituent parts of the native muriate of silver, art is enabled to imitate nature pretty nearly. If muriate of silver be made to fuse uniformly, at a moderate heat, an artificial muriate of silver ore is produced (according to Klaproth) which may be

* Nordische Beytraege, III. Vol.

made more similar to the natural one, by adding,
before the fusion, a proportional quantity of
oxid of iron. And if muriate of silver be dis-
solved in ammonia, and the fluid evaporated
in a gentle warmth, the muriate of silver ap-
pears, in small glittering scales, resembling
those with which the native ore is found partly
covered. But if this solution be left to sponta-
neous evaporation, the muriate of silver will
sometimes crystallize into solid regular crystals,
of the same appearance with the cubic crystals
of the native ore.*

Species 3.—*Analysis of Carbonate Silver.*

This ore may be analysed in the following
manner :

*Process* I.—Introduce into a tubulated retort,
connected with a graduated cylinder, filled with
mercury, and standing in the mercurial trough,
a determinate portion of the ore, and pour
over it, as expeditiously as possible, eight of ni-
tric acid ; the carbonic acid contained in the
ore will be extricated, and pass into the cy-
linder.

* Analytical Essays, VI. p. 124.

II.—To ascertain its bulk, pass up into the cylinder barytic water; the loss of the bulk of the gas gives the volume of the carbonic acid.

III.—To ascertain the quantity of silver, filter the contents of the retort, and add muriatic acid; the muriate of silver produced gives the quantity of silver contained in the ore, according to the rule so often stated before.

# ORDER IV.

## COPPER ORES.

### *Division of Copper Ores.*

The ores of copper are very numerous.—They are arranged in the following manner:

GENUS I.—*Alloys of Copper.*

Species 1.—Native Copper.

GENUS II.—*Sulphurets of Copper.*

Species I.—Vitreous, or Common Sulphuret of Copper.
      2.—Purple, or Variegated, Copper Ore.
      3.—Yellow Copper Ore, or Copper Pyrites.
      4.—Black Copper Ore.
      5.—Grey Copper Ore.

GENUS III.—*Oxides of Copper.*

Species 1.—Ruby Copper, or Red Copper Ore.

2.—Capillary Ruby Copper, or Hair
Copper Ore.

3.—Compact Ruby Copper.

4.—Tile Copper, or Brick-red
Copper.

Subspecies 1.—Indurated Tile Red Copper
Ore.

2.—Earthy Tile Red Copper.

Species 5.—Dioptase, or Emerald Copper.

6.—Bituminous Copper Ore.

GENUS IV.—*Salts of Copper.*

Species 1.—Blue Carbonate of Copper, Azure
Copper Ore, or Mountain Blue.

Subspecies 1.—Radiated Azure Copper.

2.—Earthy Azure Copper.

Species 2.—Green Carbonate of Copper, Ma-
lachite, or Mountain Green.

Subspecies 1.—Fibrous Malachite.

2.—Compact Malachite.

3.—Earthy Malachite.

4.—Ferrugenous Malachite.

Species 3.—Arseniate of Copper, Olive Ore,
or Octahedral Copper Ore.

Subspecies 1.—Lamellar, or Hexeadral Ar-
seniate of Copper.

Subspecies 2. — Prismatic Arseniate of Cop-
per.

3. Trihedral Arseniate of Cop-
per.

4.—Capillary Arseniate of Cop-
per.

5.—Ferriferous, or Martial Ar-
seniate of Copper.

Species 4.—Phosphate of Copper.

Species 5.—Muriate of Copper, or Green Cop-
per Sand.

Subspecies 1.—Compact Muriate of Cop-
per.

2.—Pulverulent Muriate of Cop-
per.

Species 6.—Sulphate of Copper.

ANALYSIS OF ORES OF COPPER.

Species 1.—*Analysis of Native Copper.*

*Process* I.—Let one part of the ore be dis-
solved in four or five times its weight of nitric
acid, and evaporate the solution to dryness.

II.—Upon the dry mass affuse about eight
times its quantity of water ; boil the mixture for
a quarter of an hour, and filter the fluid.

o

. III.—Immerse into this solution a polished cylinder of iron or zinc; the copper will be precipitated in a metallic state.

*Remark.*—If the ore contains gold, silver, and iron, it must be repeatedly digested in dilute nitric acid. The silver may be precipitated from this solution by a cylinder of zinc. The iron may be separated by evaporating the solution to dryness, dissolving it again in concentrated nitric acid, evaporating the acid as before, and repeating this operation several times successively : this being done, let water be poured on the mass, and filter the solution ; the iron will now remain upon the filter in the form of a brown powder, and the nitrate of copper becomes dissolved in the watery fluid. This fluid may be decomposed by boiling it with potash ; a precipitate is produced which is black oxid of copper; 100 parts of it, after being dried in a red heat, contain 80 of copper.

### ANALYSIS OF SULPHURET OF COPPER.

*Species* 1.—*Analysis of Vitreous, or Common Sulphuret of Copper.*

*Process* I.—Digest one part of the pulverized ore repeatedly in three times its weight of dilute

nitric acid, till it extracts no more copper, which may be known by dropping into the obtained solution liquid ammonia in excess; if the fluid acquires no blue colour it contains no copper.

II.—Evaporate this solution to dryness, re-dissolve it in concentrated nitric acid, and again evaporate the solution to dryness : repeat this process for several times successively.

III.—Boil the dry mass in eight times its weight of water, a brown powder becomes se-parated, which is the iron that was contained in the ore; collect it on a filter, wash, dry, and ignite it.

IV.—Mingle the fluid from which the iron has been separated with a solution of potash, till no further precipitate ensues, and boil it for a few minutes; collect the precipitate, and dry it in a red heat : 100 parts contain 80 of copper.

V. To ascertain the quantity of sulphur con-tained in the ore, heat the residue of process I. and proceed as directed before; but as part of the sulphur is generally acidified during the diges-tion of the nitric acid upon the ore, the solution, after the metal is separated, may be assayed for sulphuric acid by nitrate of barytes, and the real

quantity ascertained, according to the rule laid down, page 117. The ores called purple, yellow, and black copper ores may be analysed in a similar manner.

Grey copper ore contains, besides copper, sulphur and iron; also, silver, lead, and antimony: it may be analysed in a like manner; the silver may be separated by common salt (see page 112); but as lead is also separated by this substance, the precipitate must be digested in liquid ammonia; this dissolves the muriate of silver, and leaves the lead; by subtracting the weight which the precipitate has lost by this treatment the quantity of both the metals may be found. If antimony was present, it will be separated from the remaining solution by a copious affusion of water: the precipitate remains insoluble in that fluid.

### ANALYSIS OF OXIDS OF COPPER.

Species 1.—*Analysis of Ruby, or Red Copper Ore.*

Oxid of Copper, or Ruby Copper Ore, may be analysed by merely dissolving it in muriatic acid, and precipitating the copper by a cylinder of iron or zinc.

The following method was employed by Mr.

Chenevix* to examine the native red oxid of copper from Cornwall.

*Process* I.—One hundred parts of the ore, being submitted to the action of nitric acid, became totally dissolved by digestion.

II.—The obtained solution being evaporated to dryness was covered with muriatic acid, to convert it into a muriatic acid, and again evaporated to dryness.

III.—Upon the dry mass water was poured, till all the muriate of copper was extracted.

IV.—On immersing into the obtained solution a cylinder of iron, 88.5 of copper were obtained.

The species of copper ores called capillary, compact, or tile ruby copper ore, may be analysed in a like manner.

### ANALYSIS OF SALTS OF COPPER.

Species 1.—*Analysis of Blue Carbonate of Copper, or Mountain Blue.*

*Process* I.—In order to ascertain the quantity of carbonic acid which exists in the ore, united to the oxid of copper, let a portion of it be

* Philos. Trans. 1801.

heated in a retort to a dull redness; collect the
gas in the usual manner over mercury, and
let it be absorbed by lime-water, in order to
measure its quantity; or, if this should be
deemed too troublesome, let one part of the ore
be introduced into a bottle, containing three
parts of sulphuric acid, diluted with four of wa-
ter; close the bottle with a cork, into which is
fixed a capillary tube, and weigh the whole accu-
rately.    When no more effervescence ensues,
weigh the bottle and its contents again; and the
loss of weight will indicate, with tolerable accu-
racy, the quantity of carbonic acid which escaped.

II.—To ascertain the quantity of copper, di-
gest one part of the ore repeatedly in sulphuric
acid, diluted with an equal bulk of water, till
this acid extracts no more copper (see page 147,
process I.) and filter the solution.

III.—Immerse into the sulphuric solution a
cylinder of zinc or iron, and the copper will be
precipitated.

The analysis of carbonate of copper may
likewise be effected, and perhaps more easily,
in the following manner :

*Process* I.—Take one part of the ore, expose
it to a red heat in a crucible for about half an
hour.

II.—Let one part of this previously ignited ore be mixed with three times its weight of black flux, and one-fifth of charcoal powder, or resin; put the mixture into a crucible, cover it with a stratum of muriate of soda, and fuse it for about half an hour; a button of copper will then be found when the crucible is broken.

The ore called green carbonate of copper, and all its subspecies, may be examined in a like manner.

Dr. Fordyce has given the following general process for analysing all copper ores, with a view to ascertain the quantity of copper.

*Process* I.—Take 100 grains of the pulverised ore, digest it repeatedly in one ounce of nitro-muriatic acid, composed of equal parts of nitrous and muriatic acid, till all the copper is extricated, which may be known as directed already, page 147.

II.—The different solutions are then to be mingled, precipitated by the addition of carbonate of potash, and the precipitate collected on a filter.

III.—This precipitate is to be re-dissolved in a sufficient quantity of sulphuric acid, and the solution precipitated by a polished cylinder of zinc or iron.

### Species 2.—*Analysis of Arseniate Copper.*

In this ore and its subspecies copper exists, united to arsenic acid, without any other metallic substance; or at least very rarely it contains other bodies. The analysis may be conducted thus :

*Process* I.—Let one part of the ore, reduced to a fine powder, be repeatedly digested in nitric acid, until all the copper is extracted.

II.—To the obtained solution add carbonate of potash, in such a quantity only, as to remove the excess of acid, if any, or so as to obtain a neutral solution.

III.—To the fluid obtained add a solution of acetate or nitrate of lead, until no more cloudiness ensues.

IV.—Collect the white precipitate, which is arseniate of lead; wash and dry it : 100 grains contain 33.66 of arsenic acid.

V.—To ascertain the quantity of copper, add to the solution from which the arseniate of lead has been separated, sulphuric acid, and immerse in it a cylinder of iron. The copper will then be obtained in the metallic state. But as the copper does not exist in the ore in a metallic state, but in the oxidised state, therefore one-quarter of the weight of the obtained copper

must be added for oxigen, in stating the result of the analysis.

*Remark.*—The object of rendering the nitric solution neutral by an alkali (process II.) is merely to prevent the arseniate of lead formed in the next process from being dissolved in the excess of acid which may be present. Where iron is suspected, the solution, instead of being precipitated by a cylinder of iron (process V.) may be decomposed by ammonia, which in that case will dissolve the copper and precipitate the iron. To collect the copper, the ammoniacal solution may be neutralized by sulphuric acid, and then decomposed by a cylinder of iron. To prove that the white precipitate obtained in process IV. is arseniate of lead, it may be digested with sulphuric acid; the arsenic acid will be disengaged, and its characters manifested by the usual tests.

The following method was employed by Mr. Chenevix, for analysing the arseniates of copper of Cornwall : *

The ore being previously heated moderately, to expel and estimate the water it contained, was dissolved in dilute nitric acid, and then decom-

* Philos. Trans. 1801; p. 198.

posed by nitrate of lead. The solution being evaporated nearly to dryness, was mingled with alcohol, to promote the separation of the arseniate of lead, in case an excess of nitric acid should have dissolved a portion of it. The solution was then boiled with potash, and the brown oxid of copper (100 parts of which are equal to 80 of copper) separated by the filter.

All the remaining species of arseniates of copper may be examined in this manner.

Species 3.—*Analysis of Phosphate of Copper.*

*Process* I.—Let one part of the ore be repeatedly digested in dilute nitrc acid, till all the copper is extracted.

II.—To this solution add, gradually, carbonate of potash, to remove the excess of acid as accurately as possible, and then let fall into it a solution of sub-acetate of lead, till no further precipitate ensues. Wash the obtained precipitate, and dry it in a dull red heat; 138 parts of phosphate of lead indicate 30.95 of phosphoric acid.

III.—To ascertain the quantity of copper, suspend in the fluid left in the last process a cylinder of iron, the copper will become precipitated. But as the metal is contained in the ore

in the state of an oxid, 25 per cent. should be
added to the copper, to learn the quantity of oxid
of copper contained in the ore.*

### Species 4.—*Analysis of Muriate of Copper.*

*Process* I.—Digest one part of the ore repeat-
edly in three of dilute nitric acid, until all the
copper is removed, which may be known by
liquid ammonia not rendering the solution blue,
when added to it in excess. If iron is combined
with the ore a brown precipitate will ensue by
ammonia. (See page 153).

II.—To ascertain the quantity of muriatic
acid, add nitrate of silver, collect the precipitate,
and dry it at a dull red heat : 100 parts of the
precipitate are equal to 25 of muriatic acid.

III.—To ascertain the quantity of copper, im-
merse into the solution a cylinder of iron or zinc ;
the copper will be precipitated in a metallic state.
But as the copper exists in the ore, in the state
of an oxid, the weight of the copper ought to be
increased 25 per cent. which gives the quantity
of oxid of copper contained in the ore.

Such are the modes of analysing the ores of
copper.—On considering the different pro-

* Klaproth's Essays, Vol. I. p. 164.

ceedings, it will be found that the totallity of the examination of this class of ores is exceedingly simple, and may be shortly stated, thus :

The ore being repeatedly digested in nitric acid, till all the copper and other metals are extracted, and then precipitating from this solution the copper, either in the metallic form, or in the state of an oxid, from which the quantity of the metal may be inferred.

The presence of silver is detected by muriate of soda, or muriatic acid, which separates the silver in the state of a muriate (see page 112) and leaves the copper. The presence of lead may be detected by adding to the obtained solution sulphate of soda, which precipitates the lead, in the form of a sulphate of lead, 100 parts of which are equal to 30 of lead. The presence of antimony may be detected by decomposing the solution of the ore by an alkali, and then digesting the oxid with concentrated nitric acid, which dissolves the oxid of copper, and leaves the oxid of antimony. Iron is separated by supersaturating the solution with ammonia, which dissolves the copper, and leaves the oxid of iron; or else, by immersing a polished cylinder of iron or zinc, which separates the copper, and leaves the iron in solution. Tin, if any be present, may

be separated, by immersing into the solution a
cylinder of tin, which separates the copper only.
Arsenic is separated by acetate or nitrate of lead,
which separates the arsenic in the form of arse-
niate of lead, and leaves the copper, 100 parts of
which are equal to 33.66 of arsenic acid : to get
rid of the excess of lead, if any should remain,
let sulphate of soda be added, which will sepa-
rate this metal. If nickel should be present, it
is always in combination with iron : let liquid
ammonia be added to the solution, the copper
and the iron, and likewise the nickel, will be se-
parated. To separate the copper add muriatic
acid in excess, and then immerse into the so-
lution a cylinder of zinc or iron ; the copper
will then be precipitated, and the nickel left in
solution.*

* For a more circumstantial detail of the practical proceed-
ings, as well as for the modes of assaying and smelting ores of cop-
per, in the dry way, see the article Analysis of Copper Ores, in the
Author's System of Mineralogy and Mineralogical Chemistry.

## ORDER V.

### ORES OF LEAD.

There are a vast variety of lead ores, which are classed by mineralogists in the following manner:

*Division of Ores of Lead.*

Genus i.—*Sulphurets of Lead.*

Species 1.—Common Sulphuret of Lead, or Galena.

Subspecies 1.—Blue Sulphuret of Lead, or Blue Lead Ore.

Species 2.—Antimonial Sulphuret of Lead.

Genus ii.—*Salts of Lead.*

Species 1.—Carbonate of Lead.

Subspecies 1.—Black Carbonate of Lead.

Species 2.—Murio-Carbonate of Lead.

3.—Sulphate of Lead.

4.—Phosphate of Lead.

5.—Arseniate of Lead.

Subspecies 1.—Green Arseniate of Lead.

Species 6.—Molybdate of Lead.

7.—Chromate of Lead.

## Genus III.— *Oxids of Lead.*

Species 1.—Lead Ochre, or Earthy Lead Ore.
Subspecies 1.—Earthy Lead Ochre.
2.—Friable Lead Ochre.

### ANALYSIS OF ORES OF LEAD.

Species 1.—*Analysis of Common Sulphuret of Lead, or Galena.*

*Process* I.—Let one part of the ore, finely powdered, be digested in a flask, with six of nitric acid, diluted with three or four of water, and repeat this process for several times successively. During this process a great part of the sulphur contained in the ore will become separated, in the form of a light powder, floating on the top of the fluid, or subside to the bottom.

II.—Add to the obtained solution, previously evaporated to a small compass, muriatic acid, till no further cloudiness appears; suffer the mixture to stand undisturbed, till the precipitate is fairly deposited, then decant the fluid, separate the precipitate, and wash it repeatedly, by pouring alcohol over it.

III.—The obtained precipitate consists of muriate of lead, and muriate of silver, if the latter was contained in the ore.

P 2

IV.—In order to separate these two metals, digest the precipitate in liquid ammonia, for at least six hours ; the muriate of silver will be dissolved, and the muriate of lead left behind : or the muriate of lead may be separated by boiling the precipitate in 24 parts of water, which dissolves the muriate of lead, and leaves the muriate of silver : or the solution of the muriate of lead may still more easily be effected by digesting it in dilute nitric acid, which dissolves it readily, but does not touch the muriate of silver.

V.—Mingle the ammoniacal solution of silver with nitric acid, heat it for a few minutes, and precipitate the silver by a cylinder of copper.

VI.—To ascertain the quantity of lead obtained in process IV. mix the muriate of lead with half its weight of black flux ; introduce the mixture into a crucible, and expose it to a red heat for half an hour; the lead will be reduced to a metallic state. Or this process may be omitted, and the quantity of lead ascertained, by merely weighing the precipitate, dried at a dull red heat : 100 parts of it contain 75.2 of metallic lead.

The muriate of lead may also be reduced, by immersing into the aqueous solution of it, ob-

tained in experiment IV. a cylinder of iron, which
precipitates the lead in a metallic state.

VII.—To find the quantity of silver, proceed
as directed, analysis of silver ores.

To assay the ore for iron and copper, let the
solutions from which the lead and silver have
been separated, be mingled with liquid ammonia
in excess, a brown precipitate falls down,
which is oxid of iron. The presence of cop-
per may be known by the solution acquiring a
blue colour, by the addition of ammonia, it
may be separated by immersing into the fluid,
after having been neutralized by sulphuric acid,
a cylinder of zinc ; or by boiling it with potash
(See page 147).

All the different varieties of lead ores of this
class may be analysed in a like manner.

The proportion of silver in common sulphu-
ret of lead, or galena, varies greatly, from $\frac{1}{300}$th
part to $\frac{1}{25}$th. It is observable that the pre-
sence of this metal considerably impairs the
lustre of the ore, and that it is much more fre-
quently found in the octahedral than in the cu-
bical varieties of this mineral. The presence of
antimony may be suspected from its tendency to
a radiated texture.

P 3

Galena consists chiefly of lead and sulphur, in the proportion of about 100 of the former to 15 of the latter.

## Species 3.—*Analysis of Antimonial Sulphuret of Lead.*

This ore is a triple compound, containing lead, antimony, copper, with a minute portion of iron. It was thus analysed by Mr. Hatchett:

*Process* I.—Two hundred grains of the ore, finely pulverised, were put into a matrass, with two ounces of muriatic acid, heated, and nitric acid added to it, drop by drop, till the whole moderately effervesced. It was then gently heated for an hour, and a green solution was obtained, on the surface of which floated a quantity of sulphur, which was collected and digested with muriatic acid, and lastly washed and dried. It weighed 34 grains, and burned away in a red hot crucible, without residue.

II.—The nitric solution, together with the muriatic acid in which the sulphur had been digested, was evaporated, and mixed with six pints of boiling distilled water, which it rendered instantly milky, after which it was filtered.

The white precipitate obtained, when dried, weighed 63 grains, and was oxid of antimony.

III.—The liquor, with the washings, was found to deposit, on cooling, crystallized muriate of lead : it was therefore evaporated nearly to dryness, and a few drops of sulphuric acid added, to separate in the form of a sulphate of lead what little of that metal remained in solution.

IV.—The residue was then re-dissolved in boiling water, and decomposed by sulphate of soda. The sulphate of lead produced being added to that obtained before, process III. when dried it weighed 120.2 grains.

V.—The fluid, which was now bluish-green, acquired a deep blue colour by ammonia, and a small quantity of oxid of iron was separated, which when dried and heated with wax became magnetic, and weighed 2.4 grains.

VI.—The fluid was next evaporated nearly to dryness, boiled with a strong solution of potash till nearly dry, and on washing it with water, the oxid of copper obtained weighed 32 grains.

In this analysis the metals are estimated as in their metallic state, this being the form in which they exist in the sulphurets, and hence, for the

63 grains of oxid of antimony, 48.46 of metallic antimony are to be put down, and for 120.2 of ulphate of lead, Mr. Hatchett estimates 85.24 of metallic lead, which is in the proportion of 70.9 in 100.

### ANALYSIS OF SALTS OF LEAD.

Species 1.—*Analysis of Carbonate of Lead.*

This ore may be analysed in the following manner:

*Process* I.—Let 100 grains of the ore be dissolved in a weighed quantity of dilute nitric acid, and note down the loss of weight, which gives the quantity or carbonic acid.

II.—Into the obtained solution immerse a cylinder of zinc, which precipitates the lead in a metallic state. The remaining fluid may be examined for iron and copper, as stated before.

A specimen of carbonate of lead was analysed by Klaproth in the following way:

One hundred grains of finely pulverized ore were dissolved in 200 grains of nitric acid, diluted with 300 of water, and the loss of weight by the effervescence noted, which amounted to 16 grains: it was carbonic acid. The nitric solution was then diluted, and a cylinder of zinc

immersed in it, which precipitated the lead in the metallic state. When dried it weighed 77 grains, which are equal to 82 of oxid, as it is in this state that the lead exists in the ore. This proportion, however, would give an increase of only 6.5 of oxigen upon 100 of lead.

The black carbonate of lead may be analysed in a like manner.

### Species 3.—*Murio-Carbonate of Lead.*

This rare variety of lead ore has been analysed by Klaproth in the following manner :

*Process* I.—Fifty grains of the ore were triturated with 150 of carbonate of potash, and heated in a platina crucible to a moderate redness, then softened with water, lixiviated, and filtered : an oxid of lead was left behind.

II.—The obtained solution was next supersaturated with nitric acid, and precipitated with nitrate of silver. The muriate of silver obtained weighed 27 grains.

III.—Another quantity of the ore of 100 grains was powdered, and nitric acid affused, which produced an effervescence of carbonic acid. This solution gave, with nitrate of silver, 55 grains of muriate of silver, corres-

ponding very closely in proportion with the former experiment, the acid of which amounted to 8.5 grains.

IV.—The lead was then precipitated by potash, and the oxid thus procured weighed, after thorough drying, $85\frac{1}{2}$ grains, which is the state of oxidisement in which it is supposed to exist in the ore. In this case, therefore, 85.5 grains of oxid of lead were combined with only 8.5 of muriatic acid, which is far short of the saturating quantity, since, in the artificial crystallized muriate of lead, the proportion of acid amounts to 13 or 14 per cent.. This deficient saturation therefore allows the presence of carbonic acid, which amounts to six grains, and completes the saturation of the oxid.

A similar ore was analysed by Mr. Chenevix, nearly in the same way, and with the same result.

*Process* I.—The ore was first dissolved in nitric acid, and the quantity of carbonic acid, amounting to six grains, estimated by the loss after effervescence.

II.—The solution was then neutralized by ammonia, and assayed by different tests. As nitrate of lime gave no precipitate, the solution could not contain either arsenic, molybdic, or phos-

phoric acids; and as nitrate of barytes gave
none, the absence of sulphuric acid was proved.

III.—Nitrate of silver was then added, and
a copious precipitate ensued, the muriate of
silver weighed, after drying, 48 grains, which
Mr. C. estimates as equivalent to eight of muri-
atic acid. The composition of the ore is thus
stated: six grains of carbonic acid saturate 34
of oxid of lead, and eight of muriatic acid satu-
rate 51 of oxid of lead, and the acids may be
supposed to be in the state of perfect saturation;
consequently, the ore is composed of 59 parts of
muriate of lead, and 40 of carbonate of lead, or
of 14 of acid and 85 of oxid.

## Species 4.—*Analysis of Sulphate of Lead.*

The Anglesea sulphate of lead was thus ana-
lysed by Klaproth:

*Process* I.—One hundred grains were first ig-
nited moderately, and lost two grains, which
were water of crystallization. The remainder was
mixed with 400 grains of carbonate of potash,
and kept for some time in a red heat, in a pla-
tina crucible, it yielded a reddish-yellow har-
dened mass.

II.—This, digested with water, was all dis-
solved, except the oxid of lead separated in the

previous process, amounting to 72 grains, after strong drying.

III.—This oxid was re-dissolved in nitric acid, and deposited thereby one grain of oxid of iron.

IV.—The solution was then decomposed by zinc, and yielded 66.5 grains of metallic lead.

V.—The alkaline fluid formed by the washing of the contents of the crucible, after ignition, was saturated with nitric acid, and acetate of barytes added as long as any sulphate of barytes became precipitated. This amounted to 73 grains, equal to 24.8 of concrete sulphuric acid, on the estimation that 100 parts (after ignition) contain 34 of acid. The iron in this ore appears merely casual.

## Species 5. — *Analysis of Green Phosphate of Lead.*

In this ore lead exists in combination with phosphoric and muriatic acids. The green phosphate was thus analysed by Klaproth, after some imperfect attempts of reduction in the dry way, in the following manner:

*Process* I.—One hundred grains of the ore were dissolved in hot nitric acid, leaving no residue; and nitrate of silver being added gave a

precipitate of 11 grains of muriate of silver;
the muriatic acid of which amounted to 1.7
grains.

II—Sulphuric acid was then added to the
warmed solution, by which sulphate of lead was
precipitated, weighing after ignition 106 grains,
equal to 73.61 of metallic lead, or 78.4 of the
oxid.

III.—The fluid was freed from sulphuric acid
by nitrate of barytes, and was then nearly satu-
rated with ammonia, and acetite of lead ad-
ded. The phosphoric acid in the solution was
thus precipitated in the form of phosphate
of lead, weighing, after ignition, 82 grains,
of which the mere acid amounts to 18.37
grains.

IV.—The rest of the solution was mixed with
a little muriatic acid, concentrated by evapo-
ration, and then mingled with alcohol, to re-
dissolve the muriate of iron formed, if any ; from
which, by the addition of prussiate of potash,
there was obtained an extremely small quantity of
blue precipitate, indicating no more than about
one part of a grain of oxid of iron.

Species 6.—*Analysis of Arseniate of Lead.*

This lead ore is a compound of lead, arsenic, and iron. It was thus examined by Vauquelin:

*Process* I.—One hundred grains of the ore, being roasted in a scorifying test for half an hour, with a little suet added occasionally, to facilitate the reduction and volatilization of the arsenic, lost 38 grains; it acquired a black colour and became magnetic.

II.—Upon the roasted ore muriatic acid was made to act by heat, till no further action took place.

III.—The muriatic solution being evaporated to dryness, re-dissolved in water, and decomposed by sulphate of soda, the precipitate obtained weighed 25 grains, equal to 20.2 of lead, or 22 of oxid of lead.

IV.—The remaining fluid, being mingled with ammonia in excess, afforded 39 grains of oxid of iron.

The rest of the species of arseniate of lead may be analysed in a like manner.

With regard to the analysis of the molybdate of lead, the reader is referred to the article molybdate, and for the chromate of lead to chrome.

## ANALYSIS OF OXIDS OF LEAD, OR LEAD OCHRES.

All these ores may be analysed by dissolving them in nitric acid, and precipitating the lead, as directed before.

# ORDER VI.

### ORES OF TIN.

No metal exhibits a smaller variety of ores than tin; it has hitherto been met with in two states only, and hence the following

*Division of Ores of Tin.*

GENUS I.—*Oxids of Tin.*

Species 1.—Native Oxid of Tin, or Tin Stone.
2.—Wood Tin.

GENUS II.—*Sulphuret of Tin.*

Species 1.—Sulphuret of Tin, or Tin Pyrites.

### ANALYSIS OF ORES OF TIN.

Species 1.—*Analysis of Native Oxid of Tin.*

*Process* I.—Take one part of the ore, freed carefully from all its matrix, reduce it to an impalpable powder, triturate it with four times its weight of potash, moistened with water, and lastly, boil the mass in a silver vessel in eight

parts of water, evaporate the whole to dryness, and moderately ignite it for at least half an hour.

II.—Pour water upon the mass, boil the mixture for about a quarter of an hour, and filter the fluid.

III.—Take the residue left on the filter, if any, mix it again with a like quantity of potash, dissolved in a sufficient quantity of water, evaporate to dryness, and proceed as above.

IV.—Let the solutions thus obtained be mingled, and add to it muriatic acid till no more precipitate falls down, adding the acid rather in excess; suffer the mixture to stand undisturbed till the precipitate is subsided, in order to collect it on a filter.

V.—Dissolve this precipitate in muriatic acid, in excess, precipitate it again by the addition of carbonate of soda, collect the precipitate on a filter, wash it by pouring water over it repeatedly, and suffer it to dry.

VI.—Let the precipitate be again dissolved in muriatic acid, assisted by a gentle heat (the insoluble part, if any, consists of silex), dilute the solution with two or three parts of water, immerse into it a cylinder of zinc: leave the

whole undisturbed for some days, and all the tin that was contained in the ore will now be deposited round the cylinder of zinc, in a metallic state. It may be formed into a button, by melting it in a crucible, taking care to cover it with charcoal powder.

## Species 1.—*Analysis of Sulphuret of Tin.*

In this ore tin exists, mineralized by sulphur, and frequently associated with copper ; its analysis may be accomplished in the following manner :

*Process* I.—Let one part of finely pulverised ore be repeatedly digested in six of nitro-muriatic acid, composed of two parts of muriatic acid, and one of nitric acid, till it dissolves no more, and decant the fluid.

II.—Add to this solution carbonate of potash till no further precipitate ensues, collect the precipitate on a filter.

III.—Re-dissolve this precipitate in muriatic acid, diluted with three or four parts of water, and suspend in this solution a cylinder of tin whose weight is known. If copper was contained in the ore it will be precipitated in a metallic state on the tin cylinder, but in order

to be certain that it is not contaminated with tin, let the precipitated metal be re-dissolved by heat, in concentrated nitric acid; if a white powder remains it is a portion of oxid of tin.

IV.—As in the foregoing process, the tin employed for precipitating the copper is acted upon by the muriatic acid, immerse into the solution from which the copper has been separated a cylinder of zinc, the whole of the tin will be again precipitated on the cylinder of zinc; let it be dried and its weight ascertained, when melted into a mass. From this quantity of tin subtract now that portion which proceeds from the cylinder of tin employed for precipitating the copper, the remainder will give the true quantity of metal contained in the ore.

V.—Having thus far proceeded, expose the insoluble residue left in process I. to a low red heat in a crucible, pour water into it, filter the fluid, and ascertain the quantity of sulphur, as stated in page 117, what remains will be the matrix of the ore. It consists in general of alumine and silex.

# ORDER VII.

### IRON ORES.

There are a vast variety of ores of iron scattered over the surface of the earth, which are divided by mineralogists in the following manner:

## Division of Ores of Iron

### GENUS I.—*Alloys of Iron.*

Species 1—Native Iron.

### GENUS II.—*Sulphuret of Iron.*

Species 1.—Common Sulphuret of Iron, or Unmagnetical Iron Pyrites.

Subspecies 1.—Common Iron Pyrites.
         2.—Radiated Pyrites.
         3.—Capillary Pyrites.
         4.—Cellular Pyrites.
         5.—Hepatic Pyrites.

Species 2.—Magnetical Pyrites.

### GENUS III.—*Oxids of Iron.*

Species 1.—Magnetic Oxid of Iron, or Common Magnetic Iron Ore.

Subspecies 1.—Magnetic Iron Sand.

Species 2.—Specular Iron Ore.
    Subspecies 1.— Common Specular Iron
                Ore.
          2.—Micaceous Iron Ore.

Species 3.—Red Iron Stone.
    Subspecies 1.—Red Scaly Iron Ore.
          2.—Red Ochre.
          3.—Compact Red Iron Stone.
          4.—Red Hematite.

Species 4.—Black Iron Ore.
    Subspecies 1.—Compact Black Iron Ore.
          2.—Black Hematite.

Species 5.—Brown Iron Ore.
    Subspecies 1.—Compact Brown Iron Stone.
          2.—Fibrous Brown Iron Stone.
          3.—Scaly Brown Iron Ore.
          4.—Brown Hematite.

Species 6.—Sparry or Spathose Iron Ore.

Species 7.—Argillaceous Iron Ore.
    Subspecies 1.—Common Argillaceous Iron
                Ore.

Subspecies 2.—Graphic Red Argillaceous
Iron Ore, Reddle, or Red
Chalk.

3.—Columnar Argillaceous Iron
Ore.

4.—Lenticular Argillaceous Iron
Ore.

5.—Jaspery Argillaceous Iron
Ore.

6.—Nodular or Reniform Iron
Ore.

7.—Pisiform Iron Ore.

Species 8.—Bog or Morassy Iron Ore.
Subspecies 1.—Morassy Iron Ore.

2.—Swampy, or Lowland Iron
Ore.

3.—Meadow Iron Ore.

GENUS IV.—*Salts of Iron.*

Species 1.—Arseniate of Iron.

2.—Carbonate of Iron.

3.—Phosphate of Iron.

4.—Phosphate of Iron and Manganese.

5.—Prussiate of Iron.

6:—Arseniate of Iron and Copper,

Species 7.—Green Iron Earth.
    8.—Sulphate of Iron.

### ANALYSIS OF ALLOYS OF IRON.

## Species 1.—*Analysis of Native Iron.*

Although the mineral called native iron is exceedingly rare, it is nevertheless certain that it has been found in different parts of the world. A specimen, weighing about four pounds, was found in the mine of Hackenberg. The masses of native iron observed by Pallas in Siberia, by Rubin de Cellis in South America, &c. are now considered as masses of native iron and nickel which have descended from the atmosphere.* The presence of nickel distinguishes them from the true native iron, which is destitute of this metal.

A specimen of native iron, from the mine Johannes, near Kamsdorff in Saxony, analysed by Klaproth, consisted of iron, lead, and copper.— The analysis may be performed in the following manner:

*Process* I.—Endeavour to effect a solution of the ore by the repeated application of dilute nitric acid, assisted by a gentle heat.

---

* Cramer Philos. Mag. XIII. 32.

II.—Into the obtained solution let fall sul-
phate of soda, till no farther cloudiness ensues :
100 parts of the sulphate of lead are equal, ac-
cording to Klaproth, to 69.44 metallic lead, or,
according to Hatchett, to 70.9.

III.—To the fluid from which the lead has
been separated, add a solution of soda in excess.
Heat the mixture, and separate the precipitate,
which consists of oxids of iron and copper.

IV.—To separate the copper, digest the pre-
cipitate repeatedly in liquid ammonia, as long as
this fluid acquires a blue colour. The copper
will thus be removed, and the oxid of iron left
behind.

V.—To obtain the copper from the ammonia-
cal solution, supersaturate it slightly with sul-
phuric acid, and immerse in it a cylinder of iron,
which will separate the copper.

VI.—To ascertain the quantity of iron, let
the oxid of that metal obtained in process IV.
be heated with a little wax, in a covered crucible,
in order to become reduced to the state of a mag-
netic oxid, 100 parts of which indicate 73 of
metallic iron. Or it may be mixed with a few
grains of hyper oxi-muriate of potash, in con-
tact with a little nitric acid, evaporated to dry-
ness, and lastly heated for a few minutes in a

crucible : it will thus be changed to the red
oxid of iron; 100 parts of which are equal to
52 of iron.

### ANALYSIS OF SULPHURETS OF IRON.

Species 1.—*Analysis of Common Sulphuret of
Iron, or Unmagnetical Pyrites.*

None of the ores of iron belonging to this
species can be wrought to extract the metal;
they are more frequently employed for obtaining
from them sulphate of iron. They may be ana-
lysed in the following manner :

*Process* I.—Put into a florence flask one part of
the ore, reduced to a fine powder ; pour over it
eight of nitric aid ; digest the mixture till no
farther action takes place ; and lastly, evaporate
the whole almost to dryness.

II.—Pour three or four parts of water on the
obtained mass, separate the fluid by filtration,
and wash the residue in a small portion of
water, which may be added to the filtered so-
lution.

III.—Upon the insoluble residue left in pro-
cess I. pour again a like portion of nitric acid,
digest and evaporate it, and repeat this operation

successively, until the nitric solution, when di-
luted with water, does not become turbid, by
dropping into it nitrate of barytes; and, lastly,
separate the insoluble residue.

IV.—Let the solutions, together with the wa-
ter employed for washing the insoluble residue,
be mingled together; add to it carbonate of
potash or soda in excess, and separate the preci-
pitate by the filter, if any.

V.—To the fluid left in the last process add
nitric acid, so as to neutralize the excess of alkali
added before; or better add nitric acid rather in
excess, and then drop into it nitrate of barytes:
the precipitate obtained is sulphate of barytes,
of which 100 are equal to 14.5 sulphur.

VI.—The insoluble residue left in experiment
III. together with the precipitate obtained in
process IV. should next be mixed with about
twice its weight of soda or potash, fused for
about 20 minutes in a silver crucible, dissolved in
muriatic acid, and evaporated nearly to dryness.

VII.—The dry mass must be softened by
water, digested in that fluid, and the insoluble
part which is silex, separated by the filter.

VIII.—If to the muriatic solution liquid am-
monia be added in excess, the oxid of iron, and
alumine, if any was present, will be precipitated,

and lime, if it should be present, will be left in solution.

IX.—To separate the oxid of iron from the alumine, let the obtained precipitate be digested in concentrated nitric acid, which will dissolve the alumine, and leave the oxid of iron; 100 parts of which, after having been heated, are equal to 52 of iron.

X.—If lime was present, it may be detected by adding to the solution from which the oxid of iron and alumine are separated (process VIII.) a solution of carbonate of potash ; the precipitate which falls down is carbonate of lime, which may be decomposed by exposure to a red heat.

The ores called radiated, capillary, cellular, hepatic pyrites may be examined in a like manner.

### ANALYSIS OF OXIDS OF IRON.

Species 1.—*Analysis of Magnetic Iron Ore, or Common Magnetic Oxid of Iron.*

This ore contains, besides oxid of iron, a small portion of silex and alumine. It is not only attracted by the magnet, but it possesses itself

R 2

polarity; hence it attracts iron filing. It affords cast iron of but indifferent quality, but very excellent bar iron.

*Process* I.—Take one part of the ore levigated as fine as possible, add to it six parts of potash or soda, and 18 of water, boil the mixture in a silver bason or crucible, for at least two hours, taking care to supply the water as it evaporates; lastly, evaporate the mixture to dryness; and raise the heat, so as just to fuse the whole, and suffer it to remain fused, at a dull red heat, for about half an hour.

II.—Soften the fused alkaline mass with water, transfer it into a flask, pour over it muriatic acid, previously diluted with two of water, digest it for a few minutes, and then evaporate it to dryness.

III.—Upon the dry mass obtained pour about 10 parts of boiling water, and separate the insoluble part, which is silex, by the filter.

IV.—To the fluid from which the silex has been separated, after having been previously concentrated, add potash or soda, in excess, boil the whole for a few minutes, dilute it with water, suffer the precipitate to subside, or separate it by the filter, dry and wash it. The precipitate thus obtained may be mixed with a little

nitric acid, and kept for a few minutes in an open crucible, at a dull red heat, it will become changed into the perfect red oxid of iron, 100 parts of it indicate 52 of iron.

V.—If to the alkaline fluid from which this oxid has been separated nitric acid be added just sufficient to render the solution neutral, the alumine may be separated, by adding to it benzoate of ammonia till no farther cloudiness ensues. This precipitate, after having been heated to redness for half an hour, gives the quantity of alumine that was present in the ore.

Magnetic iron sand, specular iron ore, micaceous iron ore, red iron stone, and all its subspecies, may be analysed in a like manner.

### Species 4.—*Analysis of Black Iron Ore.*

This ore differs from the latter, by containing a small portion of manganese.

*Process* I.—Treat the ore with potash or soda, as directed in the opposite page, process I. separate the silex according to process II. and III. decompose the muriatic solution as stated process IV. and collect the precipitate. It consists of oxid of iron and oxid of manganese, which may be separated best and most expeditiously in the following manner:

II.—Transfer the precipitate into a florence flask, and effect a solution of it, by means of muriatic acid, assisted by a gentle heat.

III.—To the obtained solution add succinate of soda, whilst boiling hot, till no farther cloudiness ensues. The precipitate thus obtained is succinate of iron : 100 parts of it, after having been heated with a little wax, in a low red heat, are equal to 70 of metalic iron.

IV.—Or the two metals may be separated by dissolving the compound precipitate of oxid of iron, and oxid of manganese, in muriatic acid, by a gentle heat, and adding to it when boiling hot a solution of soda, in small quantities at a time, till the fluid becomes colourless, or till the precipitate that is thrown down by each addition of soda begins to assume a white colour. Collect this precipitate, and heat it with nitric acid : it gives the quantity of iron as stated, page 183, process IX.

V.—To the remaining fluid now add soda till no further precipitate ensues : the precipitate obtained is oxid of manganese.

The ores called black hematite, brown iron ore, and all its subspecies, may be analysed in a like manner.

Species 6.—*Analysis of Sparry or Spathose
Iron Ore.*

The composition of this ore is far more com-
plicated than any of the former. It usually con-
tains besides oxid of iron, silex, and alumine, a
considerable portion of oxid of manganese, and
carbonate of lime, and sometimes, also, a small
portion of carbonate of magnesia and barytes.

The iron obtained from this ore is particularly
valuable, as it may be converted into fine steel
immediately from the state of cast iron. The
bar iron which it yields possesses both hardness
and tenacity in a high degree. The ore may be
analysed in the following manner:

*Process* I.—Take one part of the ore, finely
levigated, put it into a bottle furnished with a
spiral glass tube, and pour over it twice its weight
of nitro-muriatic acid, and ascertain the quan-
tity of carbonic acid by the loss of weight it
sustains. (See apparatus for ascertaining the
quantity of carbonic acid, in the description of
the plates.)

II.—Upon the ore thus freed from carbonic
acid pour four times its weight of muriatic acid,
and digest it in a flask with like portions of
muriatic acid, till no further action ensues, or till

tincture of galls does not change the acid that has acted upon it, and when rendered neutral by an alcali, blue or black.

III.—Mingle the obtained solutions, and having concentrated the whole by evaporation, decompose it whilst boiling hot, by soda, adding this alkali rather in excess, and boil the whole for about a quarter of an hour. The alumine will by this means become dissolved in the excess of the alkali. Separate the insoluble residue by the filter.

IV.—To separate from the insoluble residue of the last obtained process, the lime, barytes, and magnesia it may contain, let it be digested in dilute nitric acid. The former earths will become dissolved, and the oxid of iron and manganese will be left untouched, which may be separated by filtration.

V.—Into the solution of process IV. previously diluted with 20 parts of water, let fall sulphuric acid, till no further cloudiness ensues ; the barytes which was present will be separated in the form of an insoluble white powder, being sulphate of barytes, and the other earths which were present in the solution will remain undisturbed.

VI.—To separate these earths, again concentrate the fluid from which the barytes has been

removed, and decompose it by the addition of sub-carbonate of potash. The obtained precipitate consists of carbonate of lime and carbonate of magnesia.

VII.—To separate these earths, cover them with sulphuric acid, and evaporate the mixture to dryness, till no more fumes are visible; and lastly pour over it a small portion of water, which will dissolve the sulphate of magnesia and leave the sulphate of lime.

VIII.—To the obtained solution of sulphate of magnesia add sub-carbonate of potash. The precipitate obtained is sub-carbonate of magnesia, which, after having been freed from its carbonic acid, by exposure to a red heat, gives the quantity of magnesia that was present in the ore.

IX.—To ascertain the quantity of lime, take the sulphate of lime obtained in process VII. boil it with three times its weight of sub-carbonate of potash, and ten of water, repeatedly, until it is found to be completely soluble in nitric acid; evaporate the nitric solution to dryness, and decompose it at a red heat. The lime that was present will thus become evident.

X.—To separate the oxids of iron and manganese obtained in process IV. let the mass be di-

gested at a gentle heat with dilute nitric acid, and a small piece of sugar; the manganese will be dissolved, and the oxid of iron will be left behind; from which the quantity of iron may be inferred, according to the rules laid down, page 186.

XI.—To ascertain the quantity of manganese, add to the nitric solution from which the iron has been separated carbonate of soda, till no farther cloudiness ensues. This precipitate, after being washed and dried at a low red heat, is carbonate of manganese, 100 parts of it are equal to 55 of metallic manganese.

## Species 7.—*Analysis of Common Argillaceous Iron Ore.*

This ore is chiefly composed of oxid of iron, alumine, and a small portion of silex, and hence its analysis may be effected according to the rules already pointed out, for separating these bodies: it usually yields from 30 to 40 per cent. of iron.

The ore called Reddle or red chalk, which is chiefly used for what are commonly called red lead pencils, is, we believe, never smelted for iron, it differs from the former, by containing the iron in the state of a red oxid.

The other subspecies of argillaceous iron ores sometimes contain, besides the ingredients already stated, variable portions of oxid of manganese, phosphate of iron, and silex; they may therefore be analysed thus:

*Process* I.—Digest one part of the ore repeatedly in nitric acid, until all the iron is extracted by the acid.

II.—Evaporate the nitric solution almost to dryness, and suffer to digest the residue in a closed phial, with cold water. The phosphate of iron, if any was present, will become precipitated.

III.—Fuse the insoluble residue left in experiment I. with four times its weight of soda for one hour; dissolve the mass in water, filter it, and separate the silex from the alkaline solution, by the admixture of muriatic acid; collect and dry it.

IV.—To the fluid from which the silex has been obtained, add the solution from which the phosphate of iron has been separated, experiment II. supersaturate the whole with soda, and boil the mixture for about half an hour. The alumine, if any, will be dissolved in the excess of soda added, and the metallic oxids, together with the lime, will remain unacted on: separate the insoluble part by the filter.

V.—Digest the mass obtained in process IV. in concentrated nitric acid; evaporate the solution to dryness. Repeat this operation for several times successively, and lastly again digest it in dilute nitric acid, and separate the fluid by the filter.

VI.—Decompose the obtained nitric solution by carbonate of potash, and expose the precipitate to a red heat for half an hour: the lime which was present in the ore will thus be obtained.

VII.—To separate the metallic oxids, namely, the oxid of iron and oxid of manganese, left undissolved in process V. proceed as directed before.

### ANALYSIS OF SALTS OF IRON.

Species 1.—*Analysis of Arseniate of Iron.*

In this ore iron is united to arsenic acid; sometimes it contains likewise a small quantity of copper. The mode of analysis recommended by Chenevix succeeds best.*

*Process* I.—Expose a weighed quantity of the ore for about ten minutes, to a low red heat: the

* Philos. Trans. 1801; p. 220.

loss gives the quantity of water of crystallization
that was present.

II.—Let the ore next be boiled in a silver
basin, with three of potash and six of water, to
dryness ; re-dissolve the mass in water, and se-
parate the insoluble part by the filter.

III.—To the obtained alkaline solution add
nitric acid sufficient to render it neutral, and
then drop into it a solution of nitrate of lead
till no more precipitate ensues ; collect the pre-
cipitate and dry it : 100 parts of it are equal to
33 of arsenic acid.

IV.—To learn the quantity of iron, take the
residue which was insoluble in potash (process
II.) and digest it repeatedly in muriatic acid ;
the metallic matter will be removed, and what
is left behind consists of silex.

V.—To the muriatic solution add liquid am-
monia in excess, the oxid of iron becomes
precipitated, and the oxid of copper remains
in the supernatant ammoniacal solution : 100
parts of the oxid of iron, after having been heated
in a crucible for a few minutes with a little
nitric acid, is equal to 52 of iron. The quan-
tity of copper may be learned by boiling down
the ammoniacal solution to dryness ; 100 parts

s

of the oxid of copper thus obtained, after being ignited, are equal to 80 of copper.

For the modern processes of smelting iron ores in the large way, the reader is referred to the article iron, in the author's System of Mineralogy and Mineralogical Chemistry.

## ORDER VIII.

### ORES OF ZINC.

*Division of Ores of Zinc.*

The ores containing zinc are the following :

GENUS I.—*Sulphurets of Zinc, or Blende.*

Species 1. —Yellow Sulphuret of Zinc, or Yellow Blende.

     2.—Brown Sulphuret of Zinc, or Brown Blende.

    Subspecies 1.—Foliated Brown Blende.

        2.— Fibrous Brown Blende.

Species 3.—Black Sulphuret of Zinc, or Black Blende.

GENUS II.—*Native Oxids of Zinc.*

Species 1.—Silicated Oxid of Zinc, or Electric Calamine.

GENUS III.— *Native Salts of Zinc, or Common Calamine.*

Species 1.—Common Calamine, or Carbonate of Zinc.

Subspecies 1.—Crystallized Calamine.
                    2.—Compact Calamine.
Species 2.—Hydrous Carbonate of Zinc, or
                    Earthy Calamine.
                    3.—Sulphate of Zinc.

### ANALYSIS OF SULPHURET OF ZINC.

Species 1.—*Analysis of Yellow Sulphuret of
          Zinc, or Yellow Blende.*

This ore usually contains, besides zinc and
sulphur, also iron, lead, copper, arsenic, alu-
mine, silex, and sometimes water.—Let us sup-
pose they should all be present.—

*Process* I.—To ascertain the quantity of water,
introduce a given weight of the ore into a retort,
to which a receiver has been joined, and heat the
vessel dull red hot for about ten minutes, to col-
lect the water in the usual manner in the receiver.

II.—To learn the quantity of sulphur, take a
fresh portion of the ore, digest it repeatedly in
very dilute nitric acid, till no farther action takes
place, collect the insoluble residue, weigh it,
and ignite it, the sulphur will burn off, and its
amount may be estimated by the loss of weight,
with tolerable accuracy.

III.—Upon the mass left in the preceding process pour nitro-muriatic acid, and digest it till the insoluble part becomes white; it is then pure silex.

IV.—To the nitric solution (process II.) add a few drops of a solution of sulphate of soda, from time to time, till no farther precipitate ensues, and when the whole is brought nearly to dryness cover it with very dilute muriatic acid, which will dissolve every thing and leave the sulphate of lead.

V.—Mingle the nitro-muriatic solutions (process III. and IV.) decompose the whole by carbonate of soda, and collect the precipitate.

VI.—Pour over the precipitate liquid ammonia, and suffer it to stand for a few days. The oxid of zinc and oxid of copper will become dissolved in the ammonia.

VII.—To separate the two oxids, mingle the ammoniacal solution with muriatic acid in excess, and boil it, adding a solution of caustic soda, till no more precipitate ensues : the obtained precipitate is brown oxid of copper; 100 parts are equal to 80 of copper.

VIII.—To obtain the oxid of zinc, saturate the alkaline soluton, from which the copper has been separated, with muriatic acid, and then

decompose it by carbonate of soda. The obtained precipitate, after being ignited, is oxid of zinc. To learn the quantity of metallic zinc it is capable of yielding proceed as directed, p. 201, process X.

IX.—The residue left in process VI. may be abstracted repeatedly with nitric acid, and lastly digested in a solution of soda. What remains is oxid of iron, perhaps slightly contaminated with a minute portion of arsenic.

X.—Into the alkaline solution thus obtained let fall nitric acid sufficient to neutralize it, and then decompose it by the admixture of nitrate of lead. The precipitate is arseniate of lead; 100 parts are equal to 33 of lead.

XI.—The fluid from which the arseniate of lead has been separated, may be assayed by means of sulphate of soda, to free it from nitrate of lead, if any should be present, and then add carbonate of ammonia. The precipitate produced, after being washed and ignited, is alumine.

The rest of the species of sulphurets of zinc may be analysed in a like manner.

## ANALYSIS OF NATIVE OXIDS OF ZINC.

Species 1.—*Analysis of the Electric Calamine,
or Silicated Oxid of Zinc.*

In this ore oxid of zinc exists, combined with
a considerable portion of silex and water.

*Process* I.—Digest the finely pulverized ore
repeatedly in dilute nitric acid, evaporate the so-
lution to dryness.

II.—Pour water on the mass, and separate
the insoluble part, which is silex, by the filter.

III.—If the silex is not perfectly white, let it
be digested in muriatic acid, to free it from
iron.

IV.—Decompose this muriatic solution by
sub-carbonate of potash, and transfer the preci-
pitate into the nitric solution obtained process II.
and conduct the remaining operations as stated
in the opposite pages.

*Remark.*— To determine the quantity of
water, take a weighed quantity of the ore,
heat it moderately for half an hour ; note down
the loss of weight, and transfer the residue into
muriatic acid. If it emits any gas, let the loss
of the weight be noted ; then add together the
losses by ignition and solution, and deduct from
the sum total the known weight of the gas (viz.

carbonic acid,) the remainder gives the weight of the water.

Species 1.—*Analysis of Carbonate of Zinc, or Common Calamine.*

This ore usually contains, besides oxid of zinc, and water, carbonates of lead, iron, and lime.

*Process* I.—Digest one part of the finely pulverised ore in the cold, with six of nitric acid, in a bottle furnished with a capillary tube.[*] The loss of weight after digestion gives the quantity of carbonic acid with tolerable accuracy.

II.—Heat the mixture, and keep it gently boiling for about half an hour, and filter it.

III.—Neutralize the obtained solution by means of soda, and evaporate it, gradually adding, from time to time, a few drops of sulphate of soda, till no further cloudiness takes place, and lastly evaporate it to dryness.

IV.—Digest the dry mass first in alcohol, and next wash it in a small quantity of cold water, to free it from every saline combination, except sulphate of lime and sulphate of lead.

[*] See description of the plates : apparatus for ascertaining the quantity of carbonic acid of minerals.

V.—To separate these two salts digest the re-
sidue in very dilute sulphuric acid, which will
dissolve the sulphate of lime, and leave the sul-
phate of lead, and filter the fluid.

VI.—Neutralize the solution by soda, and
evaporate it nearly to dryness, and then add to
it, when still hot, alcohol. The crystalline pre-
cipitate obtained consists chiefly of sulphate
of lime, with a small portion of sulphate of
soda; the latter may be removed by washing
the precipitate in small portions of water.

VII.—Evaporate the alcoholic solution (pro-
cess IV.) to dryness, and digest it in a concen-
trated solution of potash, the oxid of zinc will
become dissolved in the alkali, and the oxid of
iron left behind.

VIII.—To ascertain the quantity of zinc,
neutralize the alkaline solution obtained in pro-
cess VII. by muriatic acid, and add the acid a
little in excess.

IX.—Decompose the obtained muriatic solu-
tion by super-carbonate of potash, and collect the
precipitate on a filter.

X.—Dissolve the carbonate of zinc thus ob-
tained in dilute sulphuric acid, evaporate the
solution to dryness ignite the sulphate of zinc

in a platina crucible, and ascertain its weight : 100 parts of it are equal to 50 of oxid of zinc; and 50 parts of oxid of zinc are equal to 40 of metallic zinc. The quantity of water the ore contains may be learnt as stated page 199.

The rest of the ores belonging to this genus may be analysed in like manner.

# ORDER IX.

## ORES OF MERCURY.

*Division of Ores of Quicksilver.*

GENUS I.—*Native Alloys of Mercury.*

Species 1.—Native Mercury.
      2.—Native Amalgam.

GENUS II.—*Sulphurets of Mercury, or Cin-*
            *nabar.*

Species 1.—Compact, Common, or Dark Red
          Cinnabar.
      2.—Fibrous or Bright Red Cinnabar.
      3.—Liver-Coloured, or Hepatic Quick-
          silver Ore.
     Subspecies 1.—Compact Hepatic Quick-
              silver Ore.
          2.—Slaty Hepatic Quicksilver
              Ore.
          3.—Bituminous Hepatic Quick-
              silver Ore.

**Genus iii.**—*Native Salts of Mercury.*

Species 1.—Native Muriate, or Horn Quick-
silver Ore.

2.—Hydro-sulphuret, or Fœtid Hepatic
Quicksilver Ore.

### ANALYSIS OF ORES OF MERCURY.

Species 2.——*Analysis of Native Amalgam.*

The constituent parts of this ore are silver and
mercury.

*Process* I.—Introduce the amalgam into a
glass tube, about half an inch in the bore, and
eight or ten inches long, and place it in a sand
bath, or crucible filled with sand.

II.—Apply heat, and increase it gradually,
till the bottom of the tube is of a dull red heat.
The quicksilver will thus be volatilized, and be-
come sublimed in the colder part of the tube,
and the silver will be left behind in a pure state,
if no other metal was present.    But as the na-
tive amalgam contains sometimes a portion of
bismuth, and even gold, the following mode
may be pursued :

*Process* I.—Dissolve the ore in nitric acid,
assisted by a gentle heat.    If any gold should
be present, it will be left behind, in the form of

a brown powder. Let it be examined as directed under the article Ores of Gold.

II.—Evaporate the nitric solution till a pellicle appears, and then pour it into a large quantity of distilled water. If the amalgam contained bismuth, the water will become milky, and a white powder will subside, which collect by the filter.

III.—Having thus separated the greatest portion of the bismuth, concentrate the fluid from which the oxid of bismuth has been obtained to a small compass, (separate the precipitate, if any should appear during this process, and add it to that obtained before,) and mingle with the concentrated fluid a solution of common salt, or muriatic acid, till no further cloudiness ensues. Suffer the precipitate to subside, and decant or filter the fluid. The obtained precipitate consists of muriate of silver and muriate of mercury.

IV.—Into the fluid left in process III. drop a solution of carbonate of potash, till no further cloudiness ensues, then boil the mixture, separate the produced precipitate, and put it aside for further use.

V.—Upon the precipitate, consisting of muriate of silver and muriate of mercury, obtained in process III. pour nitro-muriatic acid, of a

T

moderate strength, and digest; the muriate of lead will thus be dissolved, and the muriate of silver left behind, 100 parts of it indicate 75 of silver.

VI.—Let the fluid from which the muriate of silver has been obtained, be made boiling hot, and then decompose it by a solution of carbonate of potash; collect the precipitate, and add it to that obtained in process IV. Mix the whole with a little sugar, introduce the mixture into an earthen-ware or coated glass retort, and proceed to distillation, taking care to keep the bottom part of the retort of an obscure red heat, for about half an hour, or till no more quicksilver falls into the receiver, loosely adapted to the beak of the retort. The receiver should of course be filled with water, and the neck of the retort dipt into it for about half an inch or one inch. What remains in the retort is charcoal, and perhaps a little metallic bismuth, which escaped the process of separation employed.

### ANALYSIS OF SULPHURET OF MERCURY.

Species 1.—*Analysis of Native Cinnabar.*

*Process* I.—Digest one part of the ore, levigated as fine as possible, in four of nitro-muriatic acid, composed of three parts of muriatic,

and one of nitric acid, repeatedly, until it dis-
solves no more.

II.—Ignite the insoluble residue, which con-
sists chiefly of sulphur and silex, and note
the loss of weight, which gives the weight of
the sulphur it contained, provided no portion of
the sulphur has been acidified in process I. which
may be known by nitrate of barytes not pro-
ducing a precipitate when added to the solution.
Should a precipitate take place, 100 parts of it
are equal to 14.5 of sulphur.

III.—Mingle the nitro-muriatic solution with
carbonate of potash, at a boiling heat; collect
the precipitate, and dry it thoroughly.

IV.—To the obtained precipitate add one-
eighth part of lamp-black, introduce the mix-
ture into an earthen-ware retort, to which a
receiver, previously filled with water, has been
adapted, and distill till no more drops of quick-
silver fall from the neck of the retort.

The residuary mass in the retort consists
chiefly of charcoal and oxid of iron.

### ANALYSIS OF SALTS OF MERCURY.

Species 1.—*Analysis of Muriate of Mercury.*

In this ore oxid of mercury exists with muriatic
and sulphuric acid.

*Process* I.—Take one part of the ore, reduced to a fine powder, and digest it repeatedly in acetous acid; by this means the metallic mercury, if it contains any, will be left behind, and the sulphate and muriate will become dissolved.

II.—Decompose the obtained solution by acetate of barytes, and collect the precipitate, to learn the quantity of sulphuric acid which is always present in the ore, 100 parts of the precipitate indicate 186 of sulphate of mercury.

III.—Into the remaining fluid, let fall a solution of nitrate of silver, to ascertain the quantity of muriatic acid.

IV.—To learn the quantity of mercury, immerse into the solution obtained in process III. a cylinder of iron which throws down the quicksilver in a metallic state.

The analysis of this ore may likewise be effected by boiling it repeatedly with sub-carbonate of potash in a sufficient quantity of water, by this means muriate of potash and sulphate of potash will be obtained in solution, and carbonate of mercury will be left behind. The latter may be dissolved in nitric acid, and the mercury precipitated by a cylinder of copper. The quantity of sulphuric acid may be learnt by the addition of nitrate of barytes, and that of the

muriatic acid by nitrate of silver, in the manner so often mentioned already.

Species 2.— *Analysis of Hepatic Mercury.*

The analysis of this ore was conducted by Klaproth in the following manner.

*Process* I.—One hundred grains of the ore being reduced to a fine powder, were heated with 500 grains of muriatic acid to ebullition, to which was added, by a little at a time, 100 grains of nitric acid, in order to effect a solution: a black residue remained weighing 10 grains. This residue was heated in a crucible carefully, in order that the sulphur it might contain, should be vo- latilized. There remained three grains of a light coaly powder, which became ignited and burned away by a stronger heat, leaving one grain of reddish ashes.

II.—The solution being precipitated by mu- riate of barytes, 46,5 grains of sulphate of ba- rytes fell down, so that 6,5 grains of sulphur had been converted into sulphuric acid by the action of the nitric acid. Mr. Klaproth esti- mates the quantity of sulphur contained in the sulphurated hidrogenous gas, given out during the solution of the ore, at 0,25 grains, which he

estimates to be equal to 13,75 parts of sulphur. in 100 of the mineral.

III.—Having so far proceeded, one thousand grains of hepatic mercury in powder were put into a retort joined to the pneumatic apparatus; the heat was gradually raised till the bottom of the retort became red hot. After the heat had driven out the atmospheric air from the retort, sulphurated hidrogen gas was evolved; its volume measured 24 cubic in. without reckoning that portion which had been absorbed by the water put into the intermediate receiver, which water was strongly impregnated with the gas. A few globules of mercury were collected in the receiver. The neck of the retort contained a mixture of black hydro-sulphuret of mercury, of a greasy consistence, some small metallic globules of quicksilver, and a few small needles of cinnabar. The mercury which was mechannically extracted from this mixture weighed 3,17 grains. The roof of the neck of the retort was alone covered with a solid sublimate of pure cinnabar which weighed 2,56 grains. The residue in the retort was a powder resembling soot, it weighed 39 grains. Burned in the open air it left 16 grains of ashes; so that the coal consumed amounted to 23 grains.

IV.—The earthy residue being digested with muriatic acid, left 6,5 grains of silex.

V.—The muriatic solution was supersaturated with ammonia, a brown precipitate fell down, and the fluid assumed a light blue tinge. The precipitate being dissolved in a hot alkaline solution left oxid of iron, which was attracted by the magnet. After having been ignited, it weighed 2 grains.

VI.—Muriate of ammonia was then poured into the alkaline fluid; this threw down alumine, which after ignition weighed $5\frac{1}{2}$ grains.

VII.—The other ammoniacal fluid was supersaturated with muriatic acid. A cylinder of zinc being immersed therein separated 0,20 grains of metallic copper.

On collecting the results of this analysis of the ore we find that 1000 parts consist of

Mercury . . . . . . . . . . . . . . . . . . 818
Sulphur . . . . . . . . . . . . . . . . . . 137 50
Charcoal. . . . . . . . . . . . . . . . . . 23
Silex . . . . . . . . . . . . . . . . . . . . 6 50
Alumine . . . . . . . . . . . . . . . . . . 5 50
Oxid of Copper . . . . . . . . . . . . 2
Copper . . . . . . . . . . . . . . . . . . 0 20
Water which served to form
   sulphurated hidrogen gas,
   and other loss . . . . . . . . . . . . 7 30
                     ————
                     1000

*Remark.*—This analysis may serve to rectify the false notions which have been adopted concerning the composition of this mixed mineral. By shewing that the sulphur is combined with the metal in the same proportion as in cinnabar, namely as 1 to 6 in round numbers, we are taught how little foundation there is for the opinion of those who think that a part only of the mercury is in the state of sulphuret of mercury, and that the other is a simple oxid. If that were the case, the non-sulphurated part would certainly be soluble in nitric acid. Experiment shews that this is not the case, because the acid cannot dissolve any portion, even when boiling hot, the mineral remains unchanged at the bottom of the vessel. The above opinion has arisen from observing that in sublimation part only of the mineral rises in the state of cinnabar, while the other is volatilized in the form of fluid mercury. But this no doubt arises from the presence of charcoal among its ingredients, which decomposes part of the cinnabar at an elevated temperature: whether it be that the charcoal takes from the mercury the minimum of oxigen necessary to the formation of cinnabar, or whether it be that the sulphur which combines at a high temperature with the carbon,

and forms carburetted sulphur, is put into a state in which it cannot combine with mercury. The facts shew that it is really so; for having, says Mr. Klaproth, as a direct proof sublimed artificial cinnabar with lamp black, the greatest part of the cinnabar was decomposed in the same manner as the hepatic mercury, and the result was a mixture of Ethiops mineral or hydro-sulphuret of mercury and globules of metallic quicksilver

## ORDER X.

### ORES OF ANTIMONY.

*Division of Ores of Antimony:*

GENUS I.—*Alloys of Antimony.*

Species 1.—Native Antimony.

GENUS II.—*Sulphurets of Antimony.*

Species 1.—Grey Sulphuret of Antimony.
    Subspecies 1.—Compact Grey Sulphuret
               of Antimony.
            2.—Foliated Grey Sulphuret
               of Antimony.
            3.—Radiated Grey Sulphuret
               of Antimony.

GENUS III.—*Oxids of Antimony.*

Species 1.—Red Ore of Antimony.
       2.—White Ore of Antimony.
       3.—Yellow Ore of Antimony.
       4.—Antimonial Oxid.

## ANALYSIS OF ORES OF ANTIMONY.

Species I.—*Analysis of Native Antimony.*

This ore is chiefly composed of antimony and iron, sometimes it contains a minute portion of silver and arsenic.

The analysis of it was effected by Klaproth, thus:

*Process* I.—One hundred grains of finely pulverised ore were digested in concentrated nitric acid till the whole was converted into a white powder, or till no further action took place, which was known by a fresh portion of the acid emitting no nitrous gas when suffered to act on the ore assisted by heat.

II.—The obtained mass, after being diluted with water, was thrown on a filter, the insoluble white oxid separated, washed, and dried.

III.—Into the fluid obtained by filtration, muriatic acid was dropt, a white curdly precipitate fell down, which being weighed indicated one grain of silver.

IV.—The fluid, from which the silver was obtained, yielded a blue precipitate, by the addition of prussiate of potash. This precipitate, after

being treated in the usual manner, namely, being ignited, yielded one quarter of a grain of iron.

V.—The insoluble oxid obtained in process II. was dissolved in muriatic acid assisted by heat. The solution was diluted with six times its weight of water, and the precipitate thus produced re-dissolved by the admixture of muriatic acid.

VI.—Into this muriatic solution a cylinder of zinc being immersed, 98 grains of metallic antimony were separated. Thus 100 grains of the ore contained,—antimony 98 grains, silver 1 grain, iron 0,25 grain.

If the ore contains arsenic and no silver, the analysis may be made by digesting it repeatedly in nitro-muriatic acid, composed of nitric acid, specific gravity 1,25 one part, and concentrated muriatic acid three parts. Both the arsenic and antimony become dissolved ; the latter may be separated by the mere admixture of water, and the arsenic may be disengaged by nitrate of lead; 100 parts of arseniate of lead indicate 33 of arsenic acid or 22 of metal; or, the ore may be repeatedly digested in concentratad nitric acid assisted by heat; the arsenic becomes acidified and dissolved, and the oxid of antimony is left behind: the oxid of antimony may be re-dis-

solved in muriatic acid, and treated as stated be-
fore; the quantity of arsenic may be ascertained
by nitrate of lead as stated above.

### ANALYSIS OF SULPHURETS OF ANTIMONY.

The sulphurets of antimony usually contain,
besides antimony, a portion of lead, copper,
iron, and silver; to which must be added the
earths composing the stony matrix, from which
they cannot be perfectly separated previously to
analysis. With these compound ores the best
method of proceeding is as follows:

*Process* I.—Take 500 grains of ore, finely
pulverized, digest it with 1500 grains of pure ni-
tric acid, specific gravity 1.25 and 1000 grains
of water for about half an hour, at the tempera-
ture of 150° Fahr. and repeat this process for
several times.

II.—Mingle the solution with a quantity of
water equal to the rest of the fluid, and pour off
the liquor as soon as it becomes clear; it may con-
sist of the nitrates of silver, lead, and copper,
with probably a little iron, dissolved in an excess
of acid.

III.—To separate the iron, boil the fluid, and the iron will be separated in the state of red oxid, by subsequent filtration.

IV.—Drop muriate of soda into the solution, as long as a precipitate takes place, and allow the whole to stand till the supernatant fluid becomes perfectly clear ; the precipitate is muriate of silver, which, being separated and washed, may be mixed with two or three times its weight of dry carbonate of soda, and reduced by fusion to the metallic state.

V.—The solution obtained in process IV. must now be saturated by potash or soda, and concentrated by evaporation to about one-third of its bulk ; and then mingled with ammonia in excess, the lead will be precipitated as white oxid, and the copper remains in solution. The former, by fusion with black flux, may be reduced to the metallic state.

VI.—The solution freed from lead may then be slightly acidulated with nitrous acid, and carbonate of potash added to it, which will throw down the oxid of copper; and this after being exposed to a low red heat becomes converted to the state of brown oxid, 100 parts of which denote 85 of metal.

VII.—The insoluble portion of the ore left in

process I. is to be digested, at a temperature
somewhat inferior to boiling with successive
portions of nitro-muriatic acid (consisting of
nitric acid specific gravity 1,25 one part, strong
muriatic acid three parts) as long as any action
takes place; the solutions being then mixed and
concentrated by evaporation, are to be poured
into a considerable quantity of pure water; an
immediate precipitate or white oxid of antimony
takes place, which, being separated, washed,
and mixed with twice its weight of black flux,
and a little nitre, is easily reduced to the metallic
button by a full red heat continued for a few
minutes.

VIII.—The solution obtained in process VI.
now contains only a little sulphuric acid and per-
haps iron, with some earthy matter. The addition
of nitrate of barytes, as long as any precipitate
falls down, indicates the quantity of sulphur;
after which, an excess of caustic potash, as-
sisted by a boiling heat, will throw down the
iron, and retain the alumine and silex, accord-
ing to rules given repeatedly already.

IX.—The insoluble residue of process VII.
containing only sulphur and earth, is decom-

posed by ignition, the sulphur flying off, and the earth remaining.

Thus the quantity of antimony is obtained by process VII.

of sulphur and earth by VIII. and IX.

of iron by II. and VII.

of silver by IV.

of lead by V.

of copper by VI.

The rest of the species of sulphurets of antimony may be analysed in a like manner.

### ANALYSIS OF OXIDS OF ANTIMONY.

Species 1.—*Analysis of Red Ore of Antimony.*

The analysis of this ore was conducted by Klaproth, thus:

*Process* I.—Upon 100 grains of the ore introduced into a retort, lodged in a sand-bath, and connected with the pneumatic apparatus, was poured muriatic acid. As soon as the ore was acted on by the acid, assisted by heat, sulphureted hidrogen gas was disengaged, which towards the middle of the process deposited in the neck of the retort, and in the hot water of the trough, a portion of sulphuret of antimony

of an orange-red colour, which amounted to se-
veral grains.

II.—The obtained sulphureted hidrogen gas
being measured and having deducted the com-
mon air of the retort, amounted to 37 cubic
inches.*

III.—These preliminary experiments being
made, 100 grains of the same ore, of select pure
specimens, were again digested with muriatic
acid in a long-necked mattrass. In this case,
likewise, sulphuret of antimony was deposited
in the neck of the vessel. When the solution
was effected, there remained $1\frac{1}{2}$ grain of a grey
residue, which, on being heated, burnt with the
character of sulphur,

IV.—The antimony contained in the muriatic
solution, was next precipitated, in the state of a
white oxid, by diluting it with water, and the
small portion of the metal that might still re-
main in that fluid was afterwards thrown down
by the addition of potash.

V.—The oxid thus procured, was re-dissolved
in muriatic acid, the solution diluted with six
times its quantity of water, and once more com-
bined with such a proportion of the same acid,

* From this Klaproth infers that the ore contains 19,70 of
sulphur.

as was necessary to re-dissolve the oxid precipitated. After the dilute solution had in this manner again been rendered clear, the antimony was separated in a metallic state by a polished cylinder of iron. It weighed $67\frac{1}{2}$ grains.

Hence the products obtained, were

<div style="text-align:center">

Antimony............... 67,50

Oxigen ................ 10,80

Sulphur................ 19,70

———

98

</div>

Species 2.—*Analysis of the White Ore of Antimony.*

The analysis of this ore was performed by Klaproth in the following manner:

*Process* I.—Twenty-five grains of the ore were mixed with 200 grains of carbonate of potash, and heated to redness in a platina-crucible. It melted and acquired a yellow colour.

II.—The mass was softened with water, and the oxid of antimony separated by the filter.

III.—The clear fluid was then supersaturated with nitric acid; upon which the mixture became turbid, depositing a small quantity of oxid of antimony; which, being separated, nitrate of silver when dropped into the clear fluid, pro-

duced no change. This mineral is therefore a
pure oxid of antimony; which, as may be
judged from its solubility in nitro-muriatic acid,
is but imperfectly saturated with oxigen, and
bears the greatest resemblance to the artificial
oxid of that metal.

# ORDER XI.

## ORES OF BISMUTH.

*Division of Ores of Bismuth.*

GENUS I.—*Alloys of Bismuth.*

Species 1.—Native Bismuth.

GENUS II.—*Sulphurets of Bismuth.*

Species 1.—Common Sulphuret of Bismuth.
2.—Cupreous Sulphuret of Bismuth.

GENUS III.—*Oxids of Bismuth.*

Species 1.—Bismuth ochre.

ANALYSIS OF ORES OF BISMUTH.

Species 1.—*Analysis of Native Bismuth.*

*Process* I.—Digest a determinate quantity of
finely pulverised ore repeatedly in dilute nitric
acid, assisted by a very gentle heat, till the fluid
dissolves no more, which may be known by the
last portion of acid occasioning no precipitate,
when poured into water.

II.—To separate the bismuth from the solu-
tion, mingle it with a large portion of water, a
white precipitate falls down, which is oxid, or
more properly, nitrate of bismuth. But as the
whole cannot be separated by one process, let
the solution be concentrated again by evapo-
ration, a second affusion of water will then
precipitate another portion of the oxid, which
escaped the action of the water. The same
process may be repeated for several times suc-
cessively. If lead, silver, copper, or iron,
should be present, they will remain in the
fluid, which is decanted from the precipitate.

III.—To effect the separation of the oxid of
bismuth in the most perfect manner, let the
remaining fluid, from which water separates no
precipitate, be again concentrated to as small a
bulk as possible; that is to say, so as just to
hold all substances it may contain in solution,
without crystallizing; or if part of nitrate of lead
should be deposited in a crystalline form, add
again a few drops of water, to effect a solution,
and then add to this concentrated fluid, muriatic
acid, drop by drop, as long as a precipitate
ensues; this precipitate consists of the remain-
ing portion of oxid of bismuth, and perhaps of

muriate of silver, or muriate of lead, if these metals were present.

IV.—To separate these precipitates, add a few drops of concentrated nitric acid, which will dissolve the bismuth and leave the silver, and then drenching again the fluid with water, which will now separate the whole: 100 parts of the oxid contain, according to Klaproth, 81,3 of bismuth.

V.—The bismuth and silver being thus separated the fluid may be examined for iron by ammonia, in the manner stated under the article iron ores.

Sulphurets and oxids of bismuth may be analysed in a similar manner, the quantity of sulphur may be found by means of nitrate of barytes, according to the rules described already, page 117.

# ORDER XII.

### ORES OF NICKEL.

*Divison of Ores of Nickel.*

The ores of nickel are not numerous; they are the following:

Genus 1.—*Sulphurets of Nickel.*

Species 1.—Sulphuret of nickel, or copper nickel.

Genus 11.—*Oxid of Nickel.*

Species 1.—Nickel ochre.

### ANALYSIS OF ORES OF NICKEL.

Species 1.—*Analysis of Sulphuret of Nickel.*

This ore, when pure, is composed of nickel, sulphur, and arsenic, but it is often found contaminated with cobalt, iron, and bismuth.— Besides these metals it may contain copper and silver; the matrix, which is usually quartz and alumine, cannot be separated completely. Let

us suppose that all these substances were contained in the ore, the mode of analysis might then be conducted thus:

*Process* I.—Take one part of the finely pulverised ore, pour over it four of nitric acid diluted with an equal bulk of water; digest the mixture by a gentle heat till no further action ensues; and repeat this operation, with fresh quantities of acid, for several times successively, until no farther action takes place; and lastly, separate the insoluble part by the filter.

II.—Let the insoluble part, which consists chiefly of sulphur and the silex of the ore, be weighed; when dry ignite it in a crucible, and ascertain the loss which gives the weight of the sulphur with tolerable accuracy.

III.—Boil the remaining part in concentrated nitric acid repeatedly, wash, dry, and ignite it; it is silex.

IV.—Mingle the before-obtained nitric solution, and add to it a solution of soda so as to render it neutral, or nearly so; then concentrate it by evaporation and pour it into water. If a white precipitate falls down it is oxid of bismuth. Separate it by the filter; dry and weigh it, 100 parts are equal to 81.3 of metallic bismuth.

V.—To the fluid, from which the oxid of

bismuth has been separated, add muriate of soda
till no further precipitate falls down. The pre-
cipitate is muriate of silver, 100 parts are equal
to 75 of silver.

VI.—To learn whether iron was present in
the ore, evaporate the solution to dryness, and
boil it repeatedly to dryness with concentrated
nitric acid ; lastly, diffuse it through water, and
collect the oxid of iron by the filter, 100 parts
= 53 of metallic iron.

VII.—To the fluid from which the iron has
been separated add a solution of soda to render
it neutral, and then drop into it a solution of
nitrate of lead. The precipitate is arseniate of
lead, 100 parts = 33 arsenic acid, or to 22 of
metallic arsenic.

VIII.—If to the nitric solution carbonate of
soda is now added, a precipitate falls down,
which, after being washed in liquid ammonia,
consists of oxid of iron and alumine.

IX.—To separate these two substances boil
the precipitate in a concentrated solution of
potash, the alumine will be dissolved, and the
oxid of iron left behind ; deducting the weight of
the latter, from the weight of the whole, the
quantities of each may be found.

x

X.—To separate the copper supersaturate the ammoniacal solution, process VII. slightly with nitric acid, and immerse into it a cylinder of iron, to get again rid of the iron used for separating the copper, again decompose the solution by carbonate of soda, and again digest the precipitate in ammonia.

XI.—The solution being now freed from all metals, and containing nothing but nickel and cobalt, should be treated according to Mr. Phillips, in the following manner :

XII.—Evaporate the fluid till the excess of ammonia is volatilized, which may be known by the vapours ceasing to discolour moist turmeric paper, then dilute it copiously with water, and decompose it by a solution of potash or soda, the precipitate is oxid of nickel.

XIII.—The solution now contains only cobalt, which may be separated by carefully saturating it with nitric acid, and adding carbonate of soda.

The oxids of nickel are best analysed in a like manner,

## ORDER XIII.

### ORES OF COBALT.

Few of the ores of cobalt have hitherto been examined with accuracy, hence much confusion exists with regard to them. The following is the general division of ores of cobalt adopted.

### *Division of Ores of Cobalt.*

GENUS I.—*Alloys of Cobalt.*

Species 1.—White Cobalt Ore.
      2.—Bright White, or Glanz Cobalt Ore.
      3.—Dull grey Cobalt Ore.

GENUS II.—*Oxids of Cobalt, or Earthy Cobalt Ores.*

Species 1.—Friable black Cobalt ochre
      2.—Indurated Black Cobalt Ochre.
      3.—Yellow Cobalt Ore.
      4.—Brown Cobalt Ore.

Genus III.— *Salts of Cobalt.*

Species 1.—Red Cobalt Ore, or Arseniate of
                Cobalt.
          2.—Earthy Red Cobalt Ore.
          3.— Cobalt Bloom, or Radiated Red
                Cobalt Ore.
          4.—Sulphate of Cobalt.


### ANALYSIS OF ORES OF COBALT.

The native alloys of cobalt often contain a con-
siderable portion of arsenic in the metallic state,
and nickel and iron; sometimes even a small
portion of manganese and copper has been
detected in them; hence the analysis of these
ores, is rather difficult.

### ANALYSIS OF ALLOYS OF COBALT.

It having been stated that arsenic in the me-
tallic state is usually contained in cobalt ores, it
should be remembered that when we apply nitric
acid to effect a solution of these ores, the arsenic
becomes changed either into arsenious or arsenic
acid, according to the mode in which the nitric
acid is applied. If, namely, a small portion of
nitric acid, and in a diluted state, is applied to

the ore of cobalt, containing metallic arsenic,
the latter metal becomes converted into arsenious
acid, which is insoluble, and therefore becomes
precipitated by simply evaporating or concen-
trating the nitric solution; whereas, on the
contrary, if a concentrated, or a large quantity
of nitric acid is applied to the ore, the arsenic
is compleatly acidified at the expense of the
nitric acid, and becomes converted into arsenic
acid, which is not precipitated, but being so-
luble is held in solution. This arsenic acid
thus formed, unites as arsenic acid with part of
the cobalt, as well as with the other metals, and
forms arseniates of those metals which are de-
composable by alcalies, and thus render the
analysis exceedingly difficult. Let it be under-
stood, however, that oxid of cobalt is soluble in
liquid ammonia, but oxid of iron is not, and
that nitrate of iron deposits much of its oxid by
mere exposure to air, but the solution of nitrate
of cobalt is permanent.

This being premised, the following analysis
of Tassaert will be easily understood.

*Process* I.—To estimate the quantity of ar-
senic separately M. Tassaert digested one hun-
dred parts of the cobalt ore with dilute nitric
acid, and in some hours the whole was dissolved;

x 3

but by cooling, a quantity of white crystalline
grains were deposited. On evaporation more
of them were deposited, and when all had thus
separated, they were collected and dried, and
weighed 56 parts, all of which was sublimed
by heat except 3 parts, probably a mixture of
arsenic and cobalt. Hence the oxid of arsenic
from this ore may be reckoned at about 53 parts,
indicating 49 per cent. of metallic arsenic in
the ore.

II.—Three hundred parts of the ore were
then digested with four times as much nitric
acid, which made a rose-coloured solution. By
partial evaporation, and subsequent addition of
water, and heating, a rose-white precipitate fell
down, leaving a rose-coloured solution.

III.—This solution, boiled with an excess of
potash, gave an oxid of cobalt at first rose-
coloured, then passing to green, and when dried
in a red heat, it became black. It weighed 85
parts.

IV.—The 85 parts of the last experiment
were then examined for iron. When re-dis-
solved in nitro-muriatic acid, liquid ammonia
was added, which gave a black precipitate,
which became re-dissolved by an excess of
the alkali except a small portion. This being

again treated with nitro-muriatic acid and am-
monia, was reduced to 4 parts, and appeared to
be oxid of iron.

V.—The rose-coloured precipitate of experi-
ment III. which proved to be a mixed arseniate
of cobalt and iron, was decomposed by potash
in excess, and gave a precipitate weighing 100
parts when dried.

VI.—The precipitate obtained in the last
experiment was re-dissolved in nitric acid, the
solution concentrated, and diluted with water.
A precipitate of oxid of iron weighing 27 parts
separated, and a clear solution of cobalt was left
behind.

VII.—The nitric solution of cobalt of ex-
periment VI. was decomposed by ammonia,
the precipitate became re-dissolved by an excess
of the alkali, except 15 parts which were oxid
of iron. The solution was added to the ammo-
niacal solution of cobalt of experiment IV.

VIII.—The insoluble precipitates of oxid of
iron obtained in experiments IV. VI. VII. were
then mixed and examined. They still gave a
blue glass when fused with borax, and therefore
contained a portion of cobalt. Acetic acid was
found a good method of separating them.

IX.—For this purpose they were re-dissolved

in nitro-muriatic acid, precipitated by a sufficient quantity of ammonia, and the precipitate whilst still wet was put into acetic acid. This dissolved the whole at first, but on boiling and evaporating the solution nearly to dryness, most of the iron separated, and by re-dissolving the mass in water and evaporating it nearly to dryness successively, nearly all the oxid of iron was rendered insoluble, whilst the cobalt remained in the solution, and this acetate of cobalt in proportion as it was freed from iron became more and more of a fine rose colour.

X.—The solution was then supersaturated with ammonia, and this solution was added to the different portions of the same fluid obtained in the former experiments. The whole was then boiled to expel the excess of ammonia, and by adding potash the oxid of cobalt was precipitated, which after being washed and dried, weighed 133 parts. This oxid reduced in a crucible lined with charcoal, gave regulus of cobalt in its purest form, of the specific gravity of 8,538, totally free from arsenic and iron.

XI.—Lastly, to estimate the quantity of sulphur, 100 parts of the ore were separately boiled with 500 of nitric acid, and diluted with water

to separate all the oxid of arsenic or arsenious
acid, that would be deposited spontaneously.
All the sulphur being now converted into sul-
phuric acid by the action of the nitric acid,
nitrate of barytes was added, and from the pre-
cipitated sulphate of barytes the quantity of sul-
phuric acid, and of course, of sulphur, was
estimated according to the rules stated, p. 117.

*Remarks.*—Some improvements may be sug-
gested in this ingenious analysis. To separate
arsenic compleatly from the cobalt to which it
adheres so obstinately, Mr. Chenevix's method
may be advantageously adopted of adding nitrate
of lead to the solution of the ore containing the
arsenic fully acidified and partly united to the
cobalt. The nitrate of lead engages all the
arsenic acid, and decomposes the arseniate of
cobalt. The arseniate of lead, being insoluble,
remains at the bottom, the clear solution may
then be decomposed by carbonate of potash,
which separates the metallic contents, after
which ammonia will dissolve the cobalt, and
also any nickel that may be present, leaving the
iron and any excess of lead that may remain.
The ammoniacal solution of nickel and cobalt
may be separated, according to Mr. R. Phil-
lips, viz. Let the solution be evaporated till the

excess of ammonia is driven off (which is known by a paper dipped in tincture of turmeric no longer turning brown) in this state, if potash is added, and diluted with much water, the whole of the nickel is precipitated very speedily, but the cobalt remains suspended for a considerable time.

If copper be present, after the arseniate of lead is precipitated, let the copper be separated by a cylinder of iron before the nitric solution is decomposed by alkalies.

The ore called bright white cobalt ore, may be examined in a like manner.

### Species 3.—*Analysis of the Dull Grey Cobalt Ore.*

The analysis of this ore (which may be effected like the former) was conducted by Klaproth, in the following manner:

*Process* I.—One hundred grains of the ore, when gently digested with nitric acid, dissolved in it gradually, leaving behind $16\frac{1}{2}$ grains and a half of minute white-grey resplendent globules, which consisted of arsenic, with a little sulphur. By boiling with water, this arsenical ingredient was dissolved, and there remained $1\frac{1}{2}$ grain : of which $\frac{1}{2}$ grain of sulphur deflagrated on a small

scorifying test. The remaining 1 grain was oxid of cobalt.

II.—The nitric solution which was brownish red was evaporated partly in a sand-bath. In this process there still became separated some oxid of arsenic, in the form of a white crystalline crust; which, collected after cooling, and being by degrees lixiviated with a little water, weighed 30 grains when dry. It again entirely dissolved in the water with which it was boiled.

III.—Both the solutions of the arsenical oxid in water shewed exactly the same appearances which are exhibited by any other aqueous solution of oxid of arsenic. By combination with limewater, they yielded arseniate of lime ; with sulphuret of ammoniac they produced yellow sulphuret of arsenic (orpiment), and the green pigment of Scheele with ammoniacal oxid of copper.

IV.—When the nitric solution of cobalt did no longer deposit arsenic, it was diluted with water, and precipitated by carbonate of potash ; the oxid of cobalt, thus obtained, had a peach-flower colour. On dissolving it in muriatic acid, and diluting the solution with water, the fluid acquired a rose-red colour.— Therefore the constituent parts of the crystal-

lized, white cobalt-ore, separately produced in
this analysis, consist, according to Klaproth, in
the hundred, besides the portion of cobalt itself,
of 45 grains of oxid of arsenic, and $\frac{1}{2}$ grain of
sulphur : no traces of iron was found.

### ANALYSIS OF OXIDS OF COBALT.

The analysis of the native oxids of cobalt may
be conducted in the manner stated already ; but, as
sometimes a portion of manganese and copper is
present in these ores, we shall give the analysis
of a native oxid of cobalt containing both these
metals, as conducted by Klaproth.

*Process* I.—Five hundred grains of a magne-
sian ore of cobalt were digested in moderately
strong muriatic acid. The solution was effected
with the extrication of oxy-muriatic gas. By
continuing the digestion at the degree of ebulli-
tion, the mixture lost its brown colour, and the
fluid became green, leaving a white earthy resi-
due. On diluting the solution with water, its
green colour disappeared, and the filtered fluid
acquired a brownish red colour. The residue,
separated by filtration, weighed 206 grains, after
ignition.

II.—The obtained solution being concentrated by evaporation a precipitate became deposited, which was silex; it being collected on the filter and ignited, weighed 10 grains. After this the solution was saturated or mingled with potash in excess, and the mixture digested for some time and filtered. A muddy residue remained on the paper of a dirty light brown colour, which rapidly turned black on exposure to air.

III.—The fluid separated from this residue was neutralized with muriatic acid, and then combined with carbonate of potash. It deposited alumine, the quantity of which, after ignition, amounted to 12 grains.

IV.—The black residue (process II.) was again dissolved in muriatic acid, and precipitated by carbonate of potash; the precipitate was of a pale red colour. When washed and dried it was subjected to a strong red heat for one hour, it acquired a greyish brown hue, it weighed 178 grains.

V. — These 178 grains were digested for some time in a boiling heat, with nitric acid, and the solution afterwards diluted with water, and filtered. There remained a black residue,

Y

which, being washed, dryed, ignited, weighed 80 grains, it was oxid of manganese. In order to examine it for iron, it was again digested in nitric acid ; in which, on the addition of a little sugar, it immediately dissolved, without leaving iron, or any other residue. When precipitated by carbonated potash, it yielded a carbonate of manganese, of a white colour.

VI.—Hence the nitric solution still contained 98 grains of the mentioned 178 ; but from the first there must be subtracted one grain for copper, discovered in the sequel. By carbonate of potash, this re-dissolved portion was again precipitated, of a pale peach-flower colour; and this precipitate, as the following examination of it has shewn, consisted of a mixture of oxid of cobalt and oxid of manganese.

VII.—The 206 grains, which remained on dissolving the ore, process I. were mixed with twice their weight of carbonate of potash, and moderately ignited for two hours ; they were then covered with water, supersaturated with muriatic acid, and evaporated to a gelatinous constistence : when the siliceous earth had been separated, washed, and ignited, it weighed 114 grains.

VIII.—The remaining muriatic solution being
neutralized with carbonate of potash, and then
combined with oxalate of potash, did not yield a
precipitate.   It was therefore combined with
liquid ammonia, which threw down alumine,
the quantity of which, after ignition, weighed
90 grains.   The still remaining portion of the
fluid continued clear on the addition of car-
bonate of soda.

IX.—To ascertain the proportion of copper,
the presence of which has already been ob-
served in the previous experiments, sulphuric
acid was affused upon 500 grains of the ore, the
solution being evaporated, the inspissated mass
was dissolved in water, and a polished cylinder
of iron was immersed into the clear solution,
which acquired a pale rose colour.   The iron
became gradually incrusted with a cupreous
pellicle; which, when carefully collected, weighed
$\frac{1}{2}$ grain; and thus one grain of oxid of copper
must be put in the computation.

X.—One hundred grains of the ore lost on
exposure to heat 17 grains.   Therefore, the five
hundred grains of the mineral here examined
have been decomposed into

Oxid of cobalt, mixed with oxid

    of magnesia,  process VI......... 97

Oxid of manganese     V......... 80

Oxid of Copper         IX......... 1

Silex              II.   10 ⎫ 124
─────              VII.  114 ⎭

Alumine            III.  12 ⎫ 102
─────              VIII.  90 ⎭

Water                   X. ...... 85
                              ─────
                              489

The analysis of the salts of cobalt may be easily accomplished, according to what has been stated in the preceding analysis.

## ORDER XIV.

### ORES OF ARSENIC.

The ores of arsenic are very abundantly diffused through the mineral kingdom, and accompany almost every other ore. They may be divided in the following manner:

*Division of Ores of Arsenic:*

GENUS I.—*Alloys of Arsenic.*

Species 1.—Native Arsenic.

GENUS II.—*Sulphurets of Arsenic.*

Species 1.—Arsenical Pyrites, Mispickel, or Marcasite.

2.—Sulphuret of Arsenic, or Realgar.

Subspecies 1.—Yellow Sulphuret of Arsenic, or Orpiment.

GENUS III.—*Oxids of Arsenic.*

Species 1.—Native White Oxid of Arsenic.

### GENUS IV.—*Salts of Arsenic.*

Species 1.—Arseniate of Lime, or Pharmaco-
lite.

#### ANALYSIS OF ORES OF ARSENIC.

### Species 1.—*Analysis of Native Arsenic.*

This ore usually contains a portion of iron,
and sometimes, though very rarely, a portion of
gold and silver. Its analysis may be effected
thus:

*Process* I.—Take one part of the finely pul-
verized ore, digest it repeatedly, assisted by a
gentle heat, in three of nitro-muriatic acid,
composed of one part of nitric and one and a half
of muriatic acid, and repeat this operation till a
complete solution is obtained, or till a new por-
tion of acid produces no further action upon the
residue; then decant the fluid, and let it sub-
side. If a white precipitate be observed in the
solution, the ore contained silver : let the preci-
pitate be therefore collected. It is muriate of
silver.

II.—Evaporate the muriatic solution, from
which the silver has been separated, to about $\frac{1}{4}$,
or till it becomes turbid, and add to it water,

till this fluid occasions no further turbidness, which may be known by filtering from time to time a small quantity of the mixture, and assaying the filtered solution by a new addition of water. The white precipitate obtained is oxid of arsenic. The water which has been employed for precipitating the oxid of arsenic should again be evaporated to as small a compass as possible, and again assayed for arsenic by water, and this process must be repeated till no more precipitate takes place by adding water to the concentrated solution; and lastly the solution should be evaporated to compleat dryness, and then diffused through water, to separate the last portion of arsenic, if any.

III.—Re-dissolve this precipitate in muriatic acid, and precipitate it, by immersing into its solution a cylinder of zinc, mixing with it at the same time $\frac{1}{10}$ part of alcohol; this precipitate after being dried, may be fused. It is metallic arsenic.

IV.—The solution from which the arsenic has been separated, may be assayed for iron: for that purpose, let it be concentrated, and mix it with liquid ammonia in excess; if a brown precipitate ensues, it is iron.

*Remark.*—If the ore contain gold, nitric acid

should be made use of in the first process. The residue may then be treated in a similar manner with nitro-muriatic acid, and the solution precipitated by sulphate of iron, to obtain the gold.

*Remark.*—As a general rule in attempting the analysis of the ores of arsenic, as usual by the application of nitro-muriatic or nitric acid, it should be observed that whenever the object is to obtain merely a solution of the ore, with a view to obtain, in the manner stated by water, or by an alcali, the arsenical oxid, no more acid should be used than is absolutely necessary to effect the solution of the ore. For if a larger portion of nitric or nitro-muriatic acid be applied, the arsenic, or a portion of it, is converted into arsenic acid, which is no longer precipitable by water or by an alcali, and which combining with the iron or other metallic oxid, or earth, that may be present, renders the analysis unnecessarily complicated and difficult.

But as in every application of nitric or nitro-muriatic acid to arsenic, some arsenic acid will probably be generated, another mode of analysis may be pursued, which is by far the most accurate: it consists in the compleat acidification of arsenic in the first instance, and afterwards transferring the arsenic acid to lead, with which .

it forms an insoluble compound, the proportions of which are invariable. The following may serve as an illustration of what has been stated.

ANALYSIS OF SULPHURETS OF ARSENIC.

Species 1.—*Analysis of Arsenical Pyrites.*

*Process* I.—Reduce the ore to as fine a pow-as possible, pour over it in a Florence flask four parts of nitro-muriatic acid, assist the action by a gentle heat, and repeat this operation for se-veral times successively, and lastly, filter the fluid. The whole of the arsenic that was pre-sent in the ore will thus be acidified or con-verted into arsenic acid.

II.—Saturate the obtained solution with car-bonate of potash accurately, and decompose it by dropping into it a solution of nitrate of lead till no farther precipitate ensues. One hundred parts of the obtained arseniate of lead, when dried at a low red heat, contain 33 of arsenic acid, of which the metallic contents may be reckoned at 22 parts.

III.—But as the ore contains sulphur, sul-phuric acid must have been formed by the application of the nitro-muriatic acid, and the precipitate obtained by nitrate of lead, must con-

tain sulphate of lead. To get rid of this let it be digested in very dilute nitric acid or in acetous acid, the arseniate of lead will become dissolved, and the sulphate of lead will be left behind. Hence the difference of weight between the precipitate before and after treatment with the latter acid will show the proportion of the arseniate and sulphate of lead.

In this manner all the rest of the sulphurets and oxids of arsenic may be examined.

### ANALYSIS OF SALTS OF ARSENIC.

#### Species 1.—*Analysis of Arseniate of Lime.*

In this ore arsenic exists in the state of arsenic acid combined with lime and water. Its analysis was conducted by Klaproth thus :

*Process* I.—One hundred grains of the ore being moderately heated lost $22\frac{1}{2}$ grains. As in this operation neither by the smell nor by the sight any other volatile matter, the water, could be observed, Mr. Klaproth considers the loss of weight as water of crystallization.

II.—Those 77 grains and a half which remained after the ignition, dissolved in nitric acid, left a grey residue of 6 grains of silex mixed with alumine.

III.—The filtered solution had a reddish hue, it was evaporated to a small volume, and mixed with a solution of acetate of lead as long as a precipitation ensued. The precipitate, when collected, washed, dried, and ignited, weighed 138 grains. It consisted of arseniate of lead. Agreeably to a counter experiment, in which 100 grains of dry acid of arsenic, dissolved in water and combined with the quantity of acetated lead requisite to effect a saturation, yielded 297 parts of arseniate of lead, those 138 grains mentioned before, indicate, according to Klaproth, $46\frac{1}{2}$ grains of concrete acid of arsenic.

IV.—What remained of the fluid after the separation of the precipitate, together with the washings, was concentrated, during which operation green coloured borders appeared on the inner surface of the vessel. To separate the small quantity of undecomposed acetate of lead, it might yet have contained, muriatic acid was added. When upon farther evaporation no muriate of lead appeared, it was mixed with sulphuric acid. This produced a copious precipitate of sulphate of lime, which being collected on the filter, washed with weak spirit

wine, and heated to redness, weighed 54 grains
Therefore, since in 100 parts of ignited sulphate
of lime, the lime amounts to $42\frac{1}{2}$ parts, the
mentioned 54 grains determine the portion of
lime contained in the fossil examined at 23
grains.

V.—The remainder of the fluid was neutra-
lized with carbonate of soda, and evaporated
to dryness. On re-dissolving in water the dry
saline mass, there remained a powder weighing
$\frac{1}{2}$ grain, which tinged glass of borax with a fine
deep blue, and thus proved to be oxid of co-
balt.

Thus hundred grains of pharmacolite, sub-
mitted to this analysis, have been decomposed
by Klaproth, into

Arsenic Acid_____46,5
Lime_____ 23,
Oxid of Cobalt ._____  0,5
Alumine and Silex _____  6,
Water_____ 22,5
                          _____
                          98,5

But since the oxid of cobalt is here but
casually admixed, and as the silex originates

merely from the granitic matrix of the ore, it follows, that after subtracting these, the proportions of the constituent parts of the pharmacolite, are,

Arsenic Acid ................ 50,54
Lime ........................ 25,
Water ....................... 24,46
                             ———
                             100*

* Analytical Essays, vol. I. p. 224:

Z

## ORDER XV.

### ORES OF TUNGSTEN.

There are only two ores of Tungsten hitherto known.

*Division of Ores of Tungsten.*

GENUS I. — *Oxid of Tungsten.*

Species 1.—Tungstate of Iron and Manganese, or Wolfram.

Species 2.—Tungstate of Lime.

### ANALYSIS OF ORES OF TUNGSTEN.

Species 1.—*Analysis of Tungstate of Iron and Manganese, or Wolfram.*

In this ore oxid of tungsten exists in combination with a considerable portion of iron, and oxid of manganese. Its analysis may be accomplished in the following manner:

*Process* I.—Take one part of the ore levigated as finely as possible, digest it in a very gentle heat for at least four hours with 3 parts of

muriatic acid; suffer it to cool, decant the solu-
tion, and wash the residue repeatedly in water,
and dry it.

II.—Pour over the residue two parts of liquid
ammonia, suffer it to stand 4 or 5 days, and
agitate it frequently ; decant the ammoniacal
solution, wash the residue, dry it, and digest it
alternately in muriatic acid and in liquid am-
monia, till it experiences no farther diminution,
or till the whole is nearly, or totally dissolved.
What remains is silex.

III.—Mingle the ammoniacal solutions, and
evaporate it in a retort or bason, to dryness ;
transfer the mass into a platina crucible, and
heat it thoroughly, or till it acquires a yel-
low colour. This product is oxid, or acid of
tungsten.

IV.—Having done this, mix all the muriatic
solutions which contain the iron and manganese,
with $\frac{1}{6}$ part of sulphuric acid, and evaporate the
whole to dryness.

V.—Re-dissolve the before obtained mass in
water, and add to it liquid ammonia, the preci-
pitate which falls down consists of the oxids of
iron and manganese, contained in the ore; col-
lect, wash, and dry it.

VI.—To separate these metals, digest the precipitate by heat repeatedly in concentrated nitric acid, and evaporate it to dryness.

VII.—Transfer the mass into acetic acid, and digest it with heat; the manganese will become dissolved, and the iron remain behind, deducting the weight of this, from the weight of the whole precipitate, the respective proportions of each may be found; or if a solution of an alkali be added, the fluid will assume a brown colour, and a precipitate will be obtained after boiling for a few minutes. This is the oxid of manganese contained in the ore.

### Species 2.—*Analysis of Tungstate of Lime.*

In this ore oxid of tungsten exists combined with lime.

*Process* I.—Digest one part of the ore repeatedly in three of nitric or nitro-muriatic acid, till a new addition of acid dissolves no more; the earth will be dissolved, and the tungsten remain behind in the form of a yellow oxid, if pure: it is soluble in liquid ammonia, from which it may be recovered, as directed in the preceding analysis.

II.—The nitric or muriatic solution contains the lime, and sometimes a little iron; on adding

to it at a boiling heat, carbonate of potash,
the lime will be precipitated, as carbonate of
lime, 32 parts of which = 17,6 of lime : if it
contains iron, dissolve the precipitate in muriatic
acid, and add liquid ammonia, the iron will thus
become separated.

## ORDER XVI.

### ORES OF TELLURIUM.

*Division of Ores of Tellurium.*

There is but one genus of the ore of Tellurium, which is an alloy of the metal called Tellurium. As this metal, however, is met with in combination, or at least mixed with gold, silver, or lead, in various proportions, the ores of tellurium have been divided in the following manner :

GENUS I.—*Alloys of Tellurium.*

Species 1.—Native Tellurium, or Aurum Paradoxum ; Sylvanite, or White Native Tellurium.

2.—Graphic Ore, Aurum Graphicum, or Grey Native Tellurium.

3.—Yellow Native Tellurium, or Yellow Ores of Naggag.

4.—Foliated, or Black Ore of Tellurium.

### ANALYSIS OF ORES OF TELLURIUM.

Species 1.—*Analysis of Native Tellurium.*

*Process* I.—Let one part of the finely pul-
verised ore be gently digested with six parts of
muriatic acid, and add three parts of nitric
acid gradually. Repeat this operation till the
acid exercises no farther action upon the ore,
and filter the solution.

II.—Dilute it with so much water as it can
bear, without becoming turbid, and add to the
solution potash, dissolved in water, in excess, or
until the white precipitate which is first formed,
is again dissolved, and nothing remains but a
brown flaky sediment, which is a mixture of
gold and iron contained in the ore.

III.—To separate these two metals, let it be
re-dissolved in nitro-muriatic acid, precipitate
the gold from this fluid by a solution of cold
prepared nitrate of mercury added drop by
drop till no further brown precipitate ensues.
This product consists of gold and muriate of
mercury. The gold may be separated by ex-
posing it to heat, which will volatilize the mu-
riate of mercury.

IV.—To obtain the iron add to the nitro-muriatic solution liquid ammonia, the brown precipitate is oxid of iron.

V.—To the alcaline fluid of process II. add muriatic acid, taking care to avoid an excess of acid. The oxid of tellurium is thus precipitated in the form of a white oxid, 178 parts = to 148 of the metal.

VI.—To reduce this oxid to the metallic state, form it into a paste with a small quantity of oil, put it into a retort or crucible, and apply heat; as the oil becomes decomposed, brilliant metallic drops are observed in the upper part of the vessel, which increase in number until the oxid is reduced.

### Species 2.—*Analysis of Aurum Graphicum, or Grey Native Tellurium.*

In this ore tellurium is alloyed with gold and silver.

*Process* I.—Digest the finely pulverised ore repeatedly in small portions of nitro-muriatic acid, till no farther action ensues. The insoluble residue contains muriate of silver formed during this operation, together with the stony matters or matrix of the ore, which is usually quartz.

II.—To recover the silver, fuse the muriate of silver with carbonate of soda, as directed before, page 112.

III.—To obtain the oxid of tellurium concentrate the nitro-muriatic solution, and pour it into water; the powder which falls down is oxid of tellurium.

IV.—Re-dissolve the obtained oxid of tellurium in muriatic acid, and immerse in the solution a cylinder of iron, brown or black flakes will fall down, which consists of metallic tellurium.

V.—The gold which is present in the ore may be obtained by mingling the fluid from which the tellurium is separated with a solution of sulphate of iron. See ores of gold.

### Species 3.—*Analysis of Yellow Native Tellurium.*

This ore contains, besides tellurium, gold, silver, lead, and sulphur, hence its analysis is more complicated than the former. It was analysed by Klaproth thus:

*Process* I.—Four hundred grains of the pulverized ore were digested with nitric acid, till every substance soluble in this fluid had been extracted.

II.—The nitric solution was combined with muriatic acid, till no further precipitate took place; by this there was obtained 51 grains of a white powder, of which 43 grains were again dissolved in boiling water. The insoluble part amounted to 8 grains: it was muriate of silver.

III.—The solution containing the 43 grains above mentioned, being concentrated by evaporation, yielded delicate crystals of muriate of lead.

IV.—The residue of process I. which was insoluble in nitric acid, was digested with nitro-muriatic acid, as long as any substance was taken up: the solution was mixed with the nitro-muriatic solution obtained before, and reduced by evaporation till it ceased to deposit muriate of lead: 11 grains were thus obtained.

V.—To the concentrated solution, process IV. was added potash in excess, which threw down a copious blackish-brown precipitate; this being separated, the alkaline fluid was saturated with muriatic acid, and the white precipitate obtained being again dissolved in muriatic acid, and then precipitated by means of a cylinder of zinc, afforded 85 grains of metallic tellurium.

VI.—The blackish-brown precipitate of process V. was dissolved in nitro-muriatic acid,

and the fluid nearly saturated with potash; ni-
trate of mercury was then added, till the preci-
pitate began to be white. This precipitate being
separated by the filter, and washed, the filter,
with its contents, was ignited in a crucible, and
a little nitre being added, the fire was increased,
and a button of pure gold was obtained, weigh-
ing 50,75 grains.

VII.—The remainder of the nitro-muriatic
solution was saturated with carbonate of potash,
and a precipitate was obtained, consisting of
oxid of manganese, mixed with carbonate of
lime and a little alumine and oxid of iron.

VIII.—The insoluble residue of process IV,
weighing 120,5 grains, and consisting chiefly of
quartz, was heated, by which it lost about 1
grain, which was sulphur: being then mixed
with four times its weight of carbonate of pot-
ash, and fused, there was obtained a button of
silver, weighing 10,125 grains.

Species IV.—*Analysis of the Foliated, or Black
Native Tellurium.*

This ore differs from the latter, by containing,
besides the metals, tellurium, gold, silver, and
lead, also a portion of copper, &c.

It was analysed by Klaproth in the following manner:

*Process* I.—One thousand grains of the pulverized ore were digested with ten ounces of muriatic acid, to which was added, by degrees, a little nitric acid: this being poured off, five ounces more of muriatic acid were added, by which every thing soluble in this fluid was dissolved. To the filtered solution boiling water was added, to re-dissolve the muriate of lead which had begun to make its appearance.

II.—The insoluble residue consisted for the most part of sulphur, weighing 17,5 grains: This being gently ignited, left 3,5 grains of a blackish matter which was dissolved in muriatic acid, and added to the foregoing solution. Hence the sulphur of the ore amounted to 14 grains.

III.—The remainder of the insoluble residue consisted chiefly of quartz, and weighed 440,5 grains. Being melted with four times its weight of carbonate of potash, there appeared, on breaking the mass, a few globules of silver, amounting to about 2,5 grains equivalent to 3,5 grains of muriated silver; so that the quartz matrix of the ore was equal to 437 grains.

IV.—The solution, process I. being concentrated by evaporation, crystals of muriate of lead were deposited, to the amount of 330 grains, which Klaproth considers as equal to 248 of metallic lead.

V.—Having thus separated the lead, the remainder of the solution was copiously diluted with alcohol, by which a white oxid of tellurium was thrown down. This oxid, being redissolved in muriatic acid, and again precipitated by soda, afforded 178 grains of oxid, equivalent to 148 grains of metallic tellurium.

VI.—The alcoholic solution was next distilled, by which the alcohol was separated; the remaining fluid being diluted with water, was treated with nitrate of mercury, in the way already described, page 263, by which a button of gold, weighing 41,5 grains was obtained.

VII.—The fluid left in process VI. was saturated with carbonate of soda and boiled, by which a bluish-grey precipitate was obtained: by digestion in muriatic acid it dissolved, and oxy-muriatic acid gas was produced: the muriatic solution being then super-saturated

A a

with carbonate of ammonia, there was deposited carbonate of manganese, mixed with iron, to the amount of 92 grains.

VIII.—The ammoniacal solution being of a blue colour, it was super-saturated with sulphuric acid, and a cylinder of iron being immersed in it, 6 grains of copper were deposited.

# ORDER XVII.

### ORES OF URANIUM.

The ores of this metal consist all of native oxids: they are the following:

*Division of Ores of Uranium.*

GENUS I.—*Oxids of Uranium.*

Species 1.—Black Oxid of Uranium, Pitch Ore, or Pitch Blende.

     2.—Micaceous Oxid of Uranium, or Green Uranite, or Chalcolite.

     3.—Uran Ochre, or Ochery Uranium.

### ANALYSIS OF ORES OF URANIUM.

Species 1.—*Analysis of Black Oxid of Uranium.*

In this ore uranium exists in combination with oxid of iron and sulphuret of lead.

A a 2

*Process* I.—Let one part of the ore finely pulverized, be digested repeatedly in four of dilute nitric acid, till the whole of the ore is dissolved, or till a new portion of acid occasions no farther action upon the residue; the black colour of the ore shows that its decomposition is complete.

II.—Evaporate the solution to at least onethird of its original bulk, and leave it to cool, a precipitate will become deposited, which is nitrate of lead, collect it by filtration. To ascertain the quantity of lead, add sulphuric acid, and proceed as directed, page 169.

To separate a small portion of iron which is generally dissolved by the acid, immerse a cylinder of zinc into the solution, the iron will become precipitated, if any was present.

III.—Into the nitric solution from which the lead has been separated, let fall a solution of potash, at a boiling heat, the precipitate which is formed consists of oxid of uranium and oxid of copper.

IV.—To separate these two metallic oxids, transfer the precipitate into a phial containing liquid ammonia, and digest for some days, the oxid of copper will become dissolved in the ammonia, and the oxid of uranium left behind :

transfer it on a filter, wash it, and when dry, weigh it; the loss indicates the quantity of oxid of copper contained in the solution; or better su persaturate the ammoniacal solution with sulphuric acid, and separate the copper in a metallic state by a cylinder of zinc. The oxid of uranium, then freed from copper, may be ab. stracted repeatedly with nitric acid, and lastly digested in dilute nitric acid, which will dissolve the uranium, and leave oxid of iron, if any was present.

V.—To the nitric solution of the oxid of uranium add potash, and boil the whole for a few minutes, pure yellow oxid of uranium will thus be obtained.

The undissolved residue of process I. is a mixture of silex, sulphur, and perhaps iron, which was contained in the ore: the sulphur may be separated as stated before, page 117. The iron may be separated by liquid ammonia, the remainder is silex.

The rest of the ores of uranium may be analysed in a similar manner.

# ORDER XVIII.

### ORES OF MOLYBDENA.

*Division of Ores of Molybdena.*

GENUS I.—*Sulphuret of Molybdena.*
Species 1.— Common Sulphuret of Molyb-
dena.

GENUS II.—*Salt of Molybdena.*
Species 1.—Molybdate of Lead.

### ANALYSIS OF ORES OF MOLYBDENA.

*Process* I.—Take one part of the ore freed
from its matrix, and finely levigated, put it
into a retort containing 3 parts of nitric acid,
adapt a receiver, and distil till no more drops
fall from the neck of the retort, affuse a new
portion of acid on the residue, distil it off again,
and repeat this operation for several times suc-
cessively, until the whole of the ore be converted
into a white powder.

II.—Wash this powder in water, and dry it: it is the oxid, or acid of molybdena·

III.—Mingle the water used for washing the acid, after having concentrated it by evaporation with ammonia, till no farther precipitate ensues; add more ammonia till the precipitate is re-dissolved, and then drop into it nitric acid to saturate the excess of the ammonia, a precipitate falls down, it is also a portion of acid of molybdena, separate it by the filter, and add it to that obtained before.

IV.—Having done this, add muriate of barytes to the solution in order to ascertain the quantity of sulphuric acid formed during the process, from which the quantity of sulphur may be inferred according to the rules described, page 117.

V.—Having so far proceeded, re-dissolve the molybdic acid obtained in process III. and I. in concentrated sulphuric acid, dilute the solution with 10 times its weight of water, and drop into it ammonia, to neutralize exactly the sulphuric acid, if the molybdic acid was contaminated with iron, it will fall down in the form of a brown oxid.

VI.—To obtain the molybdic acid from the fluid left in experiment V. evaporate the solution to

dryness, and heat the salt to a dull redness, the sulphate of ammonia formed will be volatilized. If on the remaining mass nitric acid now be poured and abstracted from it repeatedly, a yellow powder will be obtained, which is pure molybdic acid.

*Remark.*—In this analysis the molydena is obtained in the state of an acid, or in combination with oxigen, but in the ore it exists in the metallic state. The composition or proportion of oxigen and metallic molybdena forming the molybdic acid not being yet determined, this analysis can only yield an approximation to truth.

### ANALYSIS OF MOLYBDATE OF LEAD.

*Process* I.—Let one part of the ore be repeatedly boiled in sulphuric acid, till the acid refuse to dissolve any more, this solution which should have so little excess of acid as possible, contains the oxid, or acid of molybdena, and oxid of iron.

II.—The insoluble residue which consists mostly of sulphate of lead, must be boiled for some time with carbonate of soda, and then washed.

III.—Upon the washed precipitate pour very dilute nitric acid, in order to effect a solution. The insoluble powder (if any) is silex.

IV.—Decompose the nitric solution by the addition of sulphuric acid, the precipitate obtained, is sulphate of lead.

V.—Saturate this solution with liquid ammonia, if a precipitate ensues it is iron that was contained in the ore, collect and dry it.

VI.—Having thus far proceeded, subject the sulphuric solution, process I. to the same treatment as stated before, process VI. page 271.

## ORDER XIX.

### ORES OF CHROME.

*Division of Ores of Chrome.*

Genus I.—*Salts of Chrome.*

Species 1.—Chromate of Lead, or Red Lead
            Ore of Siberia.
     2.—Chromate of Iron.

Genus II.—*Alloys of Chrome.*

Species 1.—Needle Ore.

Genus III.—*Oxids of Chrome.*

Species 1.—Chrome Ochre.

### ANALYSIS OF ORES OF CHROME.

Species 1.—*Analysis of Chromate of Lead.*

*Process* I.—Let one part of the finely leviga-
ted ore be boiled in forty parts of a solution of
super-carbonate of potash, containing 3 parts of
solid carbonate of potash, for 1 hour at least,

renewing the water as it evaporates from time to time, and lastly decant the supernatant fluid.

II.—Upon the mass obtained, which consists of carbonate, and undecomposed chromate of lead, after having been washed in water, pour dilute nitric acid till it ceases to effervesce. The solution is nitrate of lead.

III.—The residue which resists the action of nitric acid, consists of chromate of lead, let it be again boiled with three times its weight of super-carbonate of potash, and a sufficient quantity of water; decant the fluid; apply nitric acid to the residue, and endeavour to effect a solution, which should be added to that obtained before. If any residue remains, treat it in a similar manner, and mingle all the different nitric solutions.

IV.—Having concentrated the nitric solutions, drop into it sulphuric acid, or a solution of sulphate of soda till no farther cloudines sensues; the obtained precipitate is sulphate of lead, 100 parts = to 30 of metallic lead.

V.—To ascertain the quantity of chromic acid add to the alcaline solutions, which were decanted from the carbonate of lead, process I. and III. dilute] nitric acid as long as any effervescence takes place; if the fluid be now

evaporated, crystals of chromate of potash mixed
with nitrate of potash will be obtained.

VI.—To ascertain the quantity of chromic
acid, dissolve the salts obtained in water, and
drop into it nitrate of lead till no farther
cloudiness ensues.   The precipitate is chro-
mate of lead, 100 parts are = to 35 of chro-
mic acid.

The analysis of chromate of lead may likewise
be effected by muriatic acid, in the following
manner:

*Process* I.—Take one part of the ore levigated
as finely as possible, pour over it 2 parts of mu-
riatic acid diluted with 1 part of water, digest
for about 2 hours, decant the fluid, wash the
residue, and repeat this operation for several
times successively, or until the whole of the
chromate of lead is converted into a white
powder.

II.—The obtained solution consists of chro-
mic acid, holding in solution a portion of mu-
riate of lead.   To get rid of the latter evoporate
it, and suffer it to stand undisturbed for a few
days, a precipitate will fall down, which is
mnriate of lead.

III.—To free the solution from the muriatic
acid, add to it gradually oxid of silver, obtained

by decomposing a solution of nitrate of silver by potash, till the last portion of this substance acquires a red or purple colour. The whole of the muriatic acid will thus be got rid of, and the fluid contain only chromic acid, in a pure state.

Species 3.—*Analysis of Chromate of Iron.*

*Process* I.—Let one part of the ore mingled with two of potash, be fused for at least one hour in a silver crucible; pour the mass into a conveninent vessel, and when cold boil it in a sufficient quantity of water, for half an hour, and filter the fluid.

II.—Digest the insoluble part in muriatic acid, decant the solution, wash the residue, and thus treat it alternately with potash and muriatic acid, till the whole is dissolved.

III.—Evaporate the muriatic solution to dryness, wash it in water, and filter it. The residue (if any) is silex.

IV.—Into the fluid from which the silex has been separated drop ammonia in excess. The obtained precipitate is oxid of iron.

V.—Neutralize carefully the alcaline solutions with nitric acid, if a precipitate ensues it

is alumine. If to the remaining fluid nitrate of lead be now added, the precipitate which falls down is chromate of lead, 100 parts when dry indicate 35 of oxid, or acid of chrome.

VI.—The nitric solutions which contain a portion of iron, together with perhaps a little chromic oxid, may now be mingled together. To separate the latter, drop into it a solution of carbonate of potash, collect the precipitate, and boil it in a solution of potash. What remains is iron.

The rest of the ores of Chrome may be analysed in a similar manner.

## ORDER XX.

### ORES OF TITANIUM.

*Divison of Ores of Titanium.*

GENUS I.— *Oxids of Titanium.*

Species 1.—Titanium of Kirwan, Red Shorl,
   or Rutile Brown Titanium.

  2.—Brown Ore of Kirwan, Sphene,
   or Rutilite.

  3.—Menachanite, or Black Oxid of
   Titanium with iron and man-
   ganese.

  4.—Iserin, or Oxid of Titanium, with
   Iron and Oxid of Uranium.

  5.—Nigrine, Titanite of Klaproth,
   or Calcareo Siliceous Oxid of
   Titanium.

  6.—Octohedrite, Oisanite, Anatase,
   or Blue Shorl.

Bb 2

### ANALYSIS OF ORES OF TITANIUM.

Specis 1.—*Analysis of Titanium, Red Shorl, or Rutile.*

In this ore oxid of titanium exists in a pure state, or nearly so. Its analysis is very easy, and may be effected thus:

*Process* I.—Let one part of the ore reduced to an impalpable powder be fused in a silver crucible, with four or five of potash or soda, or carbonate of potash.

II.—Soften the fused mass in water, and boil the whole in that fluid for a few minutes, a precipitate will fall down, which is oxid of titanium nearly pure.

III.—Let the fluid from which the oxid of titanium is separated, be again concentrated by evaporation, it may contain a minute quantity of silex and alumine, and perhaps oxids of iron and manganese, all of which may be separated, as stated before. See analysis of iron ores.

IV.—Dissolve the oxid of titanium in sulphuric acid, on adding to this solution phosphoric acid; the titanium will be precipitated, and the iron, if it contains any, left behind.

## Species 2.—*Analysis of Rutilite.*

In this ore oxid of titanium exists with lime and silex. It was analysed by Klaproth thus :

*Process* I.—One hundred grains of the finely levigated ore were fused for one hour in a silver crucible with four times their weight of potash. The mass being softened with water, and digested in muriatic acid, left undissolved 12 grains of silex.

II.—The muriatic solution was decomposed by carbonate of potash ; the precipitate being digested in muriatic acid left 23 grains of silex.

III.—To the solution from which the silex had been separated ammonia was added, till no farther cloudiness ensued. The obtained precipitate, which was oxid of titanium, after being ignited, weighed 33 grains.

IV.—The remaining fluid being saturated at a boiling heat by carbonate of potash, yielded 33 grains of carbonate of lime.

## Species 3.—*Analysis of Menachanite.*

In this ore oxid of titanium exists in combination with oxid of iron and oxid of manganese.

A specimen of this ore was examined by Vauquelin in the following manner:

*Process* I.—One hundred grains of the finely pulverized ore were fused with 400 of potash for one hour and a half: the fused mass was of a green colour. On being softened with water a brick-red powder became separated, weighing 124 grains.

II.—The obtained brick-red precipitate was boiled in a solution of potash for one hour, and the solution, after saturation with muriatic acid, yielded by the admixture of carbonate of potash a precipitate being oxid of titanium, weighing 3 grains.

III.—The remaining insoluble part, left in process II. was digested in muriatic acid, which acquired a yellow colour. The insoluble part, which weighed 46 grains, was oxid of titanium.

IV.—The obtained muriatic solution yielded, by being mingled with ammonia, 50 grains of oxid of iron.

V.—The alcaline solution, process I. was saturated with muriatic acid, and yielded by carbonate of potash 2 grains of carbonate of manganese.

From what has been stated, the analysis of all the rest of the ores of titanium becomes obvious.

## ORDER XXI.

### ORES OF MANGANESE.

*Division of Ores of Manganese.*

GENUS I.—*Oxids of Manganese.*

Species 1.—Grey Oxid of Manganese.

    Subspecies 1.—Radiated Grey Oxid of Manganese.

          2.—Foliated Grey Oxid of Manganese.

          3.—Compact Grey Oxid of Manganese.

          4.—Earthy Grey Oxid of Manganese.

Species 2.—Black Oxid of Manganese.

       3.—Red Oxid of Manganese.

GENUS II.—*Sulphuret of Manganese.*

Species 1.—Black Sulphuret of Manganese, or Black Blende.

**GENUS III.**—*Salts of Manganese.*

Species 1.—Phosphate of Manganese and Iron.

    2.—Carbonate or White Oxid of Manganese.

### ANALYSIS OF ORES OF MANGANESE.

Although the analysis of the ores of manganese is upon the whole not difficult, chemists nevertheless do not agree with regard to the best modes to be practised in the examination of these ores. The proceedings which render the analysis of ores of manganese difficult, effect chiefly the modes of ascertaining with accuracy the quantities of oxid of iron and oxid of manganes, the modes of separating them, as well as the mode of determining that portion of oxigen which is capable of being disengaged, either by the mere action of heat, or by the application of muriatic acid: a circumstance on which the goodness or excellency of these ores when employed for the purposes of the bleacher, chiefly depend.

The foreign matters which are found in ores of manganese are chiefly the following: oxid of iron, silex, barytes, alumine, carbonarte of lime, car-

bon, and water. These substances are often present in such quantities as to render the ore almost useless to the bleacher. The presence of carbonate of lime is particularly hurtful; for when to this manganese, muriatic acid, or muriate of soda, and sulphuric acid be added, an effervescence takes place, which often forces the bleaching materials into the apparatus destined to receive the gas only, and thus totally spoils the operation.

Hence the ores of manganese most esteemed by the bleachers, are those which are nearly free from foreign matters, and amongst these the manganese of the North-hill mines, near Collington, in Cornwall, and those of Upton pine, near Exeter, undoubtedly hold the first place: they are composed of about 78 of oxid of manganese, whereas none of the ores of this metal discovered elsewhere have been found to contain more than 67 of this oxid.

The analysis for detecting the foreign bodies, found in the ores of manganese, may be conducted in the followign manner:

Take 400 grains of the ore peviously reduced to a fine powder, and dried at 212° Fahr. divide the whole into two equal parts, and treat the first 200 grains in the following manner.

*Process* I.—Put the ore into a small retort,
and pour upon it about twice its weight of mo-
derately dilute and colourless nitric acid; the
carbonic acid of the carbonate of lime will be
thus disengaged without the application of heat,
and may be received in an inverted jar of lime-
water; from the regenerated carbonate of lime
thus produced, its acid may be calculated ac-
cording to the known proportions. When the
evolution of carbonic acid ceases, transfer the
contents of the retort into a flask, add a small
piece of sugar, and apply a gentle heat; when
the action of the acid has ceased, pour off the
fluid, and digest the remainder again with nitric
acid and sugar as long as any thing ceases to be
taken up; then mix together the nitric solutions
and the washings of the undissolved residue.

II.—The residue left in the last process being
dried at a heat below ignition and weighed, must
be ignited in an open crucible to burn off the
carbon, the amount of which will be indicated
with sufficient exactness by the difference of
weight before and after ignition.

III.—The residue of process II. is next to be
boiled to dryness in a silver crucible with thrice
its weight of liquid caustic soda; the hardened
mass is to be dissolved in dilute muriatic acid,

then evaporated nearly to dryness, and again boiled with water; a white powder remains, which is silex.

IV.—Add together the nitric solution, process I. and muriatic solution, III. and pour in liquid ammonia as long as any precipitate takes place; separate it, and add the washings to the clear liquor.

V.—To the clear fluid of process IV. add a slight excess of sulphuric acid, and make the whole boiling hot; the precipitate being speedily separated by the filter and washed, is sulphate of barytes.

VI.—Evaporate the clear fluid of process V. to a very small bulk, and mix it with cold alcohol; the precipitate is sulphate of lime.

VII.—The precipitate of process IV. is now to be digested in soda: when the action of the alcali ceases, pour off the liquor, wash the residue, add the washings to the liquor, neutralize it with muriatic acid, and then pour in carbonate of ammonia, till no further precipitate takes place. The precipitate being washed and ignited is alumine.

VIII.—The residue of process VII. which is insoluble in soda, consists of the mixed oxids of manganese and iron, which may be separated

as stated page 189, process X. or, dissolve the
mixt oxid in muriatic acid; saturate the solution
by potash, and decompose it by succinate of soda,
or ammonia: the precipitate is succinate of iron:
100 parts of it, after being ignited with a little
wax = to 70 of iron.

IX.—To the fluid of process VII. add soda;
the precipitate, when washed and ignited in an
open crucible, is oxid of manganese in a pure
state.

The component parts of the ore are now all
ascertained except the water and loose oxigen,
in order to determine these we must have re-
course to the second portion of the ore, weighing
like the first 200 grains.

*Process* I.—Put the ore into a small glass
retort connected with a pneumatic mercurial
apparatus, and make the bulb of the retort
moderately red-hot as long as any gas is dis-
engaged. By this means the water will be con-
densed in the receiver, and the gas will pass
forwards into the inverted jar.

II.—The air thus collected being mixed with
sulphate of iron, impregnated with nitrous gas,
the amount of its oxigen is readily ascertained.
The weight of the oxigen added to that of the
brown oxid of manganese gives very nearly,

though somewhat less than the entire weight of
the manganese in the state in which it exists in
the ore. The *disposable* oxigen, or that which
may be applied to the preparation of oxy-muriatic
acid, is found, by deducting 6 per cent. from the
brown oxid, and adding this to the weight of the
gazeous oxigen. Of the *disposable* oxigen, 16
parts represent 100 of oxy-muriatic acid, produ-
ced by distilling together the ore and common
muriatic acid, or in any other way.

#### ANALYSIS OF OXIDS OF MANGANESE.

### Sub-species 1.—*Analysis of Radiated Grey Oxid of Manganese.*

A specimen of radiated grey oxid of manga-
nese was examined by Klaproth in the following
manner :[x]

*Process* I. — Two hundred grains of the finely
pulverized ore were digested without heat in a
sufficient quantity of muriatic acid : a solution
was gradually effected, with the extrication of
much oxy-muriatic acid gas. The solution,
which was of a dark brown colour, was divided
in two equal parts, the ores of which were
examined in the following manner:

* Analytical Essays, vol. I. p. 243.

C C

II.—Sulphuric acid dropt into the muriatic solution of manganese occasioned no precipitate: hence no barytes could be present.

III.—Triple prussiate of potash occasioned a a slight peach-blossom coloured precipitate, therefore scarcely any oxid of iron was present.

IV.—Carbonate of potash occasioned a white precipitate which did not change its colour on exposure to the air.

V.—Solution of soda or potash produced no effect.

VI.—Water impregnated with sulphuretted hidrogen gas produced no turbidness.

VII.—The other half of the solution was neutralized with a solution of carbonate of potash till a slight turbidness ensued; it was then boiled and filtered, and the insoluble powder which was oxid of iron separated by the filter.

VIII.—To the remaining fluid carbonate of potash was added to full saturation, at a boiling heat; a precipitate was thus obtained, which after being dried and strongly ignited, weighed 88,5 grains.

IX.—Two hundred grains more of the ore were heated thoroughly red-hot in a glass retort, connected with a pneumatic apparatus, the products obtained were 14 grains of water,

and 4,5 of oxigen gas. Hence 100 parts of the ore contain

> 90, 5 Brown oxid of manganese.
> 2,25 Oxigen.
> 7 Water.
> ———————
> 99,3

Sub-species 3.—*Analysis of Compact Grey Oxid of Manganese.*

The analysis of this ore was conducted by Vauquelin, thus :*

*Process* I.—One hundred parts of the finely levigated ore were repeatedly digested in mu- riatic acid to effect a solution. The residue amounted to 1,6 part : it was a black substance, which on exposure to the air inflamed, and left behind 1,2 parts of silex.

II.—To the obtained solution sulphuric acid was added till no farther cloudiness ensued. It was sulphate of barytes, amounting to 21 parts, which are equal to 14 of barytes.

* Journal des Min. No. XIX p. 40

III.—To the fluid from which the sulphate of barytes had been separated carbonate of potash was added till no farther cloudiness ensued; the obtained precipitate after being dried and strongly ignited, yielded 48 parts of oxid of manganese. Thus 100 parts of the ore contained

        48    Oxid of Manganese.
        14    Barytes
        1,2   Silex.
        4     Carbon.
        ―――――――
        **63,6**

The remaining 36,4 parts requisite to make up the original weight of the ore employed, Vauquelin considers as oxigen employed in the production of oxy-muriatic acid (process I.) This, however, is probably a mistake: the ore perhaps contained some water, of which no notice is taken in the analysis; to this might be added as an established fact, that 100 parts of metallic manganese when precipitated from a solution in an acid by potash or soda, yield 168 black oxid of manganese; and hence 48 parts even of metallic manganese, require only 32 of oxigen.

Sub-species 4.—*Analysis of Earthy Grey Oxid of Manganese.*

The analysis of this ore wes performed by Klaproth in the following manner :*

*Process* I.—One hundred grains of this ore readily dissolved in the muriatic acid, that was poured upon it in the cold. They afforded with it a very dark-brown fluid : but this, after some digestion, with the assistance of heat, assumed a bright yellow colour. It deposited a blackish-grey sediment, which, upon moderate ignition in a covered crucible, weighed 9 grains. By subsequent ignition in an open vessel, its colour changed to a greyish-white, and its weight diminished about 1 grain. Therefore that blackish colour had arisen from a portion of carbon.

II.—Into the clear muriatic solution was dropped sulphuric acid. It became moderately turbid, and let fall a fine white powder, which, after being collected and examined, proved to be sulphate of barytes. It weighed $1\frac{1}{2}$ grains, equivalent to 1 grain of barytes.

III.—The solution was now combined with

* Analytical Essays, vol. I. p. 249.

C C 3

carbonate of potash, till it became turbid, and
the mixture heated to ebullition. An oxid of
iron separated, weighing $6\frac{1}{2}$ grains, after having
been heated red hot.

IV.—From the remaining fluid, left in pro-
cess III. which was colourless, white oxid of
manganese was precipitated by the addition of
carbonate of potash at a boiling heat. This
oxid being brought to the state of the brown
oxid, by igniting it in a covered crucible,
weighed 68 grains;

Therefore, the constituent parts of this ore,
are,

Brown Oxid of Manganese 68
Oxid of Iron _____ 6,50
Carbon _____ 1,
Barytes _____ 1,
Silex _____ 8,
Water _____ 17,50
                              ———
                               102

The increase of weight, in this sum, proba-
bly depends, according to Klaproth, on this
circumstance, that the ignited oxid of manga-
nese had afterwards combined with a greater

proportion of oxigen, than it contained in the
natural composition of the crude ore.

### ANALYSIS OF SULPHURET OF MANGANESE.

*Process* I.—One hundred grains of the ore
were strongly ignited in a glass retort, connected
with the pneumatic mercurial apparatus. The
neck of the retort was found lined with nothing
else but a hardly perceivable aqueous dew. The
gas obtained was carbonic acid gas, without any
trace of sulphuretted hydrogen, and amounted
to 7 cubic inches, or about 5 grains in weight.

The remainder of the ignited ore had under-
gone no change.

II.—Another hundred grains of the same
ore were covered by degrees with moderately
strong nitric acid. As often as any part of this
fluid was poured upon it, a violent action took
place, accompanied with an effervescence, and
the extrication of sulphuretted hydrogen gas.
The mixture was at first turbid and brown; but
on affusing the last portion of the acid it
became yellow and milky, much heated, and
emitted white vapours, which lined the neck of
the mattrass with a yellow sulphureous coating:
and the sulphur, which, at the beginning, sepa-

rated in detached delicate flocks, collected in a
yellowish grey porous mass.

III.—This mass, when separated by filtration,
washed and dried, weighed 16 grains. On
being moderately heated, it suffered a loss of 5
grains, which were sulphur and burned off. The
residue being treated again with nitric acid,
became dissolved; leaving $\frac{1}{2}$ grain more of
sulphur.

IV.—The filtered solution possessed a pale
reddish colour, but was entirely deprived of it
by dilution with water. To one half of it was
added a solution of soda. The oxid of manga-
nese, precipitated by it, very soon acquired a
brown tinge on exposure to air. The other half
of the solution was precipitated by carbonate of
soda, the oxid of manganese thus obtained, re-
tained its whitish colour unaltered in the air.

V.—Upon another 100 grains of pulverized ore
were poured nitric acid, weakened with twice its
weight of water, the vessel being equi-poised,
together with its contents. Here the sulphuretted
hydrogen gas was disengaged without heat; and
that portion of it which escaped, occasioned a
loss of 34 grains of weight. What remained of
the separated sulphur, floated upon the solution
in the form of brown, light flocks. The residue

collected on the filter, weighed $3\frac{1}{2}$ grains after drying. When moderately heated, only $\frac{3}{4}$ of a grain of sulphur burned away. The residue now was soluble in nitric acid, except $\frac{1}{4}$ grain of sulphur, and a few particles of quartz.

V.— When the filtered pale rose-red solution was precipitated by carbonate of soda, no effervescence ensued. The precipitated oxid appeared of a bright slate-grey; but, even while yet moist, it lost this colour again, and became white by being exposed to the air on the filter. This colour, Klaproth supposes, arose from a slight portion of the sulphuretted hydrogen gas, which still adhered to the precipitate, and was afterwards expelled by the process of washing. Of this carbonate of manganese, dried, the weight was 145 grains; but after it had been strongly ignited in a small retort, to which a receiver was joined, it weighed 82 grains. The ignited oxid retained its white colour, while the vessel was kept closed, except that its surface acquired a brown tinge.

VI.—To this ignited oxid were added, before it cooled, 41 grains of sulphur, and the retort being connected with a receiver brought to ignition in a sand-heat. After cooling the excess of sulphur was found sublimed. The residue

weighed 98 grains, and had a pale green colour,
This artificial sulphuret of manganese dissolved
in dilute nitric acid, like the crude natural sul-
phuret, with effervescence, and a developement of
sulphuretted hydrogen gas.   In this experiment
hardly any portion of sulphur remained.

VII.—Another clear solution of this black
ore of manganese in nitric acid was evaporated
in a retort to perfect dryness; it emitted deep
red nitrous vapours, at the end of the process.
The residue looked like an iron-grey solid
mass, in part possessed of a metallic lustre.   It
was manganese completely saturated with oxigen,
at the expense of the nitric acid employed.

VIII.—The muriatic and dilute sulphuric
acids dissolve this mineral as easily as the nitric.
These solutions were attended with effervescence
and extrication of sulphuretted hydrogen gas;
they were of a pale-red, and yield, after filtration by
the addition of carbonate of potash, a pure, white,
carbonate of manganese, which turned black by
ignition in an open vessel.   When in this state,
it was found insoluble in nitric acid:   but a
perfect and colourless solution was obtained as
soon as a little sugar was added.   Prussiate of
potash afforded with this solution a pale bluish
precipitate.

The analysis being now compleated, the consti-
tuent parts of this ore are, Klaproth states thus:

  White Oxid of Manganese   82
  Carbonic Acid ..........   5
  Sulphur ..............  11
        —————
        98

 Concerning the traces of quartz and iron, in
in the pure selected specimens of this ore,
Klaproth found them too slight to deserve being
put in the account.

 *Remark.*—It is singular that Klaproth should
enumerate carbonic acid as a constituent part of
the ore, for this gazeous fluid would have made
its appearance by the action of heat, if simply
charcoal had been present. And as sulphuretted
hydrogen gas was evolved by the application of
nitric acid, there is reason to suppose that the
manganese existed in the ore in the metallic
state, or at least nearly so. The quantity of
sulphur also appears to be rated much too low.
For sulphuretted hydrogen gas contains about
71 per cent. of sulphur, therefore 34 grains of
the gas contain 24 grains, to which is to be
added 1 grain of sulphur, left in the nitric

solution, after the disengagement of the sulphu-
retted hydrogen gas : hence the whole amount
of sulphur would be 25 grains; and 82 grains of
white oxid of antimony contain 66 of manga-
nese, and 16 of oxigen.  Hence the above state-
ment thus corrected would give the component
parts of the ore thus:

<div style="text-align:center">

Manganese.......... 66
Sulphur ........... 25
Carbon and Oxigen .  4
                   ————
                    100

</div>

### ANALYSIS OF SALTS OF MANGANESE.

Species 1.—*Analysis of Phosphate of Manga-
nese.*

For the composition of this ore we are in-
debted to Vauquelin,* who ascertained its con-
stituent parts in the following manner :

*Process* I.—One hundred grains of the finely
levigated ore, were boiled with a solution of
potash for some time, and lastly evaporated to
dryness in a silver bason.

II.—The alcaline mass was diffused through

* An. de Chem. XLI  p. 242.

water, and the insoluble part separated by the filter. It weighed a little more than the entire weight of the ore employed.

III.—The alcaline solution was slightly super-saturated with nitric acid, and then mingled with lime water till no farther cloudiness ensued. The obtained phosphate of lime, when dried, weighed 60 parts, which are equal to 27 of phosphoric acid.

IV.—The residue which resisted the action of the alcali, process I. was digested in acetous acid, and the whole evaporated carefully to dryness. The same operation was repeated for several times successively, and lastly it was again slightly digested in acetous acid, and the insoluble part separated by the filter. This insoluble part was oxid of iron, weighing 31 parts.

V.—The fluid obtained in process IV. was decomposed by potash; the obtained precipitate, which was oxid of manganese, after being dried, weighed 42 grains.

# ORDER XXII.

## ORE OF COLUMBIUM.

As only one *single* specimen of this ore is at present known, there are of course no ores of the metal called columbium. Though there is reason to believe that they will be discovered in North America.

### ANALYSIS OF THE ORE OF COLUMBIUM.

Mr. Hatchett, who discovered this ore in the year 1802, on examining and arranging the minerals of the British Museum, conducted his analysis in the following manner :

*Process* I.—One part of pulverised ore was mixt with 5 times its weight of carbonate of potash, and fused in a silver crucible.

II.—The alcaline mass was dissolved in boiling water, the insoluble part separated by the filter, and repeatedly washed in water.

III.—The filtered fluid was mingled with muriatic acid in excess, the result was a white flocculent precipitate, being columbic acid contained in the ore.

IV.—The insoluble residue of process II .was digested in muriatic acid, in order to get rid of the iron ; the acid being decanted, the residuum, after being washed, was again fused with carbonate of potash, dissolved and precipitated with nitric acid alternately, till the whole was decomposed.

V.—The muriatic solution was now decomposed by liquid ammonia, a copious ochreaceous precipitate fell down, which was re-dissolved in nitric acid, and the solution decomposed by means of ammonia. The iron was thus obtained.

VI.—The different alcaline solutions were mixed together, and being supersaturated with nitric acid, yielded the same white precipitate, (columbic acid.) The fluid from which the precipitate had been separated by nitric acid, was then saturated with ammonia, and after being boiled afforded a small quantity of oxid of iron. 200 parts of the ore, thus analysed, yielded Mr. Hatchett 42 of oxid of iron, and 155 of columbic acid. For a fuller account of Mr. Hatchett's analysis we refer the reader to his paper in the Philosophical Transactions, 1802, part I. p. 46.

## ORDER XXIII.

### ORES OF TANTALIUM.

*Division of Ores of Tantalium.*

With the nature of these ores we are yet but very imperfectly acquainted. The ores of tantalium have been met with in small quantities only, in Sweden. They were discovered by Mr. Eckeberg. These ores are,

*Tantalite,* a compound of oxid of tantalium, iron, and manganese, and

*Yttrotantalite,* a compound of tantalium, iron, uranium, tungsten, and yttria. The peculiar metal which exists in these ores is said to be distinguished from all others by being insoluble in any of the acids. Whether this substance will retain its place among the metals, must be left to future investigation ; at present we have only the authority of Mr. Eckeberg for inserting it.

The tantalium was obtained from the ore, by treating it repeatedly with alcalies, and nitromuriatic acid in the usual manner. The alca-

line solution, being supersaturated with an acid, deposited a white powder, which is the oxid of tantalium. The specific gravity of it, after ignition, was = 6,5. This oxid after being intensely heated, in contact with charcoal powder, acquired a metallic aspect. For a farther account the reader is referred to the Journal de Min. No. 20, An. x. p: 248.

## ORDER XXIV.

### ORE OF IRIDIUM AND OSMIUM.

For the discovery of this ore which contains two peculiar metals, we are indebted to Dr. Wollaston, who found it mixed with the ore of platina: it was long mistaken by chemists for plumbago. It has been mentioned already (see ore of platina) that when the ore of platina is digested with nitro-muriatic acid, an insoluble substance is left, containing two new metals, namely, iridium and osmium.

The ore of iridium, which is thus obtained, is an alloy of iridium and osmium, it is harder than the ore of platina, it is composed of scales and partly of a powder of a peculiar lustre. Its specific gravity = 19,7. There are some varieties of the ore of platina, in which this black powder, or ore, exists in larger proportions than in others.

### ANALYSIS OF THE ORE OF IRIDIUM AND OSMIUM.

The analysis of the ore of iridium may be

accomplished, according to Mr. Tennant, in the following manner:

*Process* I.—Fuse one part of the ore in a silver crucible, with 4 of potash, for about 1 hour, in a dull red heat; dissolve the mass in water, separate the insoluble residue, and wash it in water. The alcaline solution has a deep orange or yellowish brown colour.

II.—Transfer the insoluble part which resisted the action of the alcali into a Florence flask, cover it with about 4 parts of muriatic acid, and digest it in a gentle heat for 2 or 3 hours. Decant the supernatant fluid, wash the residue in water, and dry it.

III.—Let the powder, left in process II. be again treated alternately with potash and muriatic acid, until a compleat solution is effected. The acid solution contains the muriate of iridium, with a small portion of muriate of osmium, and the alcaline solution contains the oxid of the metal called osmium. To separate these two, proceed as follows:

IV.—Evaporate the solution of muriate of iridium slowly to dryness in a glass capsule, re-dissolve the mass in water, and suffer it to crystallize. The crystals are pure muriate of iridium. If these crystals be exposed to heat,

both the muriatic acid, as well as the oxigen, are driven, and metallic iridium is obtained in a state of purity. The metal may likewise be obtained by immersing into the muriatic solution of iridium, any metal, except gold and platina; a black powder falls down, which is metallic iridium; the former process, however, is preferable.

V. The osmium may be obtained by simply distilling the alcaline solution, previously mingled with sulphuric acid in excess. The oxid of osmium is volatilized and passes over with the water into the receiver.

Another mode of obtaining the oxid of osmium consists in distilling at a red heat with nitrate of potash; the black powder procured from the ore of platina. By this means the oxid of osmium sublimes into the neck of the retort in the form of a semi-transparent mass, possessing the properties of the metal called osmium, in a high degree.

## ORDER XXV.

### ORE OF CERIUM.

Since the printing of the preceding sheets a new metallic ore has been discovered, to which the name of cerite has been given. It was discovered by Heisinger and Berzelius, at Bastnas, in Westmanland in Sweden. The metallic oxid which this mineral contains, was regarded by Klaproth as an earth, to which he gave the name of ochroite. But Vauquelin and the Swedish chemist, who also analysed the fossil, consider it as a metallic oxid, which like yttria forms the connecting link between the earths and metals.

ANALYSIS OF THE ORE OF CERIUM.

*Process* I.—Levigate a determinate portion of the ore and ignite it. The loss gives the quantity of water.

II.—Digest the ore repeatedly in nitro-muriatic acid till no farther action takes place.

III.—Fuse the residue which resisted the action of nitro-muriatic acid with potash, dissolve the mass in water, evaporate to dryness, pour on the dry mass dilute nitric acid, digest the whole; lastly, decant the fluid. The insoluble part is silex: let it be washed, ignited, and weighed.

IV.—Mingle the nitro-muriatic solution, process I. with the muriatic solution from which the silex has been separated, and decompose it at a boiling heat by the admixture of super-carbonate of potash, and collect the precipitate.

V.—Re-dissolve the obtained precipitate in as little muriatic acid as possible, make it boiling hot, and add to it liquid ammonia in excess, and collect the precipitate. It consists of oxid of cerium and oxid of iron.

VI.—Saturate the ammoniacal fluid obtained in process IV. with muriatic acid, and then add to it carbonate of ammonia, the precipitate obtained is carbonate of lime. This after being exposed to a red heat, gives the quantity of lime that was present in the ore.

VII.—Re-dissolve the precipitate obtained in process IV. in muriatic acid, and drop into it a solution of hydro-sulphuret of potash till the precipitate, which at first will be of a greenish colour, becomes white, and then filter the whole.

VIII.—Into the fluid obtained in process VI. let fall a solution of carbonate of potash, till no farther cloudiness ensues. The precipitate thus obtained is carbonate of cerium. Let it be heated to drive off the carbonic acid.

IX.—Re-dissolve the precipitate obtained in process VI. in as little muriatic acid as possible, and then neutralize the solution by potash. If to this fluid a solution of sulphate of soda is added, a precipitate falls down, which is sulphate of cerium; separate it by the filter.

X.—To the fluid from which the sulphate of cerium is obtained, add liquid ammonia in excess, a precipitate ensues, which is oxid of iron.

XI.—Transfer the sulphate of cerium, process IX. into a flask, and boil it with about 4 times its weight of carbonate of potash, and a sufficient quantity of water, it will thus become converted into carbonate of cerium. If this carbonate of cerium, together with that obtained before, process VII. is exposed to a red heat, till all the carbonic acid is expelled, the metal will be left behind in a pure state.